

DOT/FAA/AR-06/10

Air Traffic Organization
Operations Planning
Office of Aviation Research
and Development
Washington, DC 20591

Guidelines and Recommended Criteria for the Development of a Material Specification for Carbon Fiber/Epoxy Fabric Prepregs

May 2007

Final Report

This document is available to the U.S. public
through the National Technical Information
Service (NTIS), Springfield, Virginia 22161.



U.S. Department of Transportation
Federal Aviation Administration

NOTICE

This document is disseminated under the sponsorship of the U.S. Department of Transportation in the interest of information exchange. The United States Government assumes no liability for the contents or use thereof. The United States Government does not endorse products or manufacturers. Trade or manufacturer's names appear herein solely because they are considered essential to the objective of this report. This document does not constitute FAA certification policy. Consult your local FAA aircraft certification office as to its use.

This report is available at the Federal Aviation Administration William J. Hughes Technical Center's Full-Text Technical Reports page: actlibrary.tc.faa.gov in Adobe Acrobat portable document format (PDF).

1. Report No. DOT/FAA/AR-06/10	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle GUIDELINES AND RECOMMENDED CRITERIA FOR THE DEVELOPMENT OF A MATERIAL SPECIFICATION FOR CARBON FIBER/EPOXY FABRIC PREPREGS		5. Report Date May 2007	6. Performing Organization Code
7. Author(s) Stephen Ward, William McCarvill, and John Tomblin		8. Performing Organization Report No.	
9. Performing Organization Name and Address National Institute for Aviation Research Wichita State University 1845 North Fairmount Wichita, KS 67260-0093		10. Work Unit No. (TRAIS)	11. Contract or Grant No.
12. Sponsoring Agency Name and Address U.S. Department of Transportation Federal Aviation Administration Air Traffic Organization Operations Planning Office of Aviation Research and Development Washington, DC 20591		13. Type of Report and Period Covered Final Report	14. Sponsoring Agency Code AIR-100
15. Supplementary Notes The Federal Aviation Administration Airport and Aircraft Safety R&D Division Technical Monitor was Curtis Davies.			
16. Abstract <p>The building block approach is used within the composite aircraft industry for the substantiation of composite structure. A key element supporting the building block approach is material and process specifications. Material and process specifications are interwoven throughout the qualification and validation process. They are used to define the material's attributes, define the qualification characterization tests, purchase the material, and define and control the processes used for the fabrication. It is critical that the qualification specimens fabricated through the various levels of the building block approach use the same process, which is representative of the one that will be used in the fabrication of production aircraft and rotorcraft.</p> <p>This document recommends guidance and criteria for the development of material specifications for carbon fiber/epoxy prepreg fabric materials to be used on aircraft structures. This report is intended to be a companion to previous Federal Aviation Administration reports which established methodology for developing material allowable data, control of the data, and sharing the resulting database, DOT/FAA/AR-02/109 and DOT/FAA/AR-02/110. These reports provide recommendations for prepreg tape materials and processing. The guidelines and recommendations are meant to be a documentation of current knowledge and practices, and application of sound engineering principles to the development and implementation of composite material procurement specifications. A list of material control areas needing improvement and enhancement is provided for discussion. This document can also be used to develop common industry specifications.</p>			
17. Key Words Composite, Specification, Prepreg, Carbon fiber, Epoxy, Test methods, Testing, Qualification, Certification		18. Distribution Statement This document is available to the public through the National Technical Information Service (NTIS) Springfield, Virginia 22161.	
19. Security Classif. (of this report) Unclassified	20. Security Classif. (of this page) Unclassified	21. No. of Pages 85	22. Price

ACKNOWLEDGEMENTS

The following document was assembled with help from many individuals across many areas of expertise. The following Federal Aviation Administration personnel are acknowledged for their individual contributions to this document:

Curtis Davies
Larry Ilcewicz
Peter Shyprykevich
David Swartz

TABLE OF CONTENTS

	Page
EXECUTIVE SUMMARY	xi
1. INTRODUCTION	1
1.1 Objective	1
1.2 Background	2
1.3 Related Documents	2
1.4 Certification Process	3
1.5 Recommended Specification Format	4
2. DEVELOPMENT OF MATERIAL CONTROLS	5
2.1 Industry Material Specification	6
2.2 End-User Material Specification	7
2.3 End-User Responsibilities for Material Use in Structural Design	7
2.4 Supplier Material Specifications	8
2.5 Material Qualification Process When Using an Industry Material Specification	8
2.6 Material Qualification Process When Using an End-User Material Specification	10
3. THE SCOPE SECTION OF THE MATERIAL SPECIFICATION	11
4. THE APPLICABLE DOCUMENTS SECTION OF THE MATERIAL SPECIFICATION	11
5. THE TECHNICAL REQUIREMENTS SECTION OF THE MATERIAL SPECIFICATION	15
5.1 The Definitions Section	15
5.1.1 Batch Definitions	15
5.1.2 Batch Definitions Discussion	17
5.2 The Material Requirements Section	17
5.3 The General Prepreg Requirements Section	18
5.3.1 The Resin Requirements Section	18
5.3.2 Fabric Requirements	20
5.3.3 The Fiber Requirements Section	21

5.3.4	The Prepregging Process Requirements Section	22
5.4	The Uncured Prepreg Requirements Section	23
5.4.1	The Uncured Prepreg Properties Section	23
5.4.2	Roll Characteristics	24
5.4.3	The Visual Defect Limitations and Dimensions Section	24
5.4.4	The Storage, Handling, and Out-Time Section	25
5.5	The Cured Prepreg Property Requirements Section	26
5.5.1	Baseline Cure Cycle	26
5.5.2	Cured Laminate Physical Properties	27
5.5.3	Cured Laminate Mechanical Properties	28
5.5.4	Recommended Laminate Tests	29
5.5.5	Fabric Material Lay-Up Issues	36
5.6	The Material Characterization Section of the Material Specification	40
5.6.1	The Initial Material Qualification	40
5.6.2	Equivalency Baseline Enhancement	42
5.6.3	Additional Characterization Testing for Specific Design Applications	44
6.	THE QUALITY ASSURANCE SECTION OF THE MATERIAL SPECIFICATION	44
6.1	Changes to Qualified Materials	44
6.1.1	Level 0 Changes	45
6.1.2	Level 1 Changes	45
6.1.3	Level 2 Changes	46
6.1.4	Level 3 Changes	47
6.1.5	Level 4 Changes	48
6.2	Supplier Site Qualification	49
6.3	Statistical Process Control	49
6.4	Reduced Testing	49
6.5	Product Certification	50
6.5.1	Supplier Certification Testing	50
6.5.2	End-User (Purchaser) Testing	51
6.5.3	Storage Relifing	51
6.6	Material Test Methods	52
6.7	Test Panel Fabrication	52
6.8	Material Distributors	53
6.9	Records Retention	53

7.	THE PACKAGING AND SHIPPING SECTION OF THE MATERIAL SPECIFICATION	53
7.1	Material Identification	54
7.2	Interleaf or Release Layer	54
7.3	Packaging	54
7.4	Shipping	54
8.	THE ACKNOWLEDGEMENT SECTION OF THE MATERIAL SPECIFICATION	54
9.	THE REJECTION SECTION OF THE MATERIAL SPECIFICATION	55
10.	THE NOTES SECTION OF THE MATERIAL SPECIFICATION	55
11.	SUMMARY	55

APPENDIX A—DEFINITIONS OF TERMS

LIST OF FIGURES

Figure		Page
1	Recommended Definitions of Storage, Handling, Staging Life, and Out-Time	26
2	Plain Weave Fabric	37
3	Satin Weave Fabric	37
4	Example Satin Weave Showing Alternating Warp and Fill Faces Used for Lamination	38

LIST OF TABLES

Table		Page
1	Recommended Set of Neat Resin Properties	19
2	Recommended Set of Fabric Properties	21
3	Recommended Set of Carbon Fiber Properties	22
4	Recommended Set of Uncured Prepreg Properties—Prepreg Fabric Materials	24
5	Recommended Set of Cured Laminate Physical Properties—Prepreg Fabric Materials	28
6	Ply Lay-Up Sequences for Recommended Laminate Tests—Prepreg Fabric Materials	30
7	Recommended Minimum Set of Cured Laminate Mechanical Properties—Prepreg Fabric Materials	31
8	Recommended Additional Cured Laminate Mechanical Properties for General Applications—Prepreg Fabric Materials	32
9	Optional Cured Laminate Mechanical Properties for Expanded Database—Prepreg Fabric Materials	32
10	Optional Cured Sandwich Panel Mechanical Properties for Expanded Database—Prepreg Fabric Materials	34
11	Recommended Tests for Durability and Service Life Confirmation—Prepreg Fabric Materials	35
12	Batch Acceptance and Equivalency Baseline Enhancement Testing Protocol	43

LIST OF ACRONYMS AND SYMBOLS

α level	Alpha level. The risk or error associated with rejecting conforming material
T_g	Glass transition temperature
ACO	Aircraft Certification Office
AGATE	Advanced General Aviation Transport Experiment
AMS	Aerospace Material Specification
ASTM	American Society for Testing and Materials
CFR	Code of Federal Regulations
CLC	Combined loading compression
DMA	Dynamic mechanical analyses
DSC	Differential scanning calorimetry
EBE	Equivalency baseline enhancement
FAA	Federal Aviation Administration
IR	Infrared
HPLC	High-pressure liquid chromatography
KC	Key characteristics
KPP	Key process parameter
NASA	National Aeronautics and Space Administration
NDI	Nondestructive inspection
NIST	National Institute of Standards and Technology
PCD	Process control document
RTD	Room temperature dry
SACMA	Suppliers of Advanced Composite Materials Association
SPC	Statistical process control
TBD	To be determined

EXECUTIVE SUMMARY

A widely acknowledged validation process used within the composite aircraft industry for the substantiation of composite structure is called the building block approach. This approach is a process using analysis, and associated tests of increasing structural complexity. The building block approach is integrated with supporting technologies and design considerations. MIL-HDBK-17, Rev. F, Volume 3, Chapter 4 contains a complete description of the building block approach. A key element supporting the building block approach is material and process specifications.

The material and process specifications are interwoven throughout the certification validation process. Material specifications are used to define the material's attributes and define the qualification characterization tests. Materials used within the building block tests are purchased in accordance with the material specification. The material specification is used for the procurement of production material. This ensures the delivered materials are of the same quality and performance standards used in the certification and validation process. Process specifications define and control the processes used for the fabrication of materials into structural components. It is widely known that the performance properties of composite laminates are directly affected by the specific process used for their fabrication. It is critical that the test specimens fabricated through the various levels of the building block approach use the same process, which is representative of the one that will be used in the fabrication of production aircraft and rotorcraft.

This report establishes recommendations to guide the development of new and revised composite prepreg material specifications. This is intended to advance the work that has been done through previous Federal Aviation Administration, and National Aeronautics and Space Administration programs such as the Advanced General Aviation Transport Experiment. These programs have established methodology for developing material allowable data, control of the data, and sharing the resulting database. In the current work, a generalized approach to the development of a shared composite material database is proposed. It is intended to expand on the general aviation methods to allow a broader market to use the shared database.

This document recommends guidance and criteria for the development of material specifications for carbon fiber/epoxy prepreg fabric materials to be used on aircraft structures. A previously released report, DOT/FAA/AR-02/109, "Guidelines and Recommended Criteria for the Development of a Material Specification for Carbon Fiber/Epoxy Unidirectional Prepregs," provides similar recommendations for prepreg tape materials. These recommendations were prepared by a team of industry experts. The guidelines and recommendations are meant to be a documentation of current knowledge, and application of sound engineering principles to the development and implementation of composite material procurement specifications. A list of material control areas needing improvement and enhancement is given in appendix A. This document can also be used to develop common industry specifications. This document is limited to recommendations and guidance on the development of material specifications. Additional guidance on the development of process specifications, instructions, and controls for making high-quality laminates can be found in the companion report, DOT/FAA/AR-02/110, "Guidelines for the Development of Process Specifications, Instructions, and Controls for the Fabrication of Fiber-Reinforced Polymer Composites."

1. INTRODUCTION.

1.1 OBJECTIVE.

This document recommends guidance and criteria for the development of material specifications for carbon fiber/epoxy prepreg fabric materials to be used on aircraft structures. These recommendations were prepared by a team of industry experts who have extensive experience with material specifications, part processing, qualification programs, and design allowables. Starting with section 3 of this document, the sections parallel the typical sections found in a material specification. A list of areas needing improvement and enhancement is given in appendix A. This document is limited to recommendations and guidance on the development of a material specification. Additional guidance on the development of process specifications, instructions, and controls for making high-quality laminates can be found in the companion report, DOT/FAA/AR-02/110, "Guidelines for the Development of Process Specifications, Instructions, and Controls for the Fabrication of Fiber-Reinforced Polymer Composites."

The purpose of this report is to establish recommendations to guide the development of composite prepreg material specifications. This is intended to advance the work that has been done through previous Federal Aviation Administration (FAA) and National Aeronautics and Space Administration (NASA) programs, such as the Advanced General Aviation Transport Experiment (AGATE). These programs have established methodologies for developing material allowable data, control of the data, and sharing the resulting database. In the current work, a generalized approach to the development of a shared composite material database is proposed. It is intended to expand on the general aviation methods to allow a broader market to use the shared database.

The guidelines and recommendations contained in this document should not be viewed as FAA policy or as the only acceptable method for composite material specifications and qualification. They are meant to be a documentation of current knowledge and application of sound engineering principles to the development and implementation of composite material procurement specifications.

This document can also be used to develop an industry approach so that the following goals can be achieved:

- Greatly reduce the number of material and process specifications for identical composite material systems.
- Develop property databases that uniquely define a given material.
- Establish material batch testing and process monitoring sufficient to minimize variability and preclude property changes over time.
- Reduce costs through common documentation and shared databases of basic material properties.

1.2 BACKGROUND.

Steady growth in the use of composites has continued in transport aircraft and rotorcraft. General aviation has emerged recently with the growth of new composite aircraft and composite material applications in primary structures. Several new composite aircraft are undergoing the certification process. Many more aircraft are currently undergoing the design and development processes that take advantage of composite materials for primary structure applications. With this growth of composite applications, certification issues have emerged with respect to the philosophy of quality control and quality assurance methods needed to guarantee a safe and consistent material supply.

The material properties of a composite are manufactured into the structure as part of the fabrication process (process intensive material). Therefore, it is essential that material and process specifications used to produce composite materials contain sufficient information to ensure that critical parameters in the fabrication process are identified to facilitate production and adherence to standards in the final engineered part. Due to the wide variety of composite aircraft structures now emerging for certification, control of the materials is rapidly becoming a vital issue with respect to the overall assurance of safety.

In recent years, the aerospace industry, NASA, and the FAA have worked together to develop a cost-effective method of qualifying composite material systems by sharing material qualification databases, such as MIL-HDBK-17 and AGATE. By using shared databases, a manufacturer can select an approved composite material system to fabricate parts and validate adequate control with a smaller subset of testing for a specific application. For materials to be accepted into these shared databases, the raw materials are required to be manufactured in accordance with a material specification, which imposes control of key characteristics (KC) (physical, chemical, and mechanical properties), and be processed in accordance with a process specification that controls key processing parameters.

1.3 RELATED DOCUMENTS.

The following documents provided related information:

- DOT/FAA/AR-02/109, Guidelines and Recommended Criteria for the Development of a Material Specification for Carbon Fiber/Epoxy Unidirectional Prepregs, April 2003.
- DOT/FAA/AR-02/110, Development of Process Specifications, Instructions, and Controls for the Fabrication of Fiber-Reinforced Polymer Composites, April 2003.
- DOT/FAA/AR-03/19, Material Qualification and Equivalency for Polymer Matrix Composite Material Systems: Update Procedure, September 2003 (supercedes DOT/FAA/AR-00/47).
- DOT/FAA/AR-06/25, Preliminary Guidelines and Recommendations for the Development of Material and Process Specifications for Carbon Fiber-Reinforced Liquid Resin Molded Materials, March 2007.

- DOT/FAA/AR-07/3 Guidelines and Recommended Criteria for the Development of a Material Specification for Carbon Fiber/Epoxy Unidirectional Prepregs Update, March 2007.

1.4 CERTIFICATION PROCESS.

The objective of the composite aircraft structure certification process is to validate that the design meets the applicable configuration requirements. In this context, the design validation process (to establish by proof) is accomplished through verification (to prove by evidence) and qualification (to define attributes or characteristics) of the materials, processes, and analysis tools. Verification is simply to prove by evidence, usually by test data, that the proposed design is acceptable. Material qualification is the verifying of materials' attributes and characterizations, which are typically determined through testing.

A widely acknowledged validation process used within the composite aircraft industry for the substantiation of composite structure is called the building block approach. This approach uses analysis and associated tests of increasing structural complexity. The building block approach is integrated with supporting technologies and design considerations. Refer to MIL-HDBK-17, Rev. F, Volume 3, Chapter 4 for a complete description of the building block approach. Key elements supporting the building block approach are the material and process specifications.

The material and process specifications are interwoven throughout the certification and validation process. Material specifications are used to define the material's attributes, and to define the qualification characterization tests. Materials used within the building block tests are purchased in accordance with a material specification. The material specification is used for procurement of production material. This ensures the delivered materials are of the same quality and performance standards used in the certification validation process. Process specifications define and control the processes used for the conversion of materials into structural parts. It is widely accepted that the performance properties of composite laminates are directly determined by the specific process used for their fabrication. It is critical that the test specimens fabricated through the various levels of the building block approach use the same or equivalent processes, which are representative of the ones that will be used in the fabrication of production aircraft and rotorcraft.

Material qualification is a key element of the validation process, which occurs during the coupon level of the building block approach. It is during qualification that the composite material is fully defined and characterized. Qualification tests are planned and conducted to

- establish key material attributes,
- establish material performance properties, and
- verify that material characteristics will work in the intended application.
- create a statistical basis for requirements used in subsequent material quality assurance

The objective in defining material attributes is to establish the material property limits. Examples of attributes in which limits are set include:

- Resin content
- Fiber areal weight
- Cured per ply thickness
- Fiber volume

These attributes define the material and control its resulting performance properties. Other attributes that are often overlooked are related to the physical structure of the material, which affects processing characteristics. Example attributes of this type include:

- Fiber-sizing level and type
- Level of impregnation
- Resin impregnation method (hot-melt film or solution)
- Width tolerance
- Backing material selection

Performance properties are established, or made stable, through statistically significant amounts of tests. It is imperative that the material's natural variability is captured at this time. The objective is not to meet a desired level of performance, but rather, establish the true performance range of the material. Mechanical properties are typically thought of as the only performance properties.

There are other performance-related properties that have a direct bearing on the more familiar mechanical properties, which include tack or handling characteristics, kinetic behavior, rheological behavior, sensitivity to ambient moisture and temperature (out-time effects), effect of freezer storage, and resistance to fluids and solvents. Multiple material batches (typically three) are tested to establish the material variability. Results obtained from these tests are used to establish minimum and maximum values within the material specification.

1.5 RECOMMENDED SPECIFICATION FORMAT.

For consistency and standardization purposes, a general format for composite prepreg material specifications should be followed. The following is a recommended format that follows the standard format of Society of Automotive Engineers (SAE) Aerospace Material Specification (AMS) specifications; other formats with the same content are acceptable to the FAA.

1. Scope
2. Applicable Documents
3. Technical Requirements
 - 3.1 Definitions
 - 3.2 Material Requirements
 - 3.3 General Prepreg Requirements
 - 3.3.1 Resin Requirements
 - 3.3.2 Fiber Requirements
 - 3.3.3 Roll Characteristics
 - 3.3.4 Visual Defects

- 3.3.5 Storage, Handling, and Out-Time
- 3.4 Uncured Prepreg Requirements
- 3.5 Cured Prepreg Requirements
 - 3.5.1 Baseline Cure Process
 - 3.5.2 Cured Laminate Physical Properties
 - 3.5.3 Cured Laminate Mechanical Properties
- 3.6 Material Characterization
 - 3.6.1 Initial Material Qualification
 - 3.6.2 Equivalency Baseline Database Testing
 - 3.6.3 Additional Characterization Testing for Specific Design Applications
- 4. Quality Assurance
 - 4.1 Changes to Qualified Materials
 - 4.1.1 Level 0 Changes
 - 4.1.2 Level 1 Changes
 - 4.1.3 Level 2 Changes
 - 4.1.4 Level 3 Changes
 - 4.1.5 Level 4 Changes
 - 4.2 Supplier Site Qualification
 - 4.3 Statistical Process Control
 - 4.4 Product Certification
 - 4.4.1 Supplier Certification Testing
 - 4.4.2 Purchaser Testing
 - 4.5 Test Methods
 - 4.6 Test Panel Fabrication
- 5. Preparation for Delivery
 - 5.1 Material Identification
 - 5.2 Interleaf
 - 5.3 Packaging
 - 5.4 Shipping
- 6. Acknowledgement
- 7. Rejection
- 8. Notes

2. DEVELOPMENT OF MATERIAL CONTROLS.

Before the initiation of a qualification program, the sensitivities of the material to variations in the tolerances set on the material-chemical and physical-properties and processing should be investigated. This investigation should explore the characteristics of the material as the various limits are reached. These will determine the suitability of control limits in establishing the required reliability for the normal production phase of a qualified composite material.

This investigation can be performed in a structured design of experiments that will give the relative sensitivities to the process variables with minimum tests. These parametric studies should be performed well before the qualification batches are run to allow time for any required adjustment to settle out in the manufacturing process.

The rest of this section outlines the differences between qualification to an industry standard versus an end-user material specification, the responsibilities of an end-user related to establishing the suitability of a particular material and part fabrication process, and the steps required to establish a material specification and qualify the material. The following two sections discuss different types of material procurement specifications: (1) an industry standard specification established by an industry committee and (2) the traditional specification established by an individual end-user.

The authors of this document believe that the full benefits of shared material databases can only be achieved through the use of industry standard material specifications. However, it is recognized that there will continue to be cases where end-user material specifications are appropriate or required. This section discusses the qualification steps for both approaches. It is intended that the remaining sections of the document (starting at section 3) apply to both specification types.

2.1 INDUSTRY MATERIAL SPECIFICATION.

The recommendations in this document are particularly applicable to a material specification that will be released as an industry standard. The process envisioned for such a specification would involve the development of an initial material database by the material supplier. The material supplier is the manufacturer of the prepreg in this discussion. The material supplier controls the incoming raw materials and processes to produce a consistent product. A distributor does not produce the final product; it repackages large batches of prepreg into smaller units to be resold to end-users.

Material qualification is defined as the process of evaluating a material, using a prescribed series of tests, to establish its characteristics as produced by the baseline manufacturing process, and using the evaluation results to define material specification requirements. A material qualification is performed initially for a new material and is repeated, in part or in whole, when changes to materials or manufacturing processes need to be evaluated. The scope of a previous qualification may also need to be expanded when requirements for additional characteristics are either added to an existing application or result from using the material in a new application. For material characteristics that have never been qualified, a supplier or end-user material specification may contain target values in place of requirements. In this case, following qualification, the target values are updated to requirements based on the evaluation results.

The initial material database will result from testing conducted to an FAA-approved and FAA-witnessed test plan and will provide sufficient data to establish the material specification requirements and batch acceptance limits. In this scenario, the material supplier would establish proposed specification requirements and bring the material test results, along with the proposed specification requirements to an industry committee (such as SAE AMS Committee P, SAE Commercial Airplane Composite Repair Committee, MIL-HDBK-17, and American Society for Testing and Materials (ASTM) Committee D-30) for development of an industry specification. The committee would review the data and, after finding it satisfactory and needed, would approve development of a specification. This specification would uniquely define the material and will include specific property requirements and batch acceptance limits.

With this industry specification approach, the traditional process of qualifying a material to an existing material specification (containing either target requirements or requirements from a previously qualified material) is no longer applicable. The specification requirements will be determined based on the properties of the specific material. It is envisioned that specifications will be issued for any material that the minimum dataset, process control, and documentation requirements have been met. End-users desiring multiple material sources for an application can either call out the acceptable materials on the part drawings, on a substitution document, or on an internal specification once they have validated that all materials are acceptable for the design(s). However, the materials would be purchased and accepted to the requirements of the industry specification.

It will be the responsibility of the material supplier to continually test and evaluate the material to populate the database on an ongoing basis to ensure that the material has not changed. This is expected to be accomplished by the batch certification and equivalency baseline enhancement (EBE) tests outlined in section 5.

2.2 END-USER MATERIAL SPECIFICATION.

The traditional approach in the aerospace industry is for each end-user to prepare material and process specifications. After qualification of a material to these specifications, the end-user then purchases the prepreg and manufactures a part. This approach has involved the qualification of a material to an existing material specification (either in draft or released form).

In many cases, different materials have been qualified to the same set of specification requirements, even though the properties of the materials may be significantly different. This approach can result in less than desirable levels of control over the properties of the individual materials qualified to the specification. This may then translate into less than optimum control over structure made with these materials. Therefore, control limits should be specific to a particular material based on the database statistics.

Since it may be several years before the industry standard specifications are in place, this document includes recommendations for the preparation of end-user material specifications, and the qualification of materials to these specifications, to meet the goals stated in section 2.1.

2.3 END-USER RESPONSIBILITIES FOR MATERIAL USE IN STRUCTURAL DESIGN.

It is the responsibility of the end-user to qualify the material for use in a particular aircraft or rotorcraft application (see section 5.6.1 for additional information). This process may involve additional tests to characterize the material and validate specific design details. These tests will fully populate the certification database and then, on a reduced frequency basis, to ensure that the design allowables remain valid. The end-user is also responsible for validating that many materials are acceptable for the application, if this is so desired.

If the end-user decides to use the property information in previously developed databases in the certification project, the end-user will need to perform equivalency tests to demonstrate an understanding of the associated material and process specifications. This understanding

essentially involves demonstrating that the end-user can produce test panels and specimens that give results that are statistically equivalent to the values in the existing database.

To reduce the risk of failing the equivalency demonstration, it is recommended that the equivalency tests first be done using the material supplier's baseline cure process prior to attempting to demonstrate equivalency to an end-user's modification to the cure cycle. The end-user has the option of skipping the first step and directly demonstrating the equivalency of their cure cycle to the baseline database and cure cycle. However, the two-step process is suggested, since it is further recommended that the end-user perform the purchaser batch acceptance tests on panels cured using the material supplier's baseline cure process.

Further, it is the responsibility of the end-user to validate any deviations from the baseline laminate cure cycle given in the material and process specifications. The end-user's production process must not result in statistically significant changes to design allowables established by using the baseline process. Successful demonstration of equivalency to an existing shared database will allow the end-user to avoid additional material qualification tests and to use the material allowables derived from the shared database. Once an equivalency evaluation is performed by an end-user for one application, it does not have to be repeated by that end-user for follow-on applications that use the same cure process.

This document is limited to recommendations and guidance on the development of a material specification. Additional guidance on the development of process specifications, instructions, and controls for making high-quality laminates can be found in report DOT/FAA/AR-02/110.

2.4 SUPPLIER MATERIAL SPECIFICATIONS.

Supplier-generated material specifications are often used to make the initial prepreg qualification batches and panels and, once the equivalency and acceptance values have been derived from the allowables, data may subsequently be used in one of three ways:

- As a supplier specification for a commodity product, in much the same way as carbon fiber is supplied
- As a draft for an end-user specification, where the end-user is demonstrating equivalency to the original allowables database and wishes to have a document under his control rather than under the control of the supplier
- As a draft format for submission of data for inclusion in an industry specification at a later date

2.5 MATERIAL QUALIFICATION PROCESS WHEN USING AN INDUSTRY MATERIAL SPECIFICATION.

This section outlines the process of material qualification, end-user demonstration of equivalency for their part fabrication process, and the on-going batch acceptance tests. Details of the industry committee procedures, acceptance limit and allowables calculation procedures, and FAA involvement and procedures for this material qualification process will be defined at a later date.

In this process, it is anticipated that the material supplier will

- develop a new material for potential market requirements or qualify an old material to an industry specification.
- stabilize the prepreg production process through production trials.
- establish and document the cure process parameters for the material. This cure process will be used to generate the qualification database.
- perform the minimum qualification tests, as defined in the material specification. A minimum of three batches of prepreg material will be produced for the manufacture of test panels.
- upon completion of the tests, develop statistical material batch control limits and B-basis allowables values. Specification limits and allowables should be calculated using procedures documented in DOT/FAA/AR-03/19 and MIL-HDBK-17, Rev. F.
- submit the test data and specification limits to the industry committees responsible for the industry material procurement specification, material processing specification, and database approval.
- make the process control document (PCD) available for on-site review by the industry committee and customer personnel who have executed proprietary agreements with the supplier.
- submit the material and accompanying data, material specification, and allowables to a potential end-user.

The industry committees will

- review the data and specification values and, if acceptable, will issue appropriate notifications (documents, web announcements, etc.).
- develop additional material characterization requirements based on industry input. They will also obtain additional tests, calculate material equivalence limits and allowables, and review the data calculated values.

At this point, the end-user will

- perform equivalency tests to the material procurement specification, material processing specification, and property database. These tests verify that the end-user's processes for fabricating test panels and production parts can produce equivalent properties compared to the industry-approved database developed by the material supplier.

- compare the results of the equivalency tests to the published material database. If all test data meets the requirements, then the end-user can use the material allowables developed from the supplier's database in the design and certification of the end-user's structure.
- do one of the following if equivalency is not demonstrated: (1) modify their fabrication process and rerun the equivalency test program, or (2) perform additional tests to develop design allowables specific to their situation.
- perform additional design verification and certification tests to validate specific configurations and design details of their structure. Upon completion of all certification tests and analyses, the FAA will approve the design, which specifies the materials, for a Type Certificate.

2.6 MATERIAL QUALIFICATION PROCESS WHEN USING AN END-USER MATERIAL SPECIFICATION.

This section outlines the process of material qualification, end-user demonstration of equivalency for their part fabrication process, and the on-going batch acceptance tests. It assumes that the new material will qualify to a material specification written and maintained by an end-user. It also assumes that all qualification and design-related tests will be performed or controlled by the end-user. This material qualification process is consistent with the current FAA procedures for an aircraft certification program.

In this process, it is anticipated that the material supplier will

- develop a new material for potential market requirements.
- stabilize the prepreg production process through production trials.
- establish and document the cure process parameters for the material. This cure process will be recommended to potential end-users.
- submit the material and accompanying data, and supplier material specification (if applicable) to potential end-users.

At this point the end-user will

- submit a qualification and materials allowables test plan, and material specification to the FAA.
- perform the qualification or have the supplier do the testing and allowables tests, using the end-user's planned production cure process. A minimum of three batches of prepreg material should be used for the manufacture of test panels. Panel fabrication and testing will be witnessed as required.

- upon completion of the tests, calculate proposed material batch acceptance limits and B-basis allowables values. Specification limits and allowables should be calculated using procedures documented in DOT/FAA/AR-03/19 and MIL-HDBK-17, Rev. F.
- submit the test data, material specification, and cure process documentation to the FAA. The FAA will review the data and specification values and, if acceptable, will approve the use of the material specification and allowables data for the end-user's aircraft certification project.
- perform additional design verification and certification tests to validate specific configurations and design details of their structure. Upon completion of all certification tests and analyses, the FAA will approve the materials and design for a Type Certificate.

3. THE SCOPE SECTION OF THE MATERIAL SPECIFICATION.

This section should include a general description of the product and its area of application to guide the prospective user. General temperature use limits and cure conditions should be stated. If the product is to be supplied with various resin contents, cured ply thickness and product forms, i.e., different fabric weaves, then a system must be defined to distinguish the various types, classes, grades, etc. Those products to be controlled by this specification are required to be listed here.

It is recommended that for end-user material specifications:

- Form—defines the basic material form, e.g., woven or nonwoven fabric
- Style—defines the fabric weave style, fiber tow count, and areal weight of the fiber in the prepreg
- Type—defines the resin content of the prepreg
- Class—defines the specific fiber used in the prepreg (fiber type, size type and content, surface treatment level, manufacturer, facility)

For industry standard specifications, they would specify the form, resin content, areal weight, specific fabric and fiber information for each specific prepreg material covered.

4. THE APPLICABLE DOCUMENTS SECTION OF THE MATERIAL SPECIFICATION.

This section should include appropriate drawings, specifications, standards, and methods that will form a key part of the specification. The material supplier is encouraged to use existing documentation available to the public that was developed or approved by industry organizations. Test methods can come from ASTM and SACMA (available from the American Composites Manufacturers Association). Government-recommended processes and procedures should be referenced and followed, such as DOT/FAA/AR-03/19, Material Qualification and Equivalency for Polymer Matrix Composite Material Systems, and MIL-HDBK-17, Composite Material

Handbooks. Supplier internal documents, such as special test procedures, should be kept to a minimum. When used, they should be referenced and included in the PCD.

Examples include:

ASTM C 297-94(1999)	Standard Test Method for Flatwise Tensile Strength of Sandwich Constructions
ASTM C 364-99	Standard Test Method for Edgewise Compressive Strength of Sandwich Constructions
ASTM C 393-00	Standard Test Method for Flexural Properties of Sandwich Constructions
ASTM C 613/C 613M-97	Standard Test Method for Constituent Content of Composite Prepreg by Soxhlet Extraction
ASTM D 792	Specific Gravity (Relative Density) and Density of Plastics by Displacement
ASTM D 2344	Apparent Interlaminar Shear Strength of Parallel Fiber Composites by Short-Beam Method
ASTM D 2471-99	Standard Test Method for Gel Time and Peak Exothermic Temperature of Reacting Thermosetting Resins
ASTM D 2734	Void Content of Reinforced Plastics
ASTM D 3039	Tensile Properties of Polymeric Matrix Composite Materials
ASTM D 3171-99	Standard Test Method for Constituent Content of Composite Materials
ASTM D 3529/D 3529M-97	Standard Test Method for Matrix Solids Content and Matrix Content of Composite Prepreg
ASTM D 3530/D 3530M-97	Standard Test Method for Volatiles Content of Composite Material Prepreg
ASTM D 3531-99	Standard Test Method for Resin Flow of Carbon Fiber-Epoxy Prepreg
ASTM D 3532-99	Standard Test Method for Gel Time of Carbon Fiber-Epoxy Prepreg
ASTM D 3544-76 (1996)	Standard Guide for Reporting Test Methods and Results on High Modulus Fibers

ASTM D 3800-99	Standard Test Method for Density of High-Modulus Fibers
ASTM D 3878-01	Standard Terminology Composite Materials
ASTM D 4018-99	Standard Test Methods for Properties of Continuous Filament Carbon and Graphite Fiber Tows
ASTM D 4065-95	Standard Practice for Determining and Reporting Dynamic Mechanical Properties of Plastics
ASTM D 4102-82 (1999)	Standard Test Method for Thermal Oxidative Resistance of Carbon Fibers
ASTM D 3479-96	Standard Test Method for Tension-Tension Fatigue of Polymer Matrix Composite Materials
ASTM D 3518-94 (2001)	Standard Test Method for In-Plane Shear Response of Polymer Matrix Composite Materials by Tensile Test of a $\pm 45^\circ$ Laminate
ASTM D 5229-92 (1998)e1	Standard Test Method for Moisture Absorption Properties and Equilibrium Conditioning of Polymer Matrix Composite Materials
ASTM D 5279-99	Standard Test Method for Measuring the Dynamic Mechanical Properties of Plastics in Torsion
ASTM D 5379	Shear Properties of Composite Materials by V-Notched Beam Method
ASTM D 5418	Standard Test Method for Transition Temperatures of Polymers by Differential Scanning Calorimetry
ASTM D 5467-97	Standard Test Method for Compressive Properties of Unidirectional Polymer Matrix Composites Using a Sandwich Beam
ASTM D 5687-95	Standard Guide for Preparation of Flat Composite Panels with Processing Guidelines for Specimen Preparation
ASTM D 5766-95	Standard Test Method for Open-Hole Tensile Strength of Polymer Matrix Composite Laminates
ASTM D 5961-01	Standard Test Method for Bearing Response of Polymer Matrix Composite Laminates
ASTM D 6264-98	Standard Test Method for Measuring the Damage Resistance of a Fiber-Reinforced Polymer-Matrix Composite to a Concentrated Quasi-Static Indentation Force

ASTM D 6484-99e1	Standard Test Method for Open-Hole Compressive Strength of Polymer Matrix Composite Laminates
ASTM D 6641-01e1	Standard Test Method for Determining the Compressive Properties of Polymer Matrix Composite Laminates Using a Combined Loading Compression (CLC) Test Fixture
ASTM D 6742-01	Standard Practice for Filled-Hole Tension and Compression Testing of Polymer Matrix Composite Laminates
ASTM D 5528-01	Standard Test Method for Mode I Interlaminar Fracture Toughness of Unidirectional Fiber-Reinforced Polymer Matrix Composites
ASTM D 6115-97	Standard Test Method for Mode I Fatigue Delamination Growth Onset of Unidirectional Fiber-Reinforced Polymer-Matrix Composites
ASTM D 6415-99e1	Standard Test Method for Measuring the Curved Beam Strength of a Fiber-Reinforced Polymer-Matrix Composite
ASTM D 6671-01	Standard Test Method for Mixed Mode I-Mode II Interlaminar Fracture Toughness of Unidirectional Fiber-Reinforced Polymer-Matrix
ASTM D 6507-00	Standard Practice for Fiber-Reinforcement Orientation Codes for Composite Materials
ASTM E 168	General Techniques of Infrared Quantitative Analysis
ASTM E 1252-98	Practice for General Techniques for Obtaining Infrared Spectra for Qualitative Analysis
ASTM E 1309-00	Standard Guide for Identification of Fiber-Reinforced Polymer-Matrix Composite Materials in Databases
ASTM E 1356-98	Standard Test Method for Assignment of the Glass Transition Temperature by Differential Scanning Calorimetry of Differential Thermal Analysis
ASTM E 1434-00	Standard Guide for Recording Mechanical Test Data of Fiber-Reinforced Composite Materials in Databases
ASTM E 1471-92 (1998)	Standard Guide for Identification of Fibers, Fillers, and Core Materials in Computerized Material Property Databases
ASTM E 1640-99	Standard Test Method for Assignment of the Glass Transition Temperature by Dynamic Mechanical Analysis

ASTM E 2041-99	Method of Estimating Kinetic Parameters by Differential Scanning Calorimetry Using Borchardt and Daniels Method
ASTM E 2070-00	Test Method for Kinetic Parameters by Differential Scanning Calorimetry Using Isothermal Methods
ASTM E 4473-95	Standard Practice for Measuring the Cure Behavior of Thermosetting Resins Using Dynamic Mechanical Procedures
SACMA SRM 1R-94	Compressive Properties of Oriented Fiber-Resin Composites
SACMA SRM 18R-94	Glass Transition Temperature (T_g) Determination by DMA of Oriented Fiber-Resin Composites
SACMA SRM 20R-4R	High-Performance Liquid Chromatography of Thermoset resins
SACMA SRM 22R-94	Resin Flow of Preimpregnated “B” Staged Material
SACMA SRM 23R-94	Resin Content and Fiber Areal Weight of Thermoset Prepreg with Destructive Technique
SACMA SRM 25R-94	Onset Temperature and Peak Temperature for Composite System Resins Using Differential Scanning Calorimetry (DSC)

5. THE TECHNICAL REQUIREMENTS SECTION OF THE MATERIAL SPECIFICATION.

5.1 THE DEFINITIONS SECTION.

This section should include definitions for terms or abbreviations that are used. The definitions provide clarity between the supplier and the procurer. Material properties, quality, and defects must be defined such that batches made after the original qualification have the same level of quality and properties. For example, fabric prepreg defects such as fuzz balls, creases, foreign material, dry spots, fiber alignment, splices, and edge deviation from a straight line should have a specific definition (see appendix A.2 for recommended fabric defect definitions). The degree of advancement of the resin, storage life, out life, and handling life must be clearly defined since these attributes affect the reliability of the lay-up and cure processes. Where possible, definitions from industry standards such as MIL-HDBK-17, SAE, and ASTM should be used.

5.1.1 Batch Definitions.

The following batch definitions are recommended. The specification should define the specific fiber, fabric, resin, and prepreg batch definitions, along with the definition of a roll of prepreg.

Batch (or Lot) (general)—n, A quantity of material produced essentially at the same time and under the same conditions from a well-defined collection of raw materials. The quantity of material must have minimal variation in properties throughout to be considered a unique batch.

Batch (or Lot) (fibers) – n, For fibers, a quantity of material formed during one essentially continuous, uninterrupted production run under the same process conditions using one to three precursor lots. An interruption in the process of up to 72 hours (or more if allowed by the PCD) is permitted, provided that the production equipment settings are not modified or another material is not produced on the equipment during the interruption.

Batch (or Lot) (fabric) – n, For fabrics, a quantity of material woven from multiple (preferable three or less) batches (lots) of fiber in each direction. The weaving process can be interrupted for up to 72 hours (or more if allowed by the PCD) if the loom settings are not changed and another material is not produced in the interim.

Batch (or Lot) (resin) – n, For a batch of resin, the definition varies depending on the specific mixing process:

- In a batch mixing process, a large vessel is charged with the desired types and quantities of raw ingredients. After mixing is complete, the vessel is discharged. The material made from this single-mix process is defined as a single batch of resin.
- A continuous mixing process for producing resin typically involves incrementally feeding raw ingredients into a mixing device that blends them into a stream of resin. A batch of resin made by this process is defined as a quantity of material formed during one essentially continuous uninterrupted production run under the same process conditions using the same raw ingredients. Since start up and shutdown usually require purging the equipment, a shutdown will signal the end of a specific batch. Material made after start up is defined as a new batch. If a process shutdown does not require purging, an interruption in the process of up to 72 hours (or more if allowed by the PCD) is permitted, provided that the production equipment settings are not modified or another material was not produced on the equipment during the interruption.
- In one version of a semicontinuous mixing process, a large vessel is charged with a portion of the raw ingredients (premix). After mixing, the vessel is discharged into several smaller containers, each of which acts as the vessel for subsequent mixing steps. The remaining raw ingredients are added to these smaller vessels and further mixing results in the final resin composition. The premix produced in the large vessel can be considered as a single batch of raw ingredient. The material produced during the final mixing in the small containers can be considered one batch if it is produced from the same raw ingredients batches without an interruption of more than 72 hours (or more if allowed by the PCD) without the production of another material in the interval, and until the premix is consumed.
- In another version of a semicontinuous mixing process, small complete mixes of raw ingredients are made without the premix step. A batch of resin then consists of any number of these small mixes if they are made from the same lots of raw ingredients, the production run is not interrupted for more than 72 hours (or more if allowed by the PCD), and there is no other material made in the interval.

- For all mixing processes, blending of raw ingredient lots is permissible if the same blend ratio is found throughout all portions of the resin batch. Procedures that will cause blend ratio variation, such as resin batch blending, if allowed should be controlled by the prepreg material specification or PCD. Traceability must be retained on the ingredient lots that were used. For all mixing processes, a single-resin batch may contain a maximum of three blended lots of each raw chemical ingredient.
- For a resin filming operation, the film batch will correspond to the batch designation of the resin mix used to make the film. An interruption in the filming process of up to 72 hours (or more if allowed by the PCD) is permitted, provided that the production equipment settings are not modified or another film was not produced on the equipment during the interruption. Otherwise, the resin films produced on either side of the interruption shall be considered to be separate resin batches.
- Solvated resins typically can be handled and blended easily without the heat history associated with hot melt processes. In this case up to five resin lots may be blended, but only if the individual resin lots themselves do not consist of blends of resin lots. Traceability must be maintained as to lot designations and amounts blended.

Batch (or Lot) (specific, prepreg) – n, For prepregs, material is made from one batch of fabric and one batch of resin. The fabric should contain one to three batches (lots) of fiber, more batches are allowable if so defined in the PCD. Prepregging must not be interrupted for more than 72 hours (or more if allowed by the PCD) with no other prepregging on the same equipment during the time interval to retain a singular batch designation.

Batch (or Lot) (specific, lamina, and laminates) – n, For laminae and laminates, material is made from:

- One batch of prepreg, or
- One batch (lot) of fiber and one batch of resin(s) (non-prepreg materials), or
- One batch of fabric and one batch of resin(s) (non-prepreg materials)

5.1.2 Batch Definitions Discussion.

The above definitions are generally applicable for use with material acceptance processes, including sampling plans for acceptance testing. For material qualification and allowables test programs, stricter definitions of a batch are often specified to control the amount of material variability to be evaluated in the test program. For instance, a particular batch of prepreg may be restricted to a single batch of fabric (containing a single lot of fiber), and a single mix of resin.

5.2 THE MATERIAL REQUIREMENTS SECTION.

It is strongly recommended that the prepreg material supplier establish a PCD that documents key aspects of the material fabrication, lists all raw material ingredients, defines key process parameters (KPP), and establishes statistical process control (SPC) procedures and requirements. The PCD should be maintained by the material supplier. While the PCD will typically be a

proprietary document, it should be made available for review at the supplier's site by material end-users and certification agencies. It should be referenced by the material specification.

A specific fabric prepreg specification designation should include only a single-resin formulation, a single-fabric weave style and a single, specific fiber. A specific designation is defined to be a unique form, type, style, and class. The specification document can include multiple forms, types, styles, and classes (fiber types).

There are three levels of specification requirements needed for a fabric prepreg material that are often (but not required to be) documented in separate specifications: the fiber requirements, the fabric weaving requirements, and the prepreg requirements. The prepreg requirements include those for the resin system, the uncured prepreg, and the cured prepreg material when fabricated into laminates.

5.3 THE GENERAL PREPREG REQUIREMENTS SECTION.

This section should include requirements that define the specific raw ingredients and processes for producing the prepreg (many of these requirements may be specified in the PCD, which is referenced by the specification). In the following sections, it is assumed that the resin mixing, filming, and prepregging is conducted with or without solvent (solvated or hot-melt prepreg process).

5.3.1 The Resin Requirements Section.

This section should include requirements that define the specific chemical and physical properties of the resin.

5.3.1.1 Hot-Melt Resin Requirements.

The designation of the resin must be specified and must refer to only one combination of ingredients processed via one mixing regime. The resin composition and mixing process should be defined prior to qualification. Proposed limits of ingredient-weighing accuracy and process times and temperatures should be validated through physical and chemical testing. The mixing process includes premix step(s), final mix step(s), ingredient handling, mixed-resin cooling, mixed-resin storage, mixed-resin reheating, and feed process to the filming step. The limitations of in-process tests must be understood. Current industry practice is to use resin viscosity and gel time as quick methods to validate the resin mixing step. These quick tests typically allow a wide range of acceptable values, and may not be an accurate measure of resin consistency. If blending of mixed resin batches is to be allowed, the nature and type of blending should be validated through chemical analysis. Blending of mixed hot-melt resins is discouraged unless it can be demonstrated that there is no impact on prepreg out-time and cure kinetics. Process limits defined and validated by the physical and chemical testing must be documented in the PCD or specification. These limits should be defined and validated by tests performed in all extremes of the processing envelope, design of experiments may be used.

Resin components and their manufacturers must be specified in the PCD or specifications. The prepreg material supplier should establish material specifications for all raw materials to be used

in the prepreg resin. If multiple sources of an ingredient are planned, the use of each component should be validated through chemical analysis. Raw ingredients can be blended as long as storage and handling requirements for the raw materials are met. Tests must establish that departures from the raw material manufacturer's recommendations for handling and storage are valid.

Resin requirements that measure key attributes of the final mix or premix(es) shall be identified. In some cases, this information may be considered proprietary and controlled in the PCD. These may include gel time, viscosity, degree of advancement, and analytical signature such as Infrared (IR) spectrophotometry, or high-performance liquid chromatography (HPLC). In addition, the resin cure kinetics and rheology should be well characterized. It is valuable to conduct the kinetic and rheological studies on resins made to the limits of ingredient ratios allowed by the mix procedure and weighing errors. At one extreme, the curative would be at its lowest concentration and the epoxy resin at their highest concentration. At the other extreme, the curative would be at its highest concentration and the epoxies at their lowest. Variations of usual techniques may be needed to characterize solvated resins.

The diffusion and absorption of moisture and environmental fluids in the cured resin should be evaluated via moisture uptake versus time and degree of plasticization, which leads to lowering of elastic modulus and glass transition temperature (T_g). The resistance of the cured resin to thermal microcracking over the range of use temperatures and cycles, both as cured neat resin and cured composite, should be assessed.

All the above-mentioned data should be documented by the material supplier, be made available to potential users of the material, and be made available to the industry committee responsible for the industry specification for the material, if applicable. Table 1 summarizes the resin property data discussed above. None of the tests in table 1 are recommended for batch acceptance testing.

Table 1. Recommended Set of Neat Resin Properties

Resin Property	Test Method
Density	ASTM D 792
Viscosity	Any agreed method
Gel time	ASTM D 2471
IR	ASTM E 1252
HPLC (ingredient ratios)	SRM 20R
Cure kinetics	ASTM E 2041 ASTM E 2070
Rheology	ASTM E 4473

5.3.1.2 Solvated Resin Requirements.

The same philosophy expressed for hot-melt resins should also be applied to resins prepared as a solution in solvent. In some cases, solvent is used as a fugitive process aid in preparing resins

that ultimately will be filmed and then pressed into the fibers with heat and pressure. The hot-melt section applies to resin prepared in this manner. This section refers explicitly to resins that use solvents to aid in the mix steps and in which the solvents are not removed from the resin mix. The resin solution is used to impregnate the fabric and then is driven off in a vertical or horizontal tower with heat and airflow. Typically, resins prepared from solvent-based processes experience much less thermal history. The ingredients are simply mixed together in the solvent at a relatively low temperature compared to hot-melt processes and the low-solution viscosity allows for impregnation at low temperatures and pressures. The solvated process can also be less expensive since the filming step and the backing papers are eliminated. Solvents have a profound effect on resin-processing characteristics. Residual solvent greatly increases resin flow during the cure cycle, increases tack, and contributes to volatile content. It is important to target solvent levels that provide consistent tack level, flow, and porosity in the part.

The same level of control of ingredients and processes described for hot-melt resins should be applied to solvent-based resins. Additional raw materials include the solvent and a backing film instead of a backing paper. The backing film is usually made from polyethylene, which is substantially lower cost than typical backing papers.

The presence of solvent makes the measurement of neat resin key attributes difficult. Small amounts of solvent greatly affect resin viscosity and rheology. Conversely, the time and temperature required to remove solvent to the desired level may introduce undesired resin advancement. When conducting the tests shown in table 1, care must be taken to deal with solvents in a consistent, reproducible manner. If it is not possible to isolate neat resin, then screening on prepreg made from a subscale process is typically acceptable.

5.3.1.3 Non-Hot-Melt/Nonsolvated Resin Requirements.

The resin control requirements for hot-melt resins are also applicable for a process consisting of room temperature, or low-temperature, impregnation followed by staging to create dry prepreg.

5.3.2 Fabric Requirements.

Fabric destined for either the hot-melt or solvated prepreg processes should be purchased to a fabric specification that defines the manufacturer and facility. The fabric specification should establish the fiber type, tow filament count, sizing type and level, fabric areal weight, and the fabric style. Carbon fiber fabric can include a contrasting glass or aramid fiber tow (tracer) to help in discerning tow alignment. These tracer fibers can be treated to enhance detection by nondestructive inspection (NDI) methods. It should be demonstrated that these tracer fibers do not affect the short- and long-term performance of the cured composite.

Carbon fiber fabrics that contain conductive fibers (aluminum, copper, phosphor bronze, nickel, nickel-coated carbon) for lightning protection, electromagnetic interference shielding, or other purposes must be treated in the applicable fabric, and prepreg specifications as a separate fabric style from the basic fabric without the conductive fibers. A full set of fabric and prepreg qualification test data should be obtained on the fabric with the conductive fibers.

Table 2 shows the recommended set of fabric properties.

Table 2. Recommended Set of Fabric Properties

Fabric Property	Test Condition	Test Method
Width	TBD	ASTM D 3774
Tracer spacing*	TBD	Any agreed method
Alignment*	TBD	Any agreed method
Waviness	TBD	Any agreed method
Openness	TBD	Any agreed method
Yarn count/inch*	TBD	Any agreed method
Areal weight g/m ² * (without sizing)	N/A	ASTM D 3776
Selvage edge	TBD	Any agreed method
Thickness (optional)	TBD	Any agreed method
Length (optional)	TBD	Any agreed method
Sizing content	TBD	Any agreed method

*Batch acceptance and equivalency baseline tests (see section 6.5)

N/A = Not applicable

TBD = To be determined

5.3.3 The Fiber Requirements Section.

This section should include requirements that define the mechanical and physical properties of the fiber. The carbon fiber to be used in the prepreg should be purchased to a separate fiber specification that uniquely defines the fiber type, manufacturer, and facility.

The carbon fiber must be capable of meeting the requirements of the prepreg specification when woven per the fabric specification and impregnated with the specified resin and processed per the specified cure procedure. If they are separate documents, both the fabric and prepreg specifications must define the specific fiber to be used. If multiple fiber sources are to be included in the prepreg specification, then each fiber source must correspond to a unique prepreg designation (e.g., class) and, in the case of an industry specification, must correspond to a unique designation. It should be noted that two or more facilities owned by the same company producing identical fiber can be considered a single item when it has been established by testing that the two materials are equivalent. It is not acceptable for a prepreg specification to refer to the carbon fiber and the fabric by a trade name without specifying the manufacturer and the facility that produces the fiber, the fiber specification that controls the fiber, the fabric specification that controls the fabric weaving, and the manufacturer, and the facility that produces the fabric.

The fiber specification should define the average values and ranges for all critical fiber mechanical and physical properties including tensile strength, tensile modulus, and density. The fabric and prepreg specifications should identify the fiber form, tow count (e.g., 12K flat tow), and twist or no twist. The fiber-sampling plan and test methods for fiber properties and quality should be documented.

The fiber size material, method of size application, and size content should be considered an integral part of the carbon fiber. The fiber sizing is to be unique and there should be a shelf life requirement if the sizing ages during storage. Changes to the size, application, or content will require equivalency testing or the establishment of a new material designation (see section 2).

Similarly, electrolytic treatment of the fiber surface should be considered an integral part of the carbon fiber, and changes to the surface treatment will require equivalency testing or the establishment of a new material designation.

The recommended definition of fiber batch is given in section 5.1. Fiber batch blending of up to three lots is allowed as long as there is traceability of each fiber batch and the lots are randomly distributed across the fabric and prepreg. For prepreg materials used to establish the initial material database, each prepreg batch should contain a single and unique fiber batch.

Table 3 summarizes the fiber property data discussed above. These tests should be performed by the fiber supplier on each lot of fiber supplied to the prepreg manufacturer. None of the tests in table 3 are recommended for prepreg batch-acceptance testing by the prepreg supplier or material end-user.

Table 3. Recommended Set of Carbon Fiber Properties

Fiber Property	Test Condition	Test Method
Form	N/A	ASTM E 1309
Twist	TBD	Any agreed method
Size content	N/A	ASTM D 4018
Tensile modulus	RTD	ASTM D 4018
Tensile strength	RTD	ASTM D 4018
Elongation	RTD	ASTM D 4018
Density	RTD	ASTM D 3800
Yield (mass/unit length)	TBD	Any agreed method

N/A = Not applicable
 RTD = Room temperature dry
 TBD = To be determined

5.3.4 The Prepregging Process Requirements Section.

The KPPs for filming and prepregging should be established and documented. In some cases, this information may be considered proprietary and controlled in the PCD. Process conditions should have maximum and minimum limits that are monitored, recorded, and reviewed per the SPC procedures.

5.3.4.1 Hot-Melt Prepregging Process Requirements.

The recommended definitions of resin and prepreg batches are given in section 5.1. The resin filming process limits should not only control the chemical advancement of the resin but also

film quality aspects (e.g., fish eyes, mottling, film thickness (or weight) down the length, and film thickness (or weight) across the width). Limits should be defined for film thickness (or weight), including a target thickness (or weight) value and range.

The backing paper and plastic film should be controlled like any other critical raw material.

The prepreg process limits should result in control of the resin advancement, as well as degree of resin impregnation, puckers, etc. The production of prepreg with consistent handling characteristics, such as tack, drape, thickness, resin content, and fiber areal weight are critical for subsequent part manufacture.

The capability of the prepreg to be cured within the time and temperature limits specified by the manufacturer should be demonstrated on flat panel laminates. Resin should be subjected to times and temperatures that mimic the minimum and maximum thermal histories that the prepreg is subjected to during its manufacture. These resins should then be subjected to the cure extremes claimed by the manufacturer in terms of heat-up rates, hold steps, and highest and lowest cure temperature. The rheological response of the resin, when subjected to these extremes, should be understood. The degree of cure achieved by the resin, and the mechanical properties of the resin, both dry and after fluid and water exposure, can be evaluated via differential scanning calorimetry (DSC) and dynamic mechanical analysis (DMA) tests. The tests to evaluate the extremes of the processing window will not require a complete database, but sufficient data to demonstrate that the material properties, and allowables developed using the nominal cure process are valid (equivalent) for the entire range of process parameters.

5.3.4.2 Solvated Melt Prepregging Process Requirements.

The fundamental concerns are very similar to those for hot-melt prepregging. The processes must be defined to make a reproducible, consistent product not only in mechanical properties, but also in attributes related to part manufacture. Areas differing from hot-melt processing include fabric let-off tension, resin concentration, applicator speed and gap, tower temperature, tower airflow rate, and backing film tension. If the resin bath continuously recirculates the resin solution, the resin concentration should be maintained at the desired level.

The backing film should be controlled like any other critical raw material.

5.3.4.3 Nonsolvent and Non-Hot-Melt Prepregging Process Requirements.

The same process control requirements for hot-melt prepregging are also applicable for a process consisting of room-temperature or low-temperature impregnation, followed by staging to create dry prepreg. The time and temperature of staging will have to be controlled.

5.4 THE UNCURED PREPREG REQUIREMENTS SECTION.

5.4.1 The Uncured Prepreg Properties Section.

This section should include requirements for uncured prepreg physical and chemical properties for either solvated or hot-melt-based prepreg. Table 4 outlines the minimum recommended set of uncured prepreg properties needed for characterization of the material. The requirements and

test methods for each property shall be documented in the specification. Chemical reactivity via DSC can be accomplished by evaluating the onset of exotherm. The total heat liberated cannot be measured accurately due to variability of resin content on the small-scale sample. The degree of advancement can be detected by measurement of the subambient T_g of the uncured resin.

Table 4. Recommended Set of Uncured Prepreg Properties—Prepreg Fabric Materials

Uncured Prepreg Property	Test Condition	Test Method
Fiber content, areal weight ¹	N/A	ASTM D 3776 and SACMA SRM 23
Resin content, % by weight ¹	N/A	ASTM D 3529 and SACMA SRM 23
Insoluble content	N/A	ASTM D 3529
Volatile content, % by weight ¹	N/A	ASTM D 3530
Flow, % by weight ¹	N/A	ASTM D 3531 and SACMA SRM 22
Gel time, minutes	N/A	ASTM D 3532
HPLC (ingredient ratios) ¹	N/A	SACMA SRM 20
IR (ingredients chemical signature)	RTD	ASTM E 1252
Chemical reactivity and degree of advancement via DSC	N/A	ASTM E 1356, ASTM D 3418, and SACMA SRM 25
Tack	RTD	Any agreed method
Drape	RTD	Any agreed method

¹ Batch acceptance and equivalency database enhancement tests (see section 6.5)

N/A = Not applicable

RTD = Room temperature dry

Tests should be conducted on the start and end of rolls, and should also be conducted across the full width (at least on the edges and center) of the rolls during production trials and qualification. This is intended to capture down-the-length and across-the-width variability introduced in the filming and prepregging process steps.

5.4.2 Roll Characteristics.

The roll size, weight, core type, width, length and tolerances, splice allowances, and defect/splice tracer requirements should be defined. They can be specified in the material specification or on a separate purchasing document. A separate purchasing document is expected to be used by an end-user when purchasing material to an industry standard specification.

5.4.3 The Visual Defect Limitations and Dimensions Section.

This section should include limitations on visual defects in the prepreg. Criteria for continuous defects, such as yarn alignment, width, tracer alignment, and edge alignment, should be established and documented. In some cases, this information may be considered proprietary and controlled in the PCD. Allowable defect limits can be based on generally accepted industry standards.

Procedures for closing fabric openness, e.g., through the use of rollers, can be used if documented in the PCD. Edge alignment can be corrected by tenting if procedures are established to control and document material out-time.

Criteria for discontinuous defects, e.g., impurities, dry areas, incomplete impregnation, cured resin, hard spots, localized color differences, puckers, fuzz balls, curled or folded selvages overlapping nonselvedge areas, wrinkles, slubs, crimps, splices, foreign material, yarn twists and crossovers, broken yarns, fiber distortion, crushed yarns, and bowed fibers, should be defined in the PCD or specification (see section 11 for recommended definitions of fabric defects). Where surface defects, such as foreign material and fuzz balls, can be removed by scraping or picking, these procedures can be used if defined in the PCD or specification.

Procedures for continuous inspection of the prepreg shall be defined in the specification or PCD. It is recognized that, since release paper or poly film is typically found on one side of the prepreg, only the top surface can be inspected. Should the same defects be detected by the end-user on the bottom of the prepreg when the part is being laid up, the same criteria for allowable defect limits and correction should be followed.

The specification should require each prepreg defect outside the allowable limits to be identified and marked by a flag positioned at the edge of the material. The type, location, and length of each defect should be recorded for each roll and attached to the roll. Defects can be removed by splicing per documented procedures and by criteria for maximum number and minimum spacing of splices. The splicing technique must be easily identified by the end-user to avoid incorporation of the splice into a part. The time out of cold storage during defect removal should be recorded and used to adjust the remaining out-time.

5.4.4 The Storage, Handling, and Out-Time Section.

This section should include definitions and limitations for storage life under specified conditions, handling life under ambient conditions, and out-time capability of laid-up material. These requirements should be based on specific test data and experience with similar materials. The material supplier can establish and document the storage life as a function of storage temperature. A portion of the material batches produced for the initial material database development should be placed in an appropriate storage facility. After the desired maximum shelf life is reached, the material should be tested and the results compared to the specification requirements. These tests could be performed in conjunction with the equivalency baseline database tests discussed in section 5.6.2. Recommended definitions for storage, handling, staging life, and out-time are shown in figure 1.

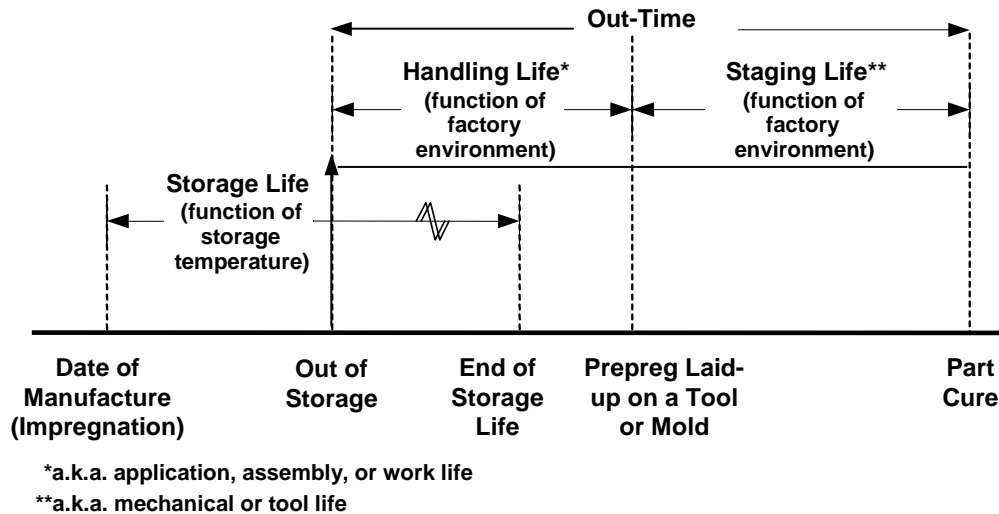


Figure 1. Recommended Definitions of Storage, Handling, Staging Life, and Out-Time

It is recommended that a tracking policy be implemented by the material supplier to document storage/out-time of material from date of manufacture (defined as the date of impregnation) to arrival on dock at the end-user. Tracking should include resin intermediates, mixed resin, and film.

Any testing to re-establish the acceptance of materials that have been subjected to storage upsets, such as a freezer breakdown, must demonstrate that key cure-related attributes are within the normal range.

A distributor should practice the same documentation of storage life and conditions as the material supplier and end-user. If original packaging is to be opened to allow for respooling into smaller units, the prepreg should be allowed to warm in the unopened package until moisture does not condense on the prepreg. All out-time accumulated during warming, respooling, and repackaging should be subtracted from the total life specified by the material supplier, and documented for the end-user.

5.5 THE CURED PREPREG PROPERTY REQUIREMENTS SECTION

This section should include requirements for the cured prepreg in a laminate form. These requirements should be based on specific data obtained for the material.

5.5.1 Baseline Cure Cycle.

It is recommended that the material supplier establish a baseline cure cycle to be used to produce laminates for the initial material database (for qualification and material allowables), and for batch acceptance testing. The baseline cure cycle should be selected based on the expected end-user applications, and requirements for the material (see DOT/FAA/AR-02/110 for recommendations on selecting the cure cycle). Reasonable tolerances on heat-up rates, time-at-temperature, and cool-down rates should be established and documented. The cure process will be capable of producing cured laminates of consistent, high quality that are representative of the

quality and variability expected for production parts. For example, with oven or vacuum bag processing, this means that defined maximum levels of porosity are acceptable in the qualification laminates.

The baseline cure cycle should be used for all batch acceptance tests by the material supplier and end-user. It is possible that part-manufacturing processes will use a different cure cycle than the baseline cure cycle. The end-user must demonstrate that the part cure cycle produces equivalent properties to the material database in order to use the allowables generated from the material characterization database for certification of the part (see DOT/FAA/AR-03/19). If the end-user uses a different cure cycle than the material supplier for batch acceptance tests, there is the potential that the supplier will produce acceptable test results while the end-user produces results that fail. In this case, the different results will confound resolution of acceptance due to the different cure cycles.

If the end-user defines a significantly different alternate cure cycle, additional batch acceptance testing with that cure cycle may be appropriate, particularly if different allowables are used for parts with the alternate cure cycle.

5.5.2 Cured Laminate Physical Properties.

It is recommended that the material specification include, as a minimum, requirements for the cured laminate physical properties listed in table 5. The limits and test methods for each property will be documented in the specification.

It is recommended that these tests be conducted on prepreg from the start and end of rolls as well as from the sides and center. This can be done on a periodic sampling basis.

Table 5. Recommended Set of Cured Laminate Physical Properties—Prepreg Fabric Materials

Cured Laminate Physical Property	Test Condition	Test Method
Cured ply thickness ¹	TBD	Any agreed method
Fiber volume, % by volume ²	TBD	Any agreed method
Resin content, % by weight ²	TBD	Any agreed method
Void content, % by volume ²	N/A	ASTM D 2734
Laminate density	RTD	ASTM D 792
Glass transition temperature, T_g ²	Precondition environments: <ul style="list-style-type: none"> • Dry • Wet (saturation under 85% relative humidity environment) 	SACMA SRM 18 ASTM D 4065 ASTM E 1356 ASTM E 1545 ASTM E 1640
Equilibrium moisture content	Equilibrium under 85% relative humidity environment	ASTM D 5229
Moisture absorption	Absorption vs time under room temperature, 85% relative humidity environment	ASTM D 5229
Thermal induced microcracking	Cycles over expected range of usage temperatures; fast heat-up spikes, etc.	Any agreed method

¹ Batch acceptance and equivalency database enhancement tests (see section 5.6.2 and 6.5)

² Equivalency database enhancement tests (see section 5.6.2)

RTD = Room temperature dry

TBD = To be determined

5.5.3 Cured Laminate Mechanical Properties.

A minimum set of mechanical property data are recommended to adequately characterize the material and to provide a database for future material equivalency evaluations. The tests should be able to detect changes in the fiber, resin, prepregging process, and the response of the prepreg to variations in the cure process. A subset of these tests are recommended for acceptance testing for each batch.

In addition to the batch acceptance tests, it is recommended that a second set of tests be run on an ongoing basis to further populate the database, especially for use as a baseline in future equivalency evaluations (see section 5.6.2). The results from these tests would be used to monitor the material acceptance and equivalency requirements in the specification. They would also assist in detecting material changes or an increase in variability. It is expected that the increase in cost associated with these tests will be greatly offset by the reduction in future costs associated with failed equivalency evaluations.

The following paragraphs present a series of recommended tests for development of a material property database. It is expected that this database will be developed over time, as the market for the material expands, and specific applications require additional data. The first set of tests represents the minimum tests recommended to establish a material specification. This test matrix is very similar to the AGATE test matrix in DOT/FAA/AR-03/19, and is intended for applications that have simple lay-up configurations and do not involve mechanically fastened joints or highly loaded structure. An additional set of open-hole laminate tests is recommended for inclusion in the specifications for materials intended for more general applications.

Further sets of recommended tests for an expanded database are then presented. These tests are optional with regard to inclusion in the material specification, but may be required for the design and certification of an end-user's product. There is a potential for cost savings if these additional tests could be shared amongst several end-users. Therefore, for marketing purposes, the material supplier may elect to perform tests to expand the shared database, either by themselves or in conjunction with one or more end-users. The expanded database could include the tests recommended below, other design specific tests and/or other environmental related tests (e.g., flammability, moisture diffusion, thermal cycling). In each step of the database development, its utility is limited until more data is collected, but the intent is to let market conditions drive the expansion of the database.

It should be understood that while material specification acceptance values are not the same as B-basis design allowables, they are typically derived from the same test data. The calculation methods are different and they are intended for different objectives.

Material specification acceptance values are specifically intended for control of material. The values are calculated using statistical procedures that are a function of a risk level for rejection of a good batch of material and acceptance of a bad batch of material. The acceptance values are a function of the database mean and standard deviation, and the batch sample size. Therefore, as data is added to the database, acceptance values will only change if there is a change in the data mean or variation.

Basis values (allowables) are intended to provide a certain level of statistical confidence for design strength calculations. B-basis values are established such that 90% of the population data falls above the basis value with 95% confidence. Basis values are a function of database mean and standard deviation and the number of data points in the database.

5.5.4 Recommended Laminate Tests.

Table 6 lists the specific fabric ply lay-ups for the tests recommended in tables 6 through 11. To establish a material specification, the tests in table 7 are recommended as a minimum set for material characterization and qualification of a prepreg fabric material. The additional open-hole tests in table 8 are recommended for materials expected to be used in more general applications that will contain mechanical fastened joints, or will be designed with notched laminate properties. The requirements and the test methods for each property will be documented in the specification. All tests should be robust in that material variability, rather than test variability, will be evaluated. Recommended test methods for each property are given in MIL-HDBK-17, Rev. F, Volume 1, Chapters 3 through 7. Moisture conditioning should be conducted per the

procedures given in MIL-HDBK-17 and ASTM D 5229. The ASTM D6641 (CLC) test method is recommended for compression testing due to its superior performance (reduced variability), and lack of requirement for tabs on the test specimens. It is expected that all industry material specifications to be developed in the near future will require the use of the CLC test method.

Table 6. Ply Lay-Up Sequences for Recommended Laminate Tests—Prepreg Fabric Materials

In the following lay-up sequences, the fabric ply orientations are defined as follows:		
0	warp fibers in 0° direction, warp face down	
0*	warp fibers in 0° direction, warp face up	
90	warp fibers in 90° direction, warp face down	
90*	warp fibers in 90° direction, warp face up	
45	warp fibers in 45° direction, warp face down	
45*	warp fibers in 45° direction, warp face up	
-45	warp fibers in -45° direction, warp face down	
-45*	warp fibers in -45° direction, warp face up	
// - indicates mid-plane of the lay-up		
Lay-Up Name	Ply Lay-Up Sequence (starting from toolside)	Recommended Thickness Range for Selecting 'n' (inches)
1. Warp Tension	[0/0*]n	0.090 to 0.120
2. Warp Compression	[0/0*]n	0.100 to 0.140
3. Fill Tension	[90/90*]n	0.090 to 0.120
4. Fill Compression	[90/90*]n	0.100 to 0.140
5. In-Plane Shear	D3518: [45/-45/45/-45 // -45*/45*/-45*/45*]	N/A
	D5379: [(0/90/0/90)n // (90*/0*/90*/0*)n]	0.120 to 0.160
6. Warp Interlaminar	[0/0*]n	0.200 to 0.250
7. Quasi Laminate	[(45/0/-45/0)n//((0*/-45*/0*/45*)n)]	0.100 to 0.150
8. Soft Laminate	[(45/-45/0/45/-45)n//((-45*/45*/0*/-45*/45*))]	0.100 to 0.150
9. Hard Laminate	[(0/0/45/0/0)n//((0*/0*/45*/0*/0*))]	0.100 to 0.150
10. Warp Sandwich	[0*/0*/core /0/0] (warp face next to core)	N/A
11. Fill Sandwich	[90*/90*/core /90/90] (warp face next to core)	N/A
12. Quasi Sandwich	[45*/0*/core /0/45] (warp face next to core)	N/A
13. Warp Toughness	[0/0*]n	0.120 to 0.200
14. Quasi CAI	[(45/0/-45/0)n//((0*/-45*/0*/45*)n)]	0.140 to 0.200

Table 7. Recommended Minimum Set of Cured Laminate Mechanical Properties—Prepreg Fabric Materials

Lay-Up (see table 6)	Test Type and Direction	Property	No. of Batches x No. of Panels x No. of Tests/Batch/Panels			
			Test Temperature/Moisture Condition			
			Lowest Temperature/ Ambient	70°F/ Ambient	Highest Temperature/ Ambient	Highest Temperature/ Wet
1. Warp Tension	0 (Warp)Tension ASTM D 3039	Ultimate Strength and Modulus	3 x 2 x 3	3 x 2 x 3 ²	3 x 2 x 3	3 x 2 x 3
2. Warp Compression	0 (Warp) Compression ASTM D 6641	Ultimate Strength and Modulus	3 x 2 x 3	3 x 2 x 3 ²	3 x 2 x 3	3 x 2 x 3
3. Fill Tension	90 (Fill) Tension ASTM D 3039	Ultimate Strength and Modulus	3 x 2 x 3	3 x 2 x 3 ¹	3 x 2 x 3 ²	3 x 2 x 3 ²
4. Fill Compression	90 (Fill) Compression ASTM D 6641	Ultimate Strength and Modulus	3 x 2 x 3	3 x 2 x 3 ²	3 x 2 x 3 ¹	3 x 2 x 3 ²
5. In-plane Shear	In-plane Shear ASTM D 3518 ([±45 lay-up) or ASTM D 5379 ([0/90] lay-up)	Ultimate Strength and Modulus	3 x 2 x 3	3 x 2 x 3 ²	3 x 2 x 3	3 x 2 x 3
6. Warp Interlaminar	Short Beam Shear ASTM D 2344	Ultimate Strength	—	3 x 2 x 3 ¹	—	—

¹ Batch acceptance and EBE tests (see section 5.6.2 and 6.5)

² EBE tests (see section 5.6.2)

Table 8. Recommended Additional Cured Laminate Mechanical Properties for General Applications—Prepreg Fabric Materials

Lay-Up (see table 6)	Test Type and Direction	Property	No. of Batches x No. of Panels x No. of Tests/Batch/Panels			
			Test Temperature/Moisture Condition			
			Lowest Temperature/ Ambient	70°F/ Ambient	Highest Temperature/ Ambient	Highest Temperature/ Wet
7. Quasi Laminate	0 (Warp) Open-Hole Tension ² ASTM D 5766	Ultimate Strength	3 x 2 x 3	3 x 2 x 3 ¹	3 x 2 x 3	3 x 2 x 3 ¹
7. Quasi Laminate	0 (Warp) Open-Hole Compression ² ASTM D 6484	Ultimate Strength	—	3 x 2 x 3 ¹	3 x 2 x 3	3 x 2 x 3 ¹

¹ EBE tests (see section 5.6.2)

² Open-hole test configuration: 0.25-inch diameter hole, 1.5-inch-wide specimen

Table 9. Optional Cured Laminate Mechanical Properties for Expanded Database—Prepreg Fabric Materials

Lay-Up (see table 6)	Test Type and Direction	Property	Test Temperature/Moisture Condition			
			Lowest Temperature/ Ambient	70°F/ Ambient	Highest Temperature/ Ambient	Highest Temperature/ Wet
7. Quasi Laminate	0 (Warp) Unnotched Tension ASTM D 3039	Ultimate Strength/ Modules	✓	✓		✓
8. Soft Laminate	0 (Warp) Unnotched Tension ASTM D 3039	Ultimate Strength/ Modules	✓	✓		✓
9. Hard Laminate	0 (Warp) Unnotched Tension ASTM D 3039	Ultimate Strength/ Modules	✓	✓		✓
7. Quasi Laminate	0 (Warp) Unnotched Compression	Ultimate Strength/ Modules		✓	✓	✓
8. Soft Laminate	0 (Warp) Unnotched Compression	Ultimate Strength/ Modules		✓		✓
9. Hard Laminate	0 (Warp) Unnotched Compression	Ultimate Strength/ Modules		✓		✓

Table 9. Optional Cured Laminate Mechanical Properties for Expanded Database—Prepreg Fabric Materials (Continued)

Lay-Up (see table 6)	Test Type and Direction	Property	Test Temperature/Moisture Condition			
			Lowest Temperature/ Ambient	70°F/ Ambient	Highest Temperature/ Ambient	Highest Temperature/ Wet
9. Hard Laminate	0 (Warp) Open-Hole Tension ¹ ASTM D 5766	Ultimate Strength	✓	✓		✓
8. Soft Laminate	0 (Warp) Open-Hole Tension ¹ ASTM D 5766	Ultimate Strength	✓	✓		✓
9. Hard Laminate	0 (Warp) Open-Hole Compression ¹ ASTM D 6484	Ultimate Strength		✓		✓
8. Soft Laminate	0 (Warp) Open-Hole Compression ¹ ASTM D 6484	Ultimate Strength		✓		✓
7. Quasi Laminate	0 (Warp) Filled-Hole Tension ² ASTM D 6742	Ultimate Strength	✓	✓		
9. Hard Laminate	0 (Warp) Filled-Hole Tension ² ASTM D 6742	Ultimate Strength	✓	✓		
8. Soft Laminate	0 (Warp) Filled-Hole Tension ² ASTM D 6742	Ultimate Strength	✓	✓		
7. Quasi Laminate	0 (Warp) Filled-Hole Compression ² ASTM D 6742	Ultimate Strength		✓		✓
9. Hard Laminate	0 (Warp) Filled-Hole Compression ² ASTM D 6742	Ultimate Strength		✓		✓
8. Soft Laminate	0 (Warp) Filled-Hole Compression ² ASTM D 6742	Ultimate Strength		✓		✓
7. Quasi Laminate	0 (Warp) Single Shear Bearing ³ ASTM D 5961	Ultimate Strength/ Yield		✓		✓

Table 9. Optional Cured Laminate Mechanical Properties for Expanded Database—Prepreg Fabric Materials (Continued)

Lay-Up (see table 6)	Test Type and Direction	Property	Test Temperature/Moisture Condition			
			Lowest Temperature/ Ambient	70°F/ Ambient	Highest Temperature/ Ambient	Highest Temperature/ Wet
9. Hard Laminate	0 (Warp) Single Shear Bearing ³ ASTM D 5961	Ultimate Strength/ Yield		✓		✓
8. Soft Laminate	0 (Warp) Single Shear Bearing ³ ASTM D 5961	Ultimate Strength/ Yield		✓		✓
[0]n	Compression Interlaminar Shear	Ultimate Strength	✓	✓		✓

¹ Open-hole test configuration: 0.25-inch diameter hole, 1.5-inch-wide specimen

² Filled-hole test configuration: 0.25-inch diameter hole, 100° tension head countersunk fastener, 1.5-inch-wide specimen

³ Single-shear bearing configuration: 0.25-inch diameter hole, 1.5-inch width, one protruding head fastener, and stabilization fixture

Table 10. Optional Cured Sandwich Panel Mechanical Properties for Expanded Database—Prepreg Fabric Materials

Lay-Up ¹ (see table 6)	Test Type and Direction	Property	Test Temperature/Moisture Condition			
			Lowest Temperature/ Ambient	70°F/ Ambient	Highest Temperature/ Ambient	Highest Temperature/ Wet
10. Warp Sandwich	Sandwich Long Beam Flexure	Ultimate Strength		✓		✓
11. Fill Sandwich	Sandwich Long Beam Flexure	Ultimate Strength		✓		✓
12. Quasi Sandwich	0 (Warp) Sandwich Long Beam Flexure	Ultimate Strength		✓		✓
12. Quasi Sandwich	0 (Warp) Sandwich Long Beam Flexure, with Open Hole	Ultimate Strength		✓		✓
12. Quasi Sandwich	0 (Warp) Sandwich Long Beam Flexure, with 30-in-lb impact	Ultimate Strength		✓		
12. Quasi Sandwich	0 (Warp) Sandwich Long Beam Flexure, with 120-in-lb impact	Ultimate Strength		✓		

¹ If the material is designed to be self-adhesive to the core, then these tests should be conducted on cocured panels fabricated without adhesive. If the material requires an adhesive layer for bonding to the core, then the tests can be conducted on either (or both) cocured panels or precured skins secondarily bonded to the core, depending on the anticipated design and fabrication methods to be used with the material.

Table 11. Recommended Tests for Durability and Service Life Confirmation—Prepreg Fabric Materials

Lay-Up (see table 6)	Test Type and Direction	Property	Test Temperature/Exposure Condition			
			Lowest Temperature/ Ambient	70°F/ Ambient	Highest Temperature/ Ambient	Highest Temperature/ Wet
In-plane Shear Exposure to Solvent A (repeat for each potential exposure fluid)	In-Plane Shear ASTM D 3518 ([±45 lay-up] or ASTM D 5379 ([0/90] lay-up)	Ultimate Strength and Modulus		✓		✓
13. Warp Toughness	Mode I Fracture Toughness ASTM D 5528	G1c	✓	✓		✓
13. Warp Toughness	Mode II Fracture Toughness	G2c	✓	✓		✓
7. Quasi Laminate	0 (Warp) Open- Hole Fatigue ¹ , R=-1 (Tension/ Compression)	Fatigue Life ²		✓		✓
8. Soft Laminate	0 (Warp) Open- Hole Fatigue ¹ , R=-1 (Tension/ Compression)	Fatigue Life ²		✓		✓
9. Hard Laminate	0 (Warp) Open- Hole Fatigue ¹ , R=-1 (Tension/ Compression)	Fatigue Life ²		✓		✓
14. Quasi CAI	0 (Warp) Compression After Impact, 270-in-lb impact SACMA SRM-2	Ultimate Strength		✓		
14. Quasi CAI	0 (Warp) Compression After Impact, 540-in-lb impact SACMA SRM-2	Ultimate Strength		✓		
14. Quasi CAI	0 (Warp) Compression After Impact, 1080-in-lb impact SACMA SRM-2	Ultimate Strength		✓		

¹ Open-hole test configuration: 0.25-inch diameter hole, 1.5-inch-wide specimen.

² Runout for fatigue life tests should be at least 1×10^6 cycles, unless the material is intended for use in severe fatigue environments, in which case the number of cycles for runout should be increased.

Batch acceptance tests are recommended in table 7 (as noted). These batch acceptance tests are recommended based on the following rationale.

- The room temperature tension test is included to monitor the fiber and fiber-resin interface properties.
- The hot-compression test is included to primarily monitor the resin properties.
- The apparent shear strength by short beam test is included to monitor the fiber-resin interface properties.

5.5.5 Fabric Material Lay-Up Issues.

Woven fabric weaves are characterized by the manner in which the warp, and fill (sometimes known as weft) yarns are interlaced to form the fabric. Typically, the warp direction runs parallel to the selvage of the fabric (along the length of the fabric as it comes off the roll). The weaving style of the yarns has some influence on the properties of the woven fabric. In composite reinforcement applications, weave styles are almost always variations of plain or satin weaves and are described in detail in sections 5.5.3.2.1 and 5.5.3.2.2.

Some controversy exists over the exact methodology that should be applied when qualifying a woven fabric material form. Since most weave patterns have approximately equal yarn counts in both the warp and fill directions, some qualifications have used a $[0/90]_{ns}$ lay-up to produce qualification panels. This type of procedure, although it may reduce the amount of testing required, may produce a nonconservative design allowable if manufacturing procedures are not in place to verify cross-ply lay-up during manufacturing at all times. In a $[0]_n$ lay-up sequence for woven fabric material, the mechanical properties in the fill direction are generally lower than the warp direction due to prepreg manufacturing. For these reasons, the warp and fill directions should be treated as independent directions in the qualification process similar to a unidirectional tape. If the warp and fill direction are not accurately tracked in the composite manufacturing process, the average of both the warp and fill should be used for the design allowable. If procedures are in place to track the warp and fill directions, the designer may use both warp and fill properties for the design allowables. If the differences are insignificant between warp and fill directions, the strength and modulus values can be pooled (combined) Thus the calculated basis value, can be used for strength and the average value can be used for modulus.

5.5.5.1 Plain Weaves.

In a plain weave fabric pattern, warp and fill yarns are interlaced over and under each other in an alternating pattern, as shown in figure 2. Plain weave fabrics are ideally suited for flat laminates, where a high degree of drapeability is not required.

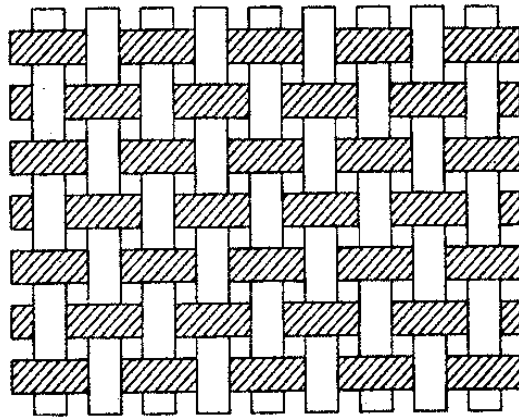


Figure 2. Plain Weave Fabric

5.5.5.2 Satin Weaves.

A satin weave construction consists of yarns that do not interlace at every yarn intersection. Instead, the yarns in both directions will cross over several intersections and interlace under one, as shown in figure 3. Satin weave fabrics have a higher degree of drapeability than plain weaves and are well suited for manufacturing parts with complex surfaces. Common satin weaves used in composite applications are four-harness satin, five-harness satin, and eight-harness satin.

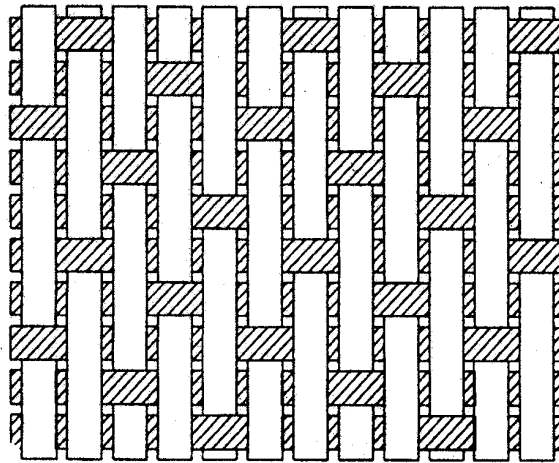


Figure 3. Satin Weave Fabric (Five-Harness Satin Shown)

Extreme care should be used when manufacturing the qualification panels using satin weave woven fabrics. Due to the unsymmetrical nature of the weave pattern, warpage may result during cure if strict lay-up practices are not followed. In the lay-up of a $[0]_n$ or $[\text{warp}]_n$ laminate, each corresponding ply should be rotated 180° about the warp axis to produce a lay-up of alternating the warp face and fill face, as shown in figure 4.

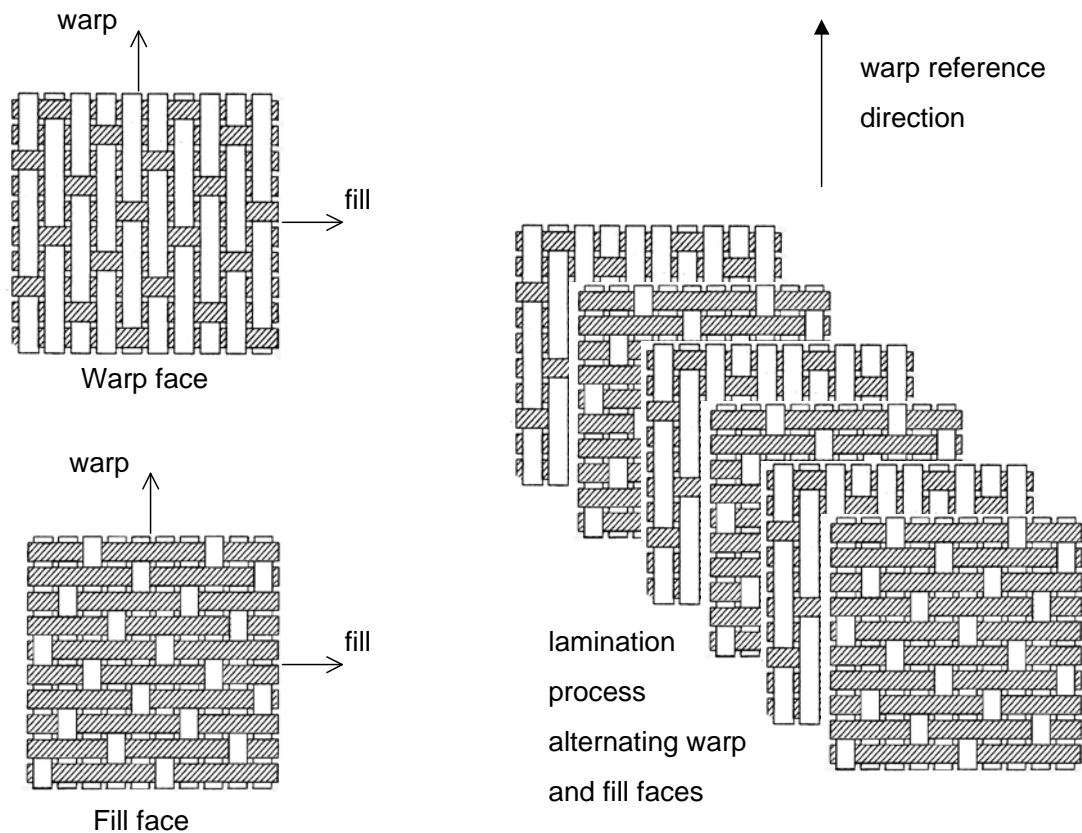


Figure 4. Example Satin Weave Showing Alternating Warp and Fill Faces Used for Lamination

5.5.5.3 Fabric Lay-Up.

For fabrics where each warp or fill yarn crosses over more than one of the other direction yarn (e.g., an eight-harness fabric), one surface of the fabric will have more warp fibers (warp surface), and the other surface will have more fill fibers (fill surface). For these fabric materials, the orientation of the fabric relative to which surface is up in the laminate stack can be important to avoid panel warping. For the tests using solid laminates containing only one of 0° , 90° , or 45° oriented plies in tables 6 to 11, it is recommended to lay-up the laminate with all of the fill faces down (if the warp and fill faces are alternated, a condition called warp face nesting can occur, which can lead to panel warping). For the tests using solid laminates containing both 0° and 45° oriented plies in tables 6 to 11, it is recommended to lay-up the lower half of the laminate with the warp face down, and the upper half of the laminate with the warp face up.

Process documents and controls for lay-up of test panels and parts should ensure accurate alignment of both the warp and fill fiber directions (it is not sufficient to only align the warp fibers of the fabric). Fiber orientation tolerances (typically $\pm 1^\circ$ for test panels and $\pm 3^\circ$ to $\pm 5^\circ$ for parts) and fiber straightness requirements (such as $\pm 2^\circ$ over a distance of 12 inches for parts) should be specified. Exceptions are often required in highly contoured areas of parts.

Table 9 shows optional tests for an expanded material database. These tests are intended to provide data for additional material design allowables that are commonly used to design and certify aircraft structures. The recommended test conditions for each test are shown with a check mark. The number of batches to be tested will depend on the acceptable level of conservatism for the allowable values, on the criticality of the structure for which the data will be used, and on acceptance by the responsible FAA ACO.

Many aircraft applications involve more than solid laminate construction. The tests listed in table 9 are recommended for honeycomb sandwich panels. The tests are selected as sensitive indicators of any change in the constituent materials. These tests require that separate specifications exist for the honeycomb and the adhesive used to bond the prepreg to the core.

Table 11 lists optional tests that may be required to show that the material will be suitable for the intended aircraft or rotorcraft application. These include testing of cured laminates after exposure of the laminates to solvents that the part will be subjected to in actual service. Recommended fluids for testing are:

Extended Contact:

- 100 Low-Lead Aviation Fuel
- JP-4 Jet Fuel
- MIL-H-5606 Hydraulic Oil
- MIL-H-83282 Hydraulic Oil
- Engine Lubricating Oil MIL-L-7808
- Engine Lubricating Oil MIL-L-23699

Short-Duration Contact:

- Methyl Ethyl Ketone Washing Fluid (ASTM D 740)
- Polypropylene Glycol Deicer (Type I) MIL-A-8243
- Isopropyl Alcohol Deicing Agent (TT-I-735)

It is recommended that the test laminates be exposed to the above fluids at room temperature conditions, unless the material is expected to be used in an application where fluid exposure occurs for significant time periods at a different temperature. For example, materials intended for use in integral fuel tanks should be exposed to fuel over the expected range of service temperatures for the fuel tank (typically cold to hot conditions). Tests for extended contact fluids should be conditioned by immersion for 500 ± 50 hours. Tests for short-duration contact fluids should be conditioned by immersion for 48 ± 4 hours.

The test method to evaluate solvent affect should be sensitive to the expected effect on the laminate. Shear tests are best for detecting the effect of solvent exposure on epoxy resins. The solvent exposure and subsequent tests should be conducted at the temperatures expected during service.

It is recommended that fatigue testing of open-hole specimens be conducted to confirm that the parts will be durable over the expected service life. Postimpact residual strength evaluation for damage tolerance is recommended for primary structure applications. Fatigue testing of impact-damaged specimens may also be required for certification of certain primary structures; however, the detailed recommendations for these tests are beyond the scope of this document. See FAA Advisory Circular 21-107A for further guidance on these issues.

It is also recommended that any other unique environmental conditions be considered, such as ultraviolet exposure, and other weathering effects that may degrade material properties. These environmental conditions should be applied for the expected service conditions and life for the material and structural application.

The recommended test conditions for each test are shown with a check mark in table 11. The number of batches to be tested will depend on the acceptable level of conservatism for the allowable values, on the criticality of the structure for which the data will be used, and on acceptance by the FAA.

All tests shown in tables 9 through 11 may not be applicable depending on the physical limitations of the material. For instance, impact energy levels may have to be adjusted for different laminate thicknesses and material characteristics.

5.6 THE MATERIAL CHARACTERIZATION SECTION OF THE MATERIAL SPECIFICATION.

5.6.1 The Initial Material Qualification.

This section should include procedures and requirements for initially characterizing the material to establish the specification requirements.

5.6.1.1 The Industry Material Specification.

To develop the information needed to qualify a material to an industry specification, tests will be conducted to establish an initial database. The tests can be performed by a material supplier, an end-user, or an industry consortium (a supplier and multiple users, e.g., AGATE). The test results are used to establish the initial material specification and batch acceptance limits. The decision of whether the specification becomes an industry standard or an end-user proprietary specification is for the developers of the database to determine.

A request for the initial qualification will be reviewed by the FAA. The organization that will conduct the tests will submit a test plan, the industry material specification, and process specification prior to the actual qualification. Appropriate reviews and inspections should be agreed upon to ensure FAA acceptance of the qualification.

5.6.1.2 The End-User Material Specification.

For qualification to an end-user specification, the material supplier and end-user typically will negotiate as to which party will fund and conduct the qualification tests. The end-user will be

responsible for submitting a test plan, material specification, and process specification to the FAA prior to the actual qualification. The qualification test results are used to establish the initial material specification and batch acceptance limits.

5.6.1.3 Minimum Level of Tests.

It is recommended that the initial material database include the minimum set of recommended properties listed in sections 5.5.2 and 5.5.3. At the discretion of the organization(s) developing the database, the test program may include the additional recommended tests listed in section 5.5.3, and any additional tests desired by the prospective end-users of the material. It is strongly recommended that fatigue be among the tested properties.

It is strongly recommended that a minimum of three different material batches consisting of a minimum of two different fiber batches and three different resin batches be used for the initial database (see batch definitions, section 5).

Per the AGATE approach, it is also recommended that laminates for mechanical property data for each batch be processed using two independent cure cycles. The data from the two processing cycles can be considered separate batches when calculating design allowables from the data.

5.6.1.4 Specification Requirements.

The statistical procedures given in DOT/FAA/AR-03/19 and MIL-HDBK-17 can be used to calculate the material property equivalency requirements and material batch acceptance limits. When using these procedures, the equivalency requirements should be calculated using an α (alpha) = 0.05, while the batch acceptance limits should be calculated using an α = 0.01. The α level is related to the risk associated with the rejection of conforming material. It is set higher for equivalency to ensure higher probability of rejecting material that is not equivalent. The equivalency requirements for all tested properties, and the acceptance limits for specified properties will be listed in the specification. These requirements and acceptance limits are recommended to be established as:

- Maximum average, minimum average, and minimum individual values for all strength properties
- Maximum and minimum average values for all stiffness properties
- Maximum and minimum average values for cured ply thickness, resin content, fabric areal weight, T_g , etc.
- Maximum average values for volatile content, void content, etc.

The nominal cured ply thickness specified in the material specification for the material should be used for all modulus and strength calculations.

5.6.2 Equivalency Baseline Enhancement.

Since the initial material qualification tests are performed on only three batches of prepreg (containing only three batches of resin and two batches of fiber), and since the qualification batch material is often produced using processes that are not completely representative of full-scale prepreg production, it is strongly recommended that the material specification contain requirements to test additional mechanical and other properties of interest on each batch with the test frequency for these tests reduced once the properties are verified to be stable.

The reasons for recommending these additional testing are:

- The additional data will provide a more robust database (closer estimate of the population means and variabilities) for calculating the material batch acceptance and material equivalency requirements. This is expected to result in fewer material batch rejections and fewer failures of material equivalency programs.
- The data provides an ongoing validation of mechanical properties, thereby minimizing the chance of surprise changes.
- A larger database will result, thereby providing the potential for higher allowables.

It is recognized that updating statistical basis values may require significant engineering expense to revisit strength calculations. It should be understood that basis values are not a constant value for samples drawn from a population, but that they have a distribution of values. For instance, two samples drawn from the same population will produce two different basis values. Both values are valid because they represent an estimate of a lower bound to the population distribution. For this reason, it is not practical to continually recalculate basis values as new data points are obtained.

The following test protocol is recommended:

1. After qualification, the EBE tests listed in section 5.5 should be performed for each prepreg production batch. After the 12th batch of production material is tested, the material equivalency and batch acceptance requirements should be recalculated, and the specification revised with the updated values. This gives a total of 15 batches of data that, assuming the material properties are in statistical control, will produce a fairly stable and representative set of specification requirements.
2. If there are no significant changes in the specification requirements from the calculations in step 1, and an SPC analysis of all of the batch data shows that the material is in control, then the EBE testing frequency can be reduced to once every 30 batches or once a year, whichever is more frequent. Normally, the material supplier should not have to obtain formal end-user or FAA approval for the reduction in EBE testing frequency; the batch data will be reviewed as part of the specification update described in step 1. A frequency of every 30th batch or once a year is recommended as a reasonable compromise between minimized cost and the desire to obtain periodic data to detect material drift or changes.

3. Upon accumulation of each additional ten sets of test results (either from the EBE tests or from intervening material equivalency tests), the material equivalency and batch acceptance requirements should be recalculated, and the specification revised with the updated values. For those properties tested for each batch of material, the data from all batches is included in the recalculation. Periodic recalculation is recommended since it does not make sense to update the specification values after every new dataset (collected on every 30th batch or once a year).
4. Basis values should only be recalculated if there is a significant change in the specification values; i.e., there is a statistically significant change in the population mean or variability.

This protocol is outlined in table 12.

Table 12. Batch Acceptance and Equivalency Baseline Enhancement Test Protocol

Batch No.	Qualification	Batch Acceptance	Equivalency Baseline Enhancement
1 - 3	All tests in tables 1 to 7 (plus tests in tables 8 to 11 as appropriate for material and application)	Part of qualification	Part of qualification
4 - 15		Tracer spacing Fiber alignment Yarn count/inch Fabric areal weight Uncured fiber content Uncured resin content Uncured volatile content Flow HPLC	Cured fiber volume Cured resin content Cured void content Warp tension RTA Warp compression RTA Fill tension HTA, HTW Fill compression HTA, HTW OHT RTA, HTW OHC RTA, HTW
16 - 44		Cured ply thickness	none
45		Fill tension RTA	Same as for batches 4-15
46 - 74		Fill compression HTA Shear RTA	none
75			Same as for batches 4-15
continuing			Repeat above pattern every 30 batches

RTA = Room temperature ambient
HTW = High temperature wet
OHT = Open-hole tension

HTA = High temperature ambient
OHC = Open-hole compression

5.6.3 Additional Characterization Tests for Specific Design Applications.

Depending on the intended application for the material, additional tests at the laminate, element, and subcomponent levels may be required to fully characterize the material. These tests would include evaluations of process and configuration variations, such as for cocured sandwich structures. For more discussion of scale-up issues of composite processing see DOT/FAA/AR-02/110. These tests could also include evaluations of solvent resistance, impact damage resistance and residual strength, fracture toughness, and bolted and bonded joint strength.

These tests can be performed at the discretion of the supplier if a common database of properties is desired; otherwise the tests can be left to the individual end-users of the material.

6. THE QUALITY ASSURANCE SECTION OF THE MATERIAL SPECIFICATION.

This section should define the batch-sampling plan and establish which tests will be the responsibility of the material supplier, and which will be conducted by the end-user (purchaser). Key characteristics such as resin content and carbon fiber areal weight are recommended for SPC control. These KCs should be monitored on a continuing basis to build a database, and to allow for detection of variations and anomalies.

Material acceptance is the process of determining, by test and inspection, whether a specific batch of material meets the requirements of the applicable procurement specification. (Material acceptance is also called quality conformance in specifications that conform to U.S. Department of Defense MIL-STD-490/961 practices.) Normally, a subset of the material qualification tests are selected and designated as acceptance tests (or quality conformance tests). These tests should be representative of key material/process characteristics, such that significant changes in the test result indicate a potential change in the material.

The material specification defines sampling requirements and limits for these acceptance tests. Statistical methods are used to determine the material specification requirements using the qualification data and subsequent production batch data. The sampling requirements for acceptance tests normally vary with the maturity and confidence in the process—larger and more frequent samples are selected when the process has a greater likelihood of changing, and conversely, smaller and less frequent samples are selected when increased process maturity and property stability has been demonstrated. This determination must always be tempered by the criticality of the part, and the acceptable risk level for the operation. Modern production practices emphasize statistical quality control tools using acceptance test data as well as process control tests to monitor production trends and make real-time or near-real-time process corrections.

6.1 CHANGES TO QUALIFIED MATERIALS.

This section should include the procedures and requirements for establishing the equivalency of future material data to the baseline database.

Material equivalency is the process of determining whether two materials or processes are similar enough in their characteristics and properties that they can be used without distinction

and without additional evaluation. Statistical tests are used to determine whether data from the same material processed in two different manners are significantly different. Equivalency is limited to the evaluation of changes in a material's constituents, manufacturing process, or to changes in the fabrication process (e.g., curing) used with a material. Two materials that meet the same minimum material specification requirements but have statistically different property distributions are not considered equivalent.

Final report DOT/FAA/AR-03/19 provides procedures for evaluating material equivalency. The procedures for material equivalency described in that document are only applicable to specific types of changes and subject to limitations. For details of the changes and conditions, see the report.

The following sections are intended to expand upon the material equivalency guidelines given in DOT/FAA/AR-03/19 by encompassing a greater range of material changes. MIL-HDBK-17, Rev. F, Volume 1, section 8.4.1, "Tests for Determining Equivalency Between an Existing Database and a New Dataset for the Same Material," gives statistical procedures that can be used to determine whether there is a statistical difference between the data from the two materials or fabrication processes. For two materials to be truly equivalent, their population means and distributions for every property of interest must be essentially identical. However, in practice, this will almost never be achieved, so engineering judgement will be required when equivalency determinations are necessary.

Since processes and materials undergo continual evolution and change, it is necessary to establish that the prepreg remain true and consistent to the original database and allowables. It is the responsibility of the material supplier to conduct tests to demonstrate that the current material, when processed to the baseline process specification, will generate composite properties statistically equivalent to the properties of the original materials.

Any material changes that result (or can be expected to result) in a change to the material allowables, or to the acceptance limits, will be considered to be a major change under Title 14 Code of Federal Regulations (CFR) Part 21.93. The approval of minor and major changes are covered in 14 CFR 21.95 and 21.97, respectively. The following sections describe five levels of material changes and the testing and notification requirements associated with these levels.

6.1.1 Level 0 Changes.

These are changes that do not affect the material. Some examples of these changes are typographical error corrections to the specification or PCD, changes to the names of incoming materials due to company name changes, and use of alternate storage facility locations using identical storage conditions. No notification to the end-users is necessary for these changes. Related document updates are not required.

6.1.2 Level 1 Changes.

These are minor changes that have been tested internally at the supplier beyond normal batch acceptance testing on the same or similar material and have been found not to affect the material.

Typical examples of level 1 changes are:

- Change in release (backing) paper or other process aid
- Alternate vendor for chemically and physically identical raw materials (there should be compelling data verifying that the alternate material is identical to the original material)
- Changes to packaging methods and materials

Physical aspects of constituent resin chemicals, such as particulate size and shape, can have a significant effect on the properties of the mixed resin even if the constituents are chemically identical.

Current end-users will be notified of these changes. Due to potential producibility issues, end-users should approve changes to backing and release papers prior to incorporation. A new revision of the applicable material specification is recommended.

6.1.3 Level 2 Changes.

Due to the type of change involved, this level is considered major by the FAA. These changes can be approved with less than the full equivalency test plan required for a level 3 change. These changes will require that the material supplier conduct tests to an extent that establishes the requirements listed in the material, and process specifications will not change.

Typical examples of level 2 changes are:

- Change in feedstock or precursor to resin ingredients
- Change in feedstock or precursor to fiber ingredients
- Second source of chemically and physically similar raw materials that have not been shown to be chemical equivalents
- Changes to test methods that reduce variability
- Modifications to process equipment or processes that do not change KCs or KPPs
- Addition of new similar equipment
- Expansion of existing facilities, including start-up of additional production facility machines

The type of change and the tests that demonstrate no significant effect should be documented in the appropriate part of the supplier PCD. It is recommended that side-by-side testing of the original material or method, and the new material or method, be conducted.

Using the material equivalency requirements contained in the specification, the statistical procedures given in DOT/FAA/AR-03/19 can be used to verify that the data from the altered material is equivalent to the baseline database for the material.

A new revision letter for the applicable material specification or PCD should be used when this level or higher change is incorporated. Current end-users will be notified of these changes, and approval of the end-users obtained prior to incorporation. End-user approval is only required for those users receiving material to the new revision of the material specification.

6.1.4 Level 3 Changes.

These are major changes that are subjected to a full equivalency test program, such as defined in DOT/FAA/AR-03/19. Level 3 major changes are those that have the possibility of changing either the part processing characteristics or the cured lamina properties such that there is a shift away from the average values established for the material. The supplier should develop and deliver to the end-users a test plan, a description of the change, and suggested modifications to the material and process specifications. Some end-users may require additional tests beyond those given in DOT/FAA/AR-03/19 to address specific critical design issues.

Typical examples of level 3 changes are:

- Change in fiber manufacturing process
- Change in fiber size type, size level, finish, or coupling agents
- Change in resin chemical characteristics (e.g., alternate resin ingredient)
- Change in viscosity of major resin components
- Change in manufacturing site for fiber, resin, or fabric
- Alternate weaver using same fiber and weave
- Change in resin mixing, filming and prepregging equipment, process and KPPs that change KCs or KPPs
- Change in cure cycle (e.g., temperature, dwell time, and pressure)
- Change in tack
- Change to/from autoclave from/to vacuum pressure cure
- Change in resin content (small, difference of less than 2% in resin content by weight)
- Change in nominal number of fibers per tow (small, difference of less than 200 fibers per tow)

Tests that validate level 3 changes should involve a minimum of one batch of prepreg. The material batch acceptance tests and the EBE tests listed in sections 5.5.2 and 5.5.3 are the minimum recommended tests for demonstration of equivalency. In addition, any other critical properties that are expected to be affected by the change should be included in the test plan.

Using the material equivalency requirement values contained in the specification, the statistical procedures given in DOT/FAA/AR-03/19 can be used to verify that the data from the altered prepreg is equivalent to the baseline database for the material. If equivalency to the original data cannot be confirmed, then the change will not be allowed, or a new material specification designation will be required for the altered material (see level 4 changes below).

A new revision letter for the applicable material specification or PCD should be used when the change is incorporated. Current end-users will be notified of these changes, and approval by the end-users obtained prior to incorporation. End-user approval is only required for those users receiving material to the new revision of the process specification.

6.1.5 Level 4 Changes.

Level 4 is a major change, where equivalency tests will not suffice for links to a previous material characterization. Level 4 changes require a new product identification (new specification designation), and a new qualification test program. Level 3 or lower material changes that fail to demonstrate equivalency will typically be considered level 4 changes. Some changes will be considered level 4 changes regardless of the results of equivalency results, due their significant potential effect on material properties or on part fabrication processing.

Typical examples of level 4 changes are:

- Change in resin composition
- Change in resin content (large, difference of 2% or more in resin content by weight)
- Change in nominal number of fibers per tow (e.g., 3K fibers per tow to 6K)
- Change in fiber or fabric areal weight (e.g., 145 to 190 gm/m²) that changes cured ply thickness
- Change in fiber type (e.g., T300 to AS4)
- Change in fiber manufacturer (e.g., Toray to Amoco)
- Change in type of fabric weave (e.g., plain weave to eight-harness satin)
- Addition of conductive fibers to the fabric (e.g., for lightning protection purposes)

Because level 4 changes are considered a new material, existing end-users will not be affected unless they elect to purchase the new material. An end-user who wishes to use the new material

must perform sufficient tests to qualify and certify the use of the material in the intended application.

6.2 SUPPLIER SITE QUALIFICATION.

The prepreg manufacturing site should demonstrate to end-users and certification agencies the capability to conduct raw material testing, final product testing, record maintenance, calibrations, and statistical process control. Training programs and records should be in place to assure that personnel are capable of conducting testing, running equipment, and assembling and interpreting test results. Adequate and consistent document control should be demonstrated. Major equipment maintenance and modification records should be available. An appropriate organizational structure should exist to ensure that each major function (i.e., operations and quality assurance) can perform their functions.

6.3 STATISTICAL PROCESS CONTROL.

The quality assurance department should maintain the procedures and requirements for SPC based on KCs and KPPs. The KCs are a subset of those properties detailed in the uncured and cured prepreg material requirement tables. KCs should be selected such that they ensure all properties of the material are within acceptable statistical limits. These are usually the set of requirements used for acceptance testing. KPPs are those process parameters that have a significant influence on the KCs. KPPs should be determined prior to qualification and be documented in the PCD. Average values, ranges, limits, and sampling frequency should be established and documented in the PCD.

The procedures used by the quality assurance department to conduct SPC analysis of the KCs, and KPPs should be documented in the PCD. The PCD should also include the procedures used to establish and calculate the control limits. It is expected that control charts will be maintained on the KCs and KPPs, and will be available for inspection by end-user and FAA personnel. It is strongly recommended that there be an effective program to collect, plot, analyze, and act on KC and KPP data. It is expected that action will be taken when the criteria for nonrandom data trends are met. Review should be initiated when the data is approaching the upper or lower control limits established during the initial database generation and subsequent production batches. Action should be taken when the data falls outside the upper or lower control limits.

If a KC is out of control, the cause of variation should be identified and eliminated, re-establishing statistical control. The supplier's quality assurance department must document all corrective actions affecting the process and monitor if the corrective action has been effective.

6.4 REDUCED TESTING.

Reduced testing may be established based on the capability of the KCs and KPPs. Reduced testing will require approval by the FAA, and the end-user(s) prior to being implemented. The reduced testing plan will be documented in the PCD. If KCs are found to be out of control, testing must return to the original level for a period of time until confidence in the control of the material is re-established. The reduced testing may take the form of a reduction of end-user

testing or less frequent supplier testing. A prerequisite for reduced testing is adherence to monitoring and action based on control charts.

6.5 PRODUCT CERTIFICATION.

This section of the specification should define the material acceptance testing to be performed by the material supplier and the end-user (purchaser).

6.5.1 Supplier Certification Testing.

The material supplier must perform material certification (acceptance) testing as designated in sections 5.5.2 and 5.5.3. The material specification should define the number of rolls of each prepreg batch that should be tested by the supplier. It is recommended that

- resin content and fabric areal weight testing be performed on every roll in the batch,
- other chemical and physical property tests be performed on at least the first and last rolls in the batch, and
- mechanical testing be performed on at least one roll plus one additional roll for every 1500 lb, or part thereof, of prepreg fabric in the batch (or the equivalent in lineal length of prepreg fabric).

Certification reports must be prepared for each prepreg batch. The test report must show that the batch meets all of the uncured and cured prepreg requirements. All records for each prepreg batch and the original baseline database shall be kept on permanent file. Records of raw material receiving inspection, in-process materials testing, SPC required by the PCD, and full prepreg batch traceability shall be kept for a minimum period of 10 years, unless superceded by other requirements. The supplier quality department will review the certification test results prior to shipment to an end-user. Materials that fail the acceptance criteria can undergo a material review board process.

Retest or replacement of test data is allowed only if

- an abnormality is observed or can be reasonably deduced to have occurred during testing,
- data is a statistical outlier, and
- the test has been conducted on materials that have not been prepared or conditioned properly (e.g., machining errors on laminates).

Note: Any testing error should be identified and corrected prior to retest.

If a retest is required, a complete set of replicates for the property should be tested. If the retest results fail the acceptance criteria, the material batch covered by the failed test should be rejected and dispositioned through a material review board (including engineering personnel) process.

All end-users of a material batch for which retests were performed must be notified at the time of batch shipment.

6.5.2 End-User (Purchaser) Testing.

The end-user (purchaser) quality department will perform the specified acceptance tests in sections 5.4 and 5.5 on each prepreg batch. The material specification should define the number of rolls of each prepreg batch that should be tested by the end-user. It is recommended that tests be performed on at least 1 out of every 20 rolls in the batch. Tests must be conducted on at least one roll from each separate material shipment.

The quality department must review the test results, and allow the prepreg to be released to manufacturing only upon satisfactory demonstration that the material meets the specification requirements. The end-user should hold to the same record keeping requirements and retest criteria as the material supplier.

An end-user must conduct the acceptance testing whether the material is bought directly from the manufacturer, or through a distributor. The original certification tests conducted by the prepreg manufacturer will be made available by the distributor for a specific batch sold to the end-user.

In cases where the material has demonstrated a high level of SPC control and capability for the material, it may be possible to reduce and/or eliminate the purchaser acceptance tests. If material is supplied by a distributor, it is recommended that purchaser tests be maintained as a safeguard against uncontrolled material. It is expected that the FAA will evaluate requests to reduce or eliminate end-user tests on a case-by-case basis (specific FAA policy for reduced test approvals will be developed in the future). If end-user tests are reduced or eliminated, then provisions for monitoring the thermal exposure history of each shipment of material between the supplier and end-user (including all transit periods and storage periods at a distributor) will be required.

6.5.3 Storage Relifing.

Material storage life is determined by tests conducted on material stored for the maximum desired time (see section 5.4.4). Acceptance testing of material only validates the material for storage up to the time characterized during initial qualification. To relife material that has been in storage beyond its previously validated storage life, it is recommended that a relifing procedure be included in the specification. This will provide a simple standard procedure to validate the use of material that has exceeded its original storage life:

The following is a typical relifing sequence used in specifications:

- A sample of the material is removed for relife testing.
- The sample is tested for KCs that are affected by storage (aging affects).
- If the material passes the relife tests, then the material may be used for an additional amount of time. If the material fails, it is scrapped and new material obtained.

- The storage life is extended as determined from the knowledge of the material volatility and reactivity. A typical first extension is one-half the original storage life. Extension is normally done a maximum of two times with the second extension being for half of the first extension. This would allow an additional life of three-quarters of the original storage life.

Note: The time extension is material dependent and can only be set after characterization of the specific material's aging behavior.

As an alternate, the determination of extension of storage life may be handled as a material review board (including engineering personnel) action. Again, characterization of the material must be done to give the review board the information necessary to properly extend the shelf life.

A supplier or end-user may choose to run intermediate surveillance tests on the material. This will provide information on the time degradation and age dependency of the material properties. This will reduce the risk of unacceptable material being used for production parts, causing them to be scrapped.

6.6 MATERIAL TEST METHODS.

Recommended test methods for each property are given in Chapters 3 through 7 of Volume 1 of MIL-HDBK-17, Rev. F. In general, ASTM Standard Test Methods are recommended. However in most cases, additional test specimen configuration requirements and test procedures will have to be defined to provide sufficient detail to avoid undesired variations. Deviations from industry standard methods must be clearly detailed in the specification. If end-user tests are required by the specification, it is recommended that the material supplier and end-user conduct round-robin test evaluations to reduce test result differences.

It is recommended that all tests be conducted by a laboratory certified to conduct the tests to the specified methods; this certification applies to supplier, end-user, and independent test labs. A certified laboratory follows established policies and procedures such as training of test technicians, written procedures for performing tests, documenting the dimensional accuracy of test fixtures, and tracing calibration to appropriate national standards organization (such as the National Institute of Standards and Technology (NIST) in the United States). The specification should define the requirements and procedures for certifying a test lab. It is recommended that for an industry specification, a national laboratory certification be required for facilities used.

6.7 TEST PANEL FABRICATION.

The baseline cure process to be used to produce test panels for initial database and subsequent acceptance and property sampling tests should be clearly defined in the material specification. Both the material supplier and end-users must be capable of performing the cure process on a routine basis. Process aids such as vacuum bag material, vacuum sealant, breathers, caul plates and edge dams must be defined in the material specification, a referenced process specification, or a test panel process instruction document (for further information on process control see DOT/FAA/AR-02/110). Acceptable nominal values and ranges for temperature ramp rates and holds should be defined.

Panels for material qualification, allowables and design values testing should require NDI to document the quality state of the panels. If higher-than-acceptable levels of porosity, as defined in the material/process specs, are found in the test panels, then the panels should be rejected and not used for testing. If a rejectable level of porosity is typical of the process, then consideration should be given to revising the specifications to reflect the actual process capability. Test panels for batch acceptance testing do not require NDI, but if the panels are not inspected, then the test organization assumes the risk of testing unacceptable panels.

6.8 MATERIAL DISTRIBUTORS.

Material distributors, either a facility of the manufacturer or an independent facility, must abide by all requirements of the material specification and the applicable portions of the process specification. The end-user should approve a distributor under their supplier surveillance system as described in their quality control manual. It is recommended that the material manufacturer will also have a role in authorizing distributors for proper control of the material. Material batches should remain traceable to the manufacturer's original batch and test reports. The distributor should provide copies of the original material certification and test reports to the user. The manufacturer's material, batch, and lot identification should be maintained.

A distributor should practice the same documentation of storage life and conditions as the material supplier. The distributor should be able to provide objective evidence of the material storage conditions. All shelf life should be determined from the date of material manufacture (impregnation). Any extension of the shelf life allowed by the material specification should be performed by a source approved by the original manufacturer.

If the product is repackaged, the materials used to repackage should be the same as approved for use by the material manufacturer. When the material is repackaged, it should first be allowed to reach room temperature in the unopened package, such that moisture does not condense on the prepreg. The repackaged material should be inspected for visual defects and documented. All out-time accumulated during warming, respooling, and repackaging must be subtracted from that specified by the manufacturer and documented for end-users, who assume responsibility after acceptance.

6.9 RECORDS RETENTION.

The supplier should retain records of the batch raw ingredients for a minimum of 10 years from date of manufacture. Records should contain date of manufacture, process control tests, certification tests, acceptance tests, and storage conditions.

7. THE PACKAGING AND SHIPPING SECTION OF THE MATERIAL SPECIFICATION.

The product must have suitable identification. The packaging and handling during shipping must result in the product being capable of its full handling and out-time when received by the end-user.

If repackaged by a distributor, the new packaging must be labeled properly, be functionally equivalent to the original packaging, and must meet labeling requirements. Any decrease in storage life, out-time, and handling life must be documented by the distributor and provided to all users.

7.1 MATERIAL IDENTIFICATION.

The batch number and roll number should be on three labels: one on the inside of the core, one on the outside of the shipping wrapper, and the third on the outside of the packaging box. The labels should also include the amount of material (either in length or area), material designation, name of manufacturer, specification number, and date of manufacture. The outside label should also clearly define the required material storage conditions.

7.2 INTERLEAF OR RELEASE LAYER.

The prepreg release film or paper should be easily removable, noncontaminating, and controlled as specified by the specification. Changes to a different release paper must demonstrate that no contaminants are transferred from the paper to the product, and that there is no impact on the end-user's producibility requirements. In general, it is desirable that release paper be detectable using NDI techniques.

7.3 PACKAGING.

The prepreg should have a core that adequately supports the weight of the roll without deformation. The roll should be in a sealed bag that prevents the ingress of moisture and contaminants. Additional packaging, such as a box, may be needed to ensure that the bag is not torn during shipment.

Provisions are needed to deal with rolls that are received with damage.

7.4 SHIPPING.

The appropriate shipping and storage temperatures must be established for the material. If freezer temperatures are needed to maintain product quality, time-temperature recording devices should be used to document the temperature exposure history of the shipment. Materials that have exceeded recommended limits will require a disposition process.

8. THE ACKNOWLEDGEMENT SECTION OF THE MATERIAL SPECIFICATION.

This section of the specifications should contain the standard phrase:

“A vendor shall mention this specification number and the applicable detail specification number and their revision letters, if any, in all quotations and when acknowledging purchase orders.”

9. THE REJECTION SECTION OF THE MATERIAL SPECIFICATION.

This section should contain the standard phrase:

“Product not conforming to this specification and the applicable detail specification, or to modifications authorized by purchaser, will be subject to rejection. Rejected batches, by a purchaser, should not be rerouted to other purchasers.”

10. THE NOTES SECTION OF THE MATERIAL SPECIFICATION.

This section is reserved for explanatory and other notes.

11. SUMMARY.

This document provides details of an acceptable standard practice for developing individual or industry material procurement specifications for carbon fabric prepreg material in civil aviation applications. The requirements are the result of a long history of development and lessons learned in current specifications controlling prepreg materials, specifically carbon fiber for aircraft applications. The intent is to develop a standard for these specifications thus reducing variation in requirements and eventually leading to an industrywide acceptable means of compliance. The next step is to use these specifications as the basis for third-party specifications, perhaps an Specification Development Organization, where material manufacturers could then provide the material to any aircraft part manufacturer.

This guidance develops requirements for all aspects of the procurement of prepreg materials. It first describes the details of how either an individual specification or industry specification would be created based on the need for a new material. It identifies the criteria required to control the complete process. All aspects are reviewed, including supplier, distributor, and end-user involvements. A detailed section-by-section layout and individual section requirements are provided to assist in the development of a standalone specification. The layout follows the outline of an SAE AMS specification, but any format that covers all the requirement areas is acceptable.

The major areas identified are specification scope, applicable documents technical requirements, quality assurance, packaging and shipping—including storage, and rejection disposition. The technical requirement area covers raw materials, prepregging process, and end-product (cured) property requirements. For the raw material requirements, resin and fabric are controlled through the best current practices in physical property and process control. The prepregging process requires development of key processing parameters to assure control of undesired changes and requires overall control of the process through a rigorous statistical process control scheme. The end-product requirements are controlled through the traditional array of mechanical and physical tests performed across the range of environments, which the structure is exposed.

Besides traditional control strategies, a continuous monitoring scheme showing the capabilities of all batches of the material is included. This ensures that the material is continuously capable of meeting the full range of expectations shown on the first few batches during material qualification.

This set of guidelines provides essential information on composite material control to those who may not have experience in material control. In the metallic materials community, these controls are provided by industry standards and are not apparent to the individuals designing and fabricating with these materials. When designers and fabricators enter into composites design, a source for material control techniques must be available. This document provides that source of material control information.

APPENDIX A—DEFINITION OF TERMS

This glossary is a compilation of terms with their definitions used within this report or of general interest. Definitions for this glossary were obtained from a variety of sources, which are noted at the end of the definition. Refer to MIL-HDBK-17 for a more complete listing of terms and their definitions.

A.1 GENERAL.

Autoclave, n—a closed vessel for conducting a chemical reaction or other operation under pressure and heat (Handbook of Composites).

B Stage, n—an intermediate stage in the reaction of a thermosetting resin in which the material softens when heated and swells when in contact with certain liquids but does not entirely fuse or dissolve. Materials are usually procured to this stage to facilitate handling and processing prior to final cure. See also C Stage (MIL-HDBK-17).

Bag, v—the process of enclosing the ply layers within a flexible container. See also vacuum bag (ASTM D 5687).

Baseplate, n—a flat plate on which a laminate is laid up. See also mold (ASTM D 5687).

Bleeder, n—cloth that allows matrix to flow into it for the purpose of removing excess matrix from the laminate. Net resin prepreg systems do not require the use of bleeder materials (ASTM D 5687).

Braided fabric, n—a cloth constructed by a braiding process (ASTM D 3878).

Breather, n—cloth that allows even gas flow over the lay-up surface. The breather also helps minimize bag punctures by protecting the bag from sharp points (ASTM D 5687).

Discussion: Typically within the bagging lay-up sequence, the breather material is a mixture of materials. The layer closest to the laminate is a lightweight glass fabric, such as Style 120, in order to minimize mark off on the laminate. The remaining layers are materials selected for their ability to transport gasses under pressure and elevated temperature. Typical materials are heavy-weight glasses such as Style 1000 or synthetic nonwoven materials.

Breather string, n—a glass string connected from the laminate to a breather in the bagging lay-up. It provides a path for gasses to be transferred from the laminate while minimizing matrix flow (ASTM D 5687).

Broadgoods, n—prepreg material (fabric or unidirectional) where the width is greater than 24 inches. See also tape.

C Stage, n—the final stage of the curing reaction of a thermosetting resin in which the material has become practically infusible and insoluble. See also B Stage (MIL-HDBK-17).

Caul plate, n—a flat plate used to provide a flat surface to the top of the laminate during laminate consolidation or cure (ASTM D 3878).

CFR—Code of Federal Regulations.

Cloth, n—a piece of textile fabric containing woven reinforcement without a load transferring matrix (ASTM D 5687).

Composite material, n—a substance consisting of two or more materials, insoluble in one another, which are combined to form a useful engineering material possessing certain properties not possessed by the constituents. Composites are subdivided into classes on the basis of the form of the structural constituents; Laminar: Composed of layer or laminar constituents; Particular: The dispersed phase consists of fibers; Flake: The dispersed phase consists of flat flakes; Skeletal: Composed of a continuous skeletal matrix filled by a second material (ASTM D 3878 and Handbook of Composites).

Consolidation, v—the process of forming individual plies into one solid composite laminate. For polymeric-based composite materials, consolidation is the compaction of the plies under pressure at elevated temperature until the polymer matrix material is cured.

Cure, v—to change the physical properties of a polymer by chemical reaction, which may be by condensation, polymerization, or vulcanization. This is usually accomplished by the action of heat and catalyst, alone or in combination, with or without pressure (ASTM D 907).

CPT—Cured ply thickness, n—the theoretical thickness of an individual ply, which is a function of the fiber areal weight, resin content, fiber density, and resin density.

Discussion: Cured per ply thickness is determined from the fiber areal weight, fiber volume, and fiber density:

$$CPT = \frac{FAW}{25400\rho_f FV}$$

where

CPT is theoretical cured ply thickness (inches)

FAW is fiber areal weight (g/m²)

25400 is a units conversion factor

ρ_f is the fiber density (g/cc)

FV is fiber volume (fraction, e.g., 0.61)

Cured per ply thickness can also be determined from the fiber areal weight, resin content, fiber density, and resin density:

$$CPT = \frac{FAW}{25400} \left[\frac{1}{\rho_f} + \frac{RC}{\rho_r(1-RC)} \right]$$

where

CPT is theoretical cured ply thickness (inches)
FAW is fiber areal weight (g/m²)
25400 is a units conversion factor
 ρ_f is the fiber density (g/cc)
 ρ_r is the resin density (g/cc)
RC is resin weight content (fraction, e.g., 0.33)

The actual cured ply thickness is determined by measuring the laminate thickness and dividing it by the number of plies (see SACMA SRM 10).

Fiber volume and resin content are related by the fiber and resin densities:

$$FV = \frac{1 - RC}{\rho_f} \left[\frac{1}{1 - RC/\rho_f + RC/\rho_r} \right]$$

where

FV is fiber volume (fraction, e.g., 0.61)
 ρ_f is the fiber density (g/cc)
 ρ_r is the resin density (g/cc)
RC is resin weight content (fraction, e.g., 0.33)

Dam, n—a solid material (such as silicone rubber, steel, or aluminum) used in the lay-up to contain the matrix material within defined boundaries during laminate consolidation (ASTM D 5687).

DAR—Designated Airworthiness Representative. FAA designees authorized to conduct conformity inspections on behalf of the FAA.

Debulk, v—process of decreasing voids between lamina before laminate consolidation through use of vacuum or by mechanical means. Lamina can be debulked at ambient or elevated temperature (ASTM D 5687).

Degree of cure (α), n—in thermoset polymers, the quantity of heat of reaction of the unreacted resin remaining after a reaction (cure cycle) compared to the total available quantity of heat of reaction expended by the complete reaction (cure) of a reacted resin.

Discussion: The degree of cure of a laminate can be obtained from differential scanning calorimetry (DSC) data. In order to obtain the degree of cure of a laminate, the baseline or total heat of reaction released by the complete curing of the resin (or prepreg) must first be obtained. This total heat of reaction is determined from the DSC curve. It is important to obtain the total heat of reaction from a sample that is of the same resin content as the laminate in question. This is typically accomplished by testing a sample of

the prepreg used to fabricate the laminate. The laminate in question is then tested to determine the partial heat of reaction. The DSC heating rate used to determine the baseline heat of reaction and partial heat of reaction must be the same. Typically a heating rate of 10°C per minute is used. The degree of cure is calculated as follows:

$$\alpha = 100 - \left(\frac{\Delta H_p}{\Delta H_T} \times 100 \right)$$

where

α is the percent degree of cure (ranges from 0% to 100% with 100% being fully cured)

ΔH_p is the heat of reaction released by the partially cured sample (laminate in question) expressed in Joules

ΔH_T is the total heat of reaction released by the uncured resin expressed in Joules (baseline)

Resin formulations commonly used in the aerospace industry rarely reach a degree of cure of 100%. Values of 95% to 98% are common. It should be noted that determining degree of cure by DSC is not considered the most repeatable test and is best limited to research investigations and not used as a production test. Depending on the circumstances, measurement of the glass transition temperature may be the best method to determine if a laminate is fully cured.

DER—Designated Engineering Representative. FAA designees authorized to approve engineering data.

DSC—differential scanning calorimetry. n—a technique in which the temperature difference between the substance and a reference material is measured as a function of temperature while the substance and reference material are subjected to a controlled-temperature program (ASTM E 473).

DMIR—Designated Manufacturing Inspection Representative. FAA designees authorized to conduct conformity inspections on behalf of the FAA.

End, n—in fabric, an individual warp yarn (single or ply) or cord (ASTM D 123).

ETD—Elevated Temperature Dry.

ETW—Elevated Temperature Wet.

FAA—Federal Aviation Administration.

Fabric, n—in textiles, a planar structure consisting of yarns or fibers (ASTM D 123).

FEP, n—fluorinated ethylenepropylene.

Discussion: fluorinated ethylenepropylene is a fluorocarbon polymer commonly known by its DuPont trade name Teflon[®] FEP.

Fiber, n—in textiles, a generic term for any one of the various types of matter that form the basic elements of a textile and that is characterized by having a length at least 100 times its diameter (ASTM D 123).

FAW—Fiber areal weight n—the weight per area of the fiber reinforcement within a composite, expressed as grams per square meter or ounces per square yard. See also prepreg areal weight.

Fiber content, n—the amount of fiber present in a composite expressed either as a percent by weight or percent by volume. This is sometimes stated as a fraction, that is, fiber volume fraction (ASTM D 3878).

Fiber volume fraction (FV or V_f), n—see fiber content (ASTM D 3878).

Filament, n—a fibrous form of matter with an aspect ratio >10 and an effective diameter <1 mm (ASTM D 3878).

Fill, n—in a woven fabric, (1) the yarn running from selvage to selvage at right angles to the warp and (2) fiber inserted by the shuttle during weaving also designated as filling (ASTM D 3878, MIL-HDBK-17, and ASTM D 5687).

Fill surface, n—in a woven fabric where each fill yarn crosses over more than one warp yarn, the ply surface that shows the larger area of fill tows with respect to warp tows.

Flip/flop, v—the process of alternating plies through an angle orientation of 180° during laminate lay-up. This practice is commonly used if the material of the same width as the laminate has a recurring flaw. The process changes the location of the flaw so that it does not unduly affect the laminate structure (ASTM D 5687).

Glass transition, n—the reversible change in an amorphous polymer or in amorphous regions of a partially crystalline polymer from (or to) a viscous or rubbery condition to (or from) a hard and relatively brittle one (MIL-HDBK-17).

Discussion: The glass transition generally occurs over a relatively narrow temperature region and is similar to the solidification of a liquid to a glassy state; it is not a phase transition. Not only do hardness and brittleness undergo rapid changes in this temperature region but other properties, such as thermal expansibility and specific heat, also change rapidly. This phenomenon has been called second order transition, rubber transition, and rubbery transition. The word transformation has also been used instead of transition. Where more than one amorphous transition occurs in a polymer, the one associated with segmental motions of the polymer backbone chain or accompanied by the largest change in properties is usually considered to be the glass transition (ASTM D 883).

Glass transition temperature (T_g), n—the approximate onset or midpoint of the temperature range over which the glass transition takes place (MIL-HDBK-17).

Discussion: The glass transition temperature can be determined readily only by observing the temperature at which a significant change takes place in a specific electrical, mechanical, or other physical property. Moreover, the observed temperature can vary significantly depending on the specific property chosen for observation and on details of the experimental technique (for example, rate of heating and frequency). Three common methods for determining T_g are Thermal Mechanical Analysis, Differential Scanning Calorimetry, or Dynamic Mechanical Analysis.

Knit, v—a textile process that interlocks, in a specific pattern loop, by means of needles or wires (ASTM D 3878).

Knitted fabric, n—a cloth constructed by a knitting process (ASTM D 3878).

Lamina, n—a subunit of a laminate consisting of one or more adjacent plies of the same material with identical orientation (ASTM D 3878).

Laminate, n—any fiber or fabric-reinforced composite consisting of lamina (plies) with one or more orientations with respect to some reference direction (ASTM D 3878).

Lamination, v—see consolidation.

Laminate coordinate axes, n—a set of coordinate axes, usually right-handed Cartesian, used as a reference in describing the directional properties and geometrical structure of the laminate. Usually, the x-axis and the y-axis lie in the plane of the laminate, and the x-axis is the reference axis from which ply angle is measured (ASTM D 3878).

Laminate principal axis, n—the laminate coordinate axis that coincides with the direction of maximum in plane Young's modulus (ASTM D 3878).

Lay-up, n—(1) the stack of plies in specified sequence and orientation before infusion, cure, or consolidation; (2) the complete stack of plies, bagging material, and so on before cure or consolidation; and (3) a description of the component materials, geometry, etc. of a laminate (ASTM D 3878).

lay-up, v—to stack plies of material in specified sequence and orientation (ASTM D 3878).

Lay-up code, n—a designation system for abbreviating the stacking sequence of laminated composites (ASTM D 3878).

Mandrel, n—a form, fixture, or male mold used as the base for production of a part in processes such as lay-up or filament winding (ASTM D 3878).

Material form, n—the contour, arrangement, and structure of an unconsolidated composite material, especially with regard to the geometry and nature of the reinforcement. Factors considered part of the material form include, but are not limited to, reinforcement length (for

discontinuous reinforcements), tow size or count, fabric areal weight, fabric style, reinforcement content, and ply thickness (ASTM D 3878).

Matrix, n—the continuous constituent of a composite material, which surrounds or engulfs embedded filler or reinforcement (ASTM D 3878).

Matrix content, n—the amount of matrix present in a composite expressed either as a percent by weight or percent by volume. Standard practice is to specify matrix content as weight percent (ASTM D 3878).

MIDO—Manufacturing Inspection District Office for the FAA.

MOL—Material Operational Limit.

Mold, n—the support structure that holds the laminate or lay-up during laminate consolidation process (ASTM D 5687).

MRB—Material Review Board.

NIST—National Institute of Standards and Technology.

NDI—nondestructive inspection, v—to identify and measure abnormal conditions within a laminate without degrading or impairing the utility of the material.

Nonperforated FEP, n—a nonporous fluorinated ethylenepropylene film used as a release film in the bagging lay-up.

Discussion: Fluorinated ethylenepropylene is a fluorocarbon polymer commonly known by its DuPont trade name Teflon[®] FEP.

Nonperforated TFE, n—a nonporous tetrafluoroethylene film used as a release film in the bagging lay-up (ASTM D 5687).

Discussion: Tetrafluoroethylene is a fluorocarbon polymer commonly known by its DuPont trade name Teflon[®] TFE.

Nonporous TFE-coated cloth, n—a cloth coated with tetrafluoroethylene used as a release material in the bagging process (ASTM D 5687).

Nonwoven fabric, n—a cloth constructed by bonding or interlocking, or both (but not interlacing), fiber by any combination of mechanical, chemical, thermal, or solvent means (ASTM D 3878).

Panel, n—a uniformly contoured composite laminate, typically flat (ASTM D 5687).

Peel ply—a cloth material that does not contain transferable chemical release agents and is designed for cocure with the surface ply of a laminate. It is generally used for the purpose of protecting a bonding surface. It is intended to be completely removed from the laminate by

peeling immediately prior to a subsequent bonding operation. Removal can be difficult, but the result is a clean and highly textured resin fracture surface. It may undergo treatment (e.g., mechanical calendaring), but not with release chemicals. This surface is typically suitable for structural adhesive bonding.

Perforated FEP, n—a porous fluorinated ethylenepropylene film used in the bagging process that allows gasses or excess matrix materials to escape (flow) from a laminate during consolidation while protecting the laminate from physical bonding to other items such as caul plates.

Perforated TFE, n—a porous tetrafluoroethylene film used in the bagging process that allows gasses or excess matrix materials to escape (flow) from a laminate during consolidation while protecting the laminate from physical bonding to other items such as caul plates (ASTM D 5687).

Plied yarn, n—a yarn formed by twisting together two or more single yarns in one operation (ASTM D 3878).

Ply, n—in laminar composites, the constituent single layer as used in fabricating or occurring within a composite structure (ASTM D 3878).

Ply coordinate axes, n—a set of Cartesian coordinates, two of which lie within the plane of the ply, one axis of which is parallel to the principal fiber direction, and the other axis perpendicular to the principal fiber direction (the third axis is through the ply's thickness) (ASTM D 3878).

Ply count, n—in laminated composite materials, the number of plies or lamina used to construct the composite (ASTM D 3878).

Ply orientation, n—the acute angle (theta) including 90° between a reference direction and the ply principal axis. The ply orientation is positive if measured counterclockwise from the reference direction and negative if measured clockwise (ASTM D 3878).

Ply principal axis, n—the ply coordinate axis that coincides with the direction of maximum in plane Young's modulus. For balance weave fabric, either warp or fill direction may be chosen (ASTM D 3878).

Polymer, n—an organic material composed of molecules characterized by the repetition of one or more types of monomeric units (MIL-HDBK-17).

Polymerization, n—a chemical reaction in which the molecules of a monomer(s) are linked together in repeating units to form larger molecules (ASTM D 907).

Porosity, n—a condition of trapped pockets of air, gas, or vacuum within a solid material, usually expressed as a percentage of the total nonsolid volume to the total volume (solid plus nonsolid) of a unit quantity of material (MIL-HDBK-17).

Porous TFE-coated cloth, n—a porous cloth coated with tetrafluoroethylene used in the bagging process that allows gasses or excess matrix materials to escape (flow) from a laminate during

consolidation. It differs from perforated TFE in that it gives a textured surface to the laminate (ASTM D 5687).

Prepreg, *n*—a ready to mold or cure fibrous reinforcement impregnated with a polymeric matrix. Its form may be sheet, tape, or tow. For thermosetting matrices, it has been partially cured to a controlled viscosity called B Stage (ASTM D 3878 and MIL-HDBK-17).

PAW—prepreg areal weight, *n*—the weight per area of the prepreg composite material, expressed as pounds per square foot or the inverse square feet per pound. Used as a conversion factor to convert prepreg area to prepreg weight. See also fiber areal weight.

Discussion: Prepreg areal weight is a function of resin content and fiber areal weight:

$$PAW = \frac{FAW}{1 - RC}$$

Where:

PAW is prepreg areal weight (g/m²)
FAW is fiber areal weight (g/m²)
RC is resin weight content (fraction, e.g., 0.33)

To convert g/m² to lb/ft² multiply by 204.81 x 10⁻⁶.

Prolong, *n*—a deliberate extension of the part designed to yield material for quality assurance/control.

Reinforcement, *n*—in a composite material, the discrete constituent of a composite material, either fiber or particle, which is contained within the continuous matrix (ASTM D 3878).

Resin, *n*—a solid or pseudo-solid organic material, often of high molecular weight, which exhibits a tendency to flow when subjected to stress, usually has a high softening or melting range, and usually fractures conchoidally (ASTM D 3878).

RC resin content, *n*—see matrix content (ASTM D 3878).

Release fabric—A cloth material that contains transferable chemical release agents and is designed for cocure with the surface ply of a laminate. It is generally used for the purpose of allowing the laminate to be more easily removed from the tooling. It is intended to be completely and easily removed from the laminate by peeling. It leaves an unfractured, relatively smooth surface impression and a chemical residue on the laminate. This surface is typically unsuitable for structural adhesive bonding.

Release film—A sheet of film designed for cocure with the surface ply of a laminate. It is generally used for the purpose of allowing the laminate to be more easily removed from the tooling. The film material is generally a derivative of polytetrafluoroethylene, PTFE (Teflon). It is intended to be completely and easily removed from the laminate by peeling. It leaves a

smooth surface finish with minimal impression and a chemical residue on the laminate. This surface is typically unsuitable for structural adhesive bonding.

Sealant, n—a high-temperature material used to seal the edges of a vacuum bag to a base plate during consolidation (ASTM D 5687).

Selvage, n—the woven edge portion of a fabric parallel to the warp (ASTM D 3878).

Single yarn, n—an end in which each filament follows the same twist (ASTM D 3878).

Stacking sequence, n—the arrangement of ply orientations and material components in a laminate specified with respect to some reference direction (ASTM D 3878).

Staggered, adj—the description of ply placement where the joints are not positioned in the same in-plane location through some specified thickness of the laminate (ASTM D 5687).

Stitching, verb—the act of combining fabrics/textiles by joining together with a separate stitching thread using one or more needles.

Tape, n—prepreg material (typically unidirectional material) equal to or less than 24 inches in width. Also see broadgoods.

Textile, n—a general term applied to fibers and organized assemblies of fibers with sufficient integrity to retain the organization (ASTM D 3878).

Thermoplastic, n—a plastic that repeatedly can be softened by heating and hardened by cooling through a temperature range characteristic of the plastic, and that in the softened state can be shaped by flow into articles by molding or extrusion for example (ASTM D 883).

Thermoset, n—a class of polymers that, when cured using heat, chemical, or other means, changes into a substantially infusible and insoluble material (ASTM D 3878).

Tow, n—in fibrous composites, a continuous, ordered assembly of essentially parallel, collimated filaments, normally without twist and of continuous filaments (ASTM D 3878).

Tracer yarn, n—in a woven fabric, a yarn woven into the fabric for the purpose of tracing the direction of the warp and fill fibers or tows.

Traveler, n—a coupon with the same nominal thickness, and preferably width, as the test specimen made of the same material, and processed similarly to the specimen except usually without tabs or gages. The traveler is used to measure mass changes during environmental conditioning when it is impractical to measure these changes on the actual specimen (ASTM D 5687).

Traveler panel, n—(a.k.a. witness panel) a panel that is subjected to the same conditions as a part or group of parts to allow destructive tests to verify processing.

Unidirectional, n—any fiber-reinforced composite with all the fibers aligned in a single direction. Both prepreg material and consolidated laminates can be described as being unidirectional.

Vacuum bag, n—a low gas permeable material used to enclose and seal the lay-up during a consolidation or debulking cycle (ASTM D 5687).

Vacuum couple, n—the mechanical connection that seals the vacuum source to the lay-up during a consolidation or debulking cycle (ASTM D 5687).

Viscosity, n—is a measure of the resistance of a liquid to shear forces, (see also permeability).

Vitrification, n—the point during polymerization where the T_g of the polymer rises above the temperature of cure.

Void, n—any pocket of enclosed gas or air within a composite (ASTM D 3878).

Void content, n—the volume percentage of voids in a composite (ASTM D 3878).

Warp, n—(1) the yarn running lengthwise in a woven fabric; (2) a group of yarns in long lengths and approximately parallel, put on beams or warp reels for further textile processing including weaving, knitting, twisting, dyeing, and so forth (ASTM D 3878).

Warp surface, n—in a woven fabric, where each warp yarn crosses over more than one fill yarn, the ply surface that shows the larger area of warp tows with respect to fill tows (ASTM D 3878).

Warp surface nesting, v—process of laying up fabric plies in an alternating pattern where the warp surface is placed up, and then for the next ply the warp surface is placed down, thus nesting the plies.


Weave, v—interlaces, in a specific pattern, strands or yarns orientated in two or more directions in a planar textile process (ASTM D 3878).

Woven fabric, n—a cloth constructed by a weaving process (ASTM D 3878).


Yarn, n—in fibrous composites, a continuous, ordered assembly of essentially parallel, collimated filaments, normally with twist, and either discontinuous or continuous filaments (ASTM D 3878).

A.2 FABRIC DEFECT DEFINITIONS.


Baggy cloth, n—in a woven fabric, a cloth that will not lie flat on a cutting table (also, crooked cloth, ridgy cloth, wavy cloth).

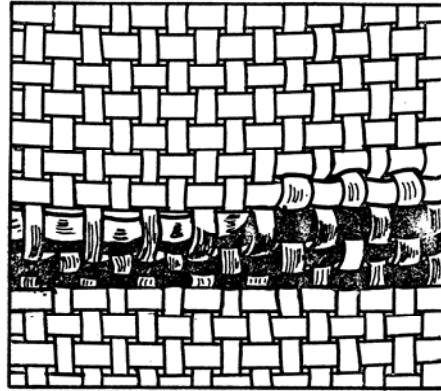


Broken tracer yarn, n—in a woven fabric, a damaged tracer yarn.

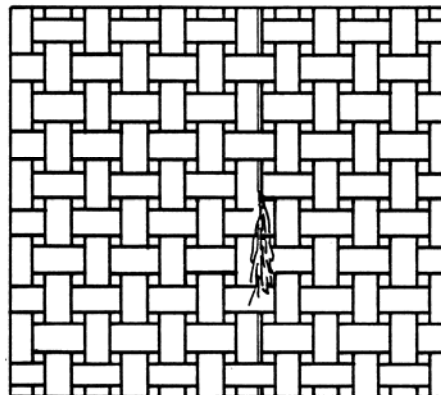


Broken warp or fill, n—in a woven fabric, a single warp fill tow, or yarn that has been severed or broken (also, broken pick, cut pick).

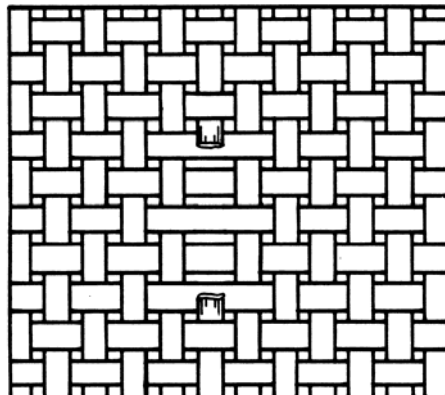


Crease or wrinkle, n—in a woven fabric, a break or line in a fabric usually caused by a sharp fold (also, mill wrinkle, wrinkle mark).

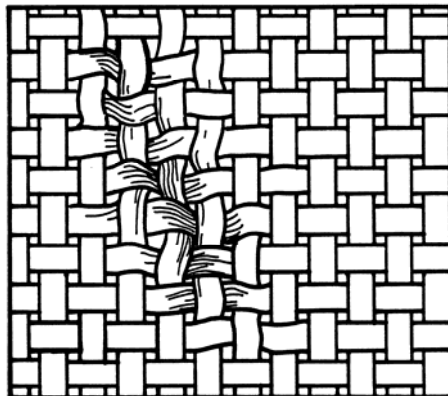


Cut or tear, n—in a woven fabric, adjacent yarns or tows that have been cut or broken.

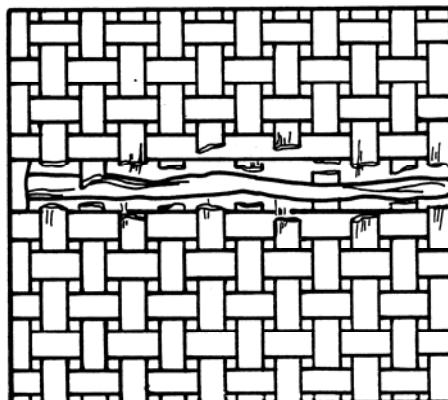


Float, n—in a woven fabric, a place in the fabric where a warp or filling yarn or tow extends unbound over the yarns or tows that should be interlaced (also, harness skip, overshot, skip).

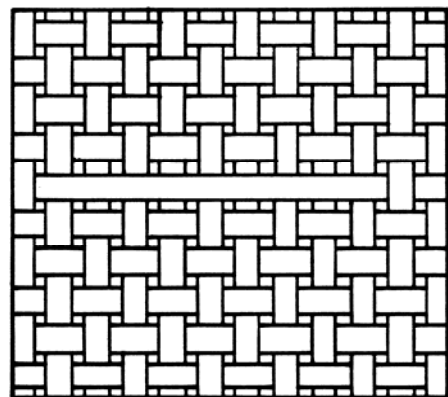


Fuzzball (also fuzz ball), n—in a woven fabric, loose or frayed fibers that have formed into a ball and are entwined either within the fabric or on the surface (also, balling up, lint ball, snowball).

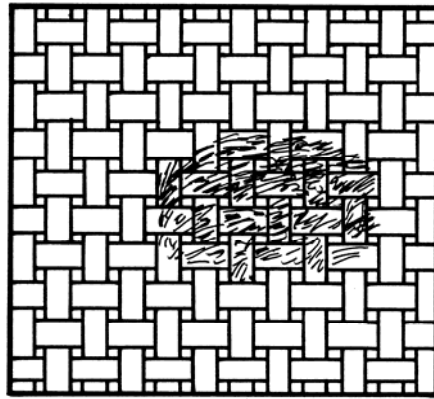


Hang pick, n—in a woven fabric, a pick (fill yarn) caught on a warp yarn producing a triangular-shaped hole in the fabric (also, hung filling yarn, hang shot).

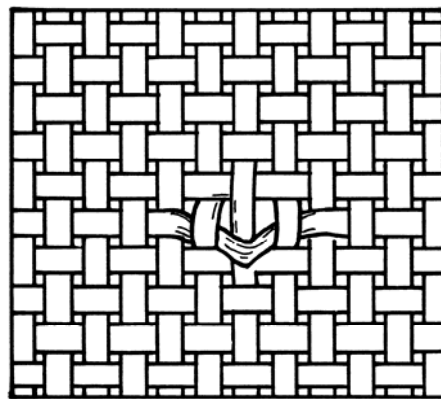


Kink, n—in a woven fabric, a yarn that has doubled back on itself to form a loop in the yarn (also, center loop, curl, snarl, kinky thread, looped yarn).

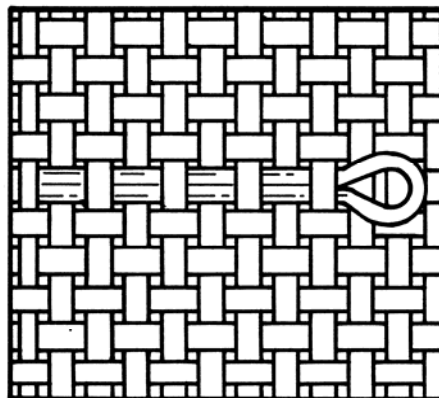


Loose pick, n—in a woven fabric, a filling yarn that is not flush with the surrounding fabric usually caused by insufficient tension (also, loose filling yarn, slack pick, slack filling).

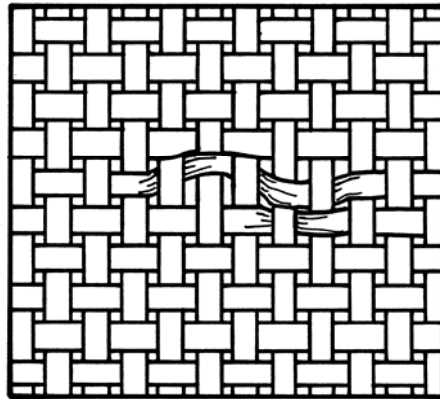


Missing pick, n—in a woven fabric, a filling yarn or tow missing from all or a portion of the width of the fabric (also, missing filling yarn, filling run out).

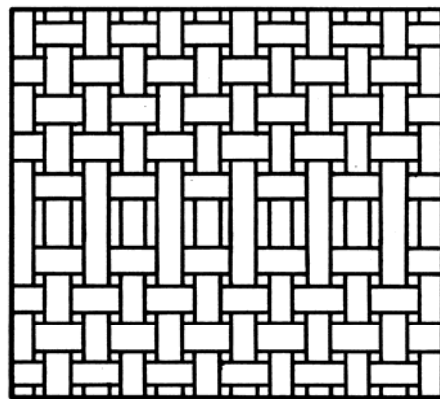


Mispick, n—in a woven fabric, a pick that is not properly interlaced, which causes a break in the weave pattern (also, wrong pick).

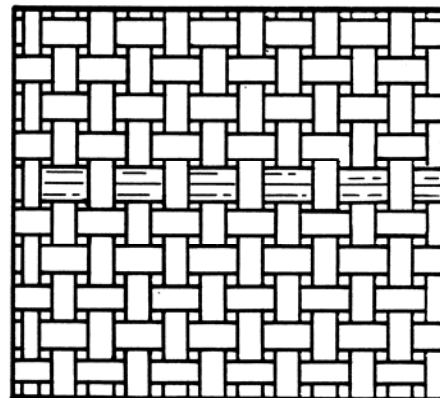


NEP, n—in a woven fabric, one or more fibers occurring in a tangled and unorganized mass (also, bird's nest, fly waste).

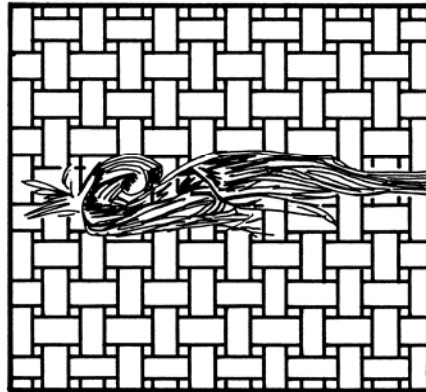


Pulled-in filling, n—in a woven fabric, an extra filling yarn or tow dragged into the fabric along with a regular filling yarn or tow (also, double pick, dragged-in, jerked-in, lashed-in, whipped-in).

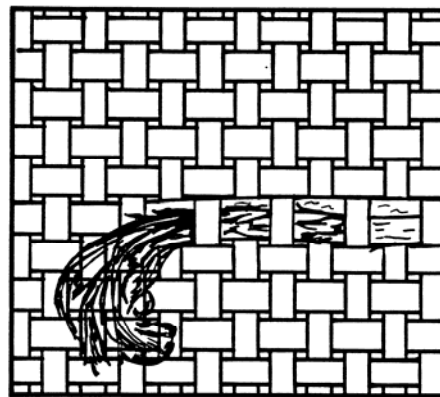


Skewing, n—in a woven fabric, a condition where the warp and fill yarns or tows are not at right angles to each other (also, bias filling).

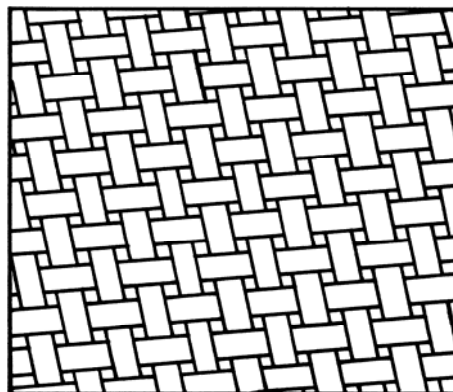


Slub, n—in a woven fabric, an abruptly thickened place in the yarn or tow (also, slug, bunch, lump, piece, slough off).

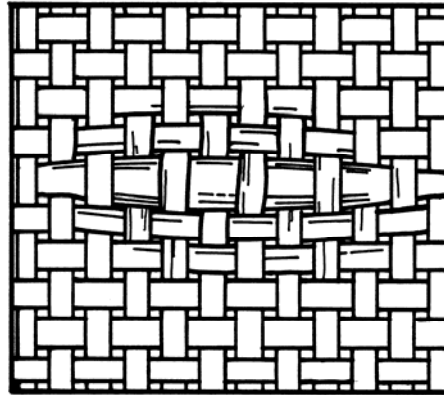


Smash, n—in a woven fabric, a place in the fabric where a number of warp or fill yarns or tows have been broken (also, breakout, slam-off).

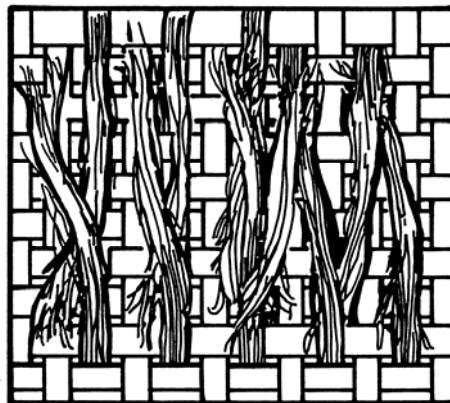


Splice, n—in a woven fabric, a portion of the fabric that has been cut and rejoined.

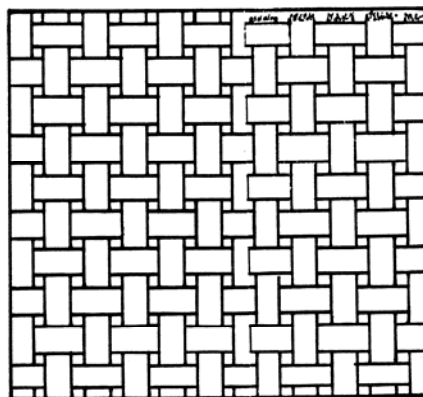

Waviness, n —in a woven fabric, a condition where the warp, fill yarns, or tows are in a sinusoidal or wave pattern (weave distortion).

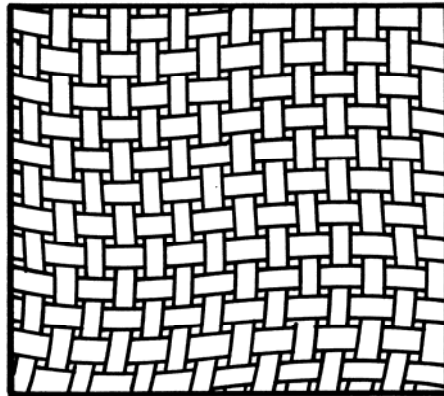

Weave separation, n —in a woven fabric, an opening between yarns or tows due to improper yarn or tow alignment (also, crack, broken weave, open place, thin spot, shier).

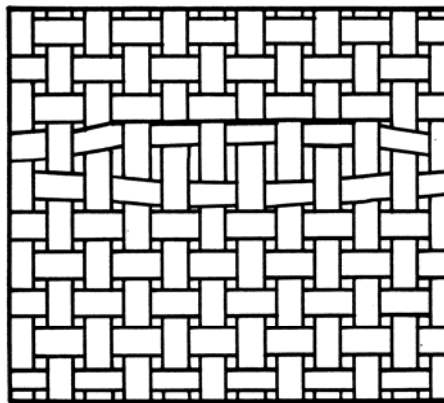

Yarn splice, n —in a woven fabric, a yarn or tow that has been cut or broken and subsequently overlap spliced (also, tow splice).

