



Effects of High-Temperature Exposures on the Fatigue Life of Superalloy Udimet[®] 720

Timothy P. Gabb and Jack Telesman
Glenn Research Center, Cleveland, Ohio

Peter T. Kantzos
Ohio Aerospace Institute, Brook Park, Ohio

Joseph W. Sweeney
Akima Corporation, Cleveland, Ohio

Paul F. Browning
Solar Turbines, Inc., San Diego, California

The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the Lead Center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA's counterpart of peer-reviewed formal professional papers but has less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or cosponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized data bases, organizing and publishing research results . . . even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA Access Help Desk at 301-621-0134
- Telephone the NASA Access Help Desk at 301-621-0390
- Write to:
NASA Access Help Desk
NASA Center for Aerospace Information
7121 Standard Drive
Hanover, MD 21076



Effects of High-Temperature Exposures on the Fatigue Life of Superalloy Udimet[®] 720

Timothy P. Gabb and Jack Telesman
Glenn Research Center, Cleveland, Ohio

Peter T. Kantzos
Ohio Aerospace Institute, Brook Park, Ohio

Joseph W. Sweeney
Akima Corporation, Cleveland, Ohio

Paul F. Browning
Solar Turbines, Inc., San Diego, California

Prepared for the
131st Annual Meeting and Exhibition
sponsored by the Minerals, Metals, and Materials Society
Seattle, Washington, February 17–21, 2002

National Aeronautics and
Space Administration

Glenn Research Center

Acknowledgments

The authors would like to acknowledge Mike Fitzpatrick of Solar Turbines and Arun Watwe of Wyman-Gordon Forgings for overseeing Udimet 720 material processing. Support of the Department of Energy and the NASA Ultrasafe program is also acknowledged.

The Aerospace Propulsion and Power Program at NASA Glenn Research Center sponsored this work.

Trade names or manufacturers' names are used in this report for identification only. This usage does not constitute an official endorsement, either expressed or implied, by the National Aeronautics and Space Administration.

Available from

NASA Center for Aerospace Information
7121 Standard Drive
Hanover, MD 21076

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22100

Available electronically at <http://gltrs.grc.nasa.gov/GLTRS>

Effects of High-Temperature Exposures on the Fatigue Life of Superalloy Udimet[®] 720

Timothy P. Gabb and Jack Telesman
National Aeronautics and Space Administration
Glenn Research Center
Cleveland, Ohio 44135

Peter T. Kantzos
Ohio Aerospace Institute
Brook Park, Ohio 44142

Joseph W. Sweeney
Akima Corporation
Cleveland, Ohio 44126

Paul F. Browning
Solar Turbines, Inc.
San Diego, California 92101

Abstract

The purpose of this study was to examine the effects of extended exposures on the near-surface fatigue resistance of a disk superalloy. Powder metallurgy processed, supersolvus heat-treated Udimet[®] 720 (U720) fatigue specimens were exposed in air at temperatures from 650 to 705 °C for 100 hr to over 1000 hr. They were then tested using conventional fatigue tests at 650 °C to determine the effects of exposure on fatigue resistance. The exposures reduced life by up to 70 percent and increased the scatter in life, compared to unexposed levels. Fractographic evaluations indicated the failure mode was shifted by the exposures from internal to surface crack initiations. The increased scatter in life was related to the competition between internal crack initiations at inclusions or large grains producing longer lives, and surface crack initiations at an environmentally affected surface layer producing shorter lives.

Introduction

Low-cycle fatigue (LCF) tests conventionally used to characterize the LCF resistance of disk superalloys are usually performed at cyclic frequencies of 0.33 Hz or faster, in the interest of time and cost. However, service conditions for disks in some aerospace and land-based gas turbine engines can produce major cycle periods extending from minutes to hours to days. Over a service life, this can produce total service times exceeding 1000 hr for aerospace applications and 100 000 hr for land-based applications. The costs of running strain-controlled LCF tests in this manner would be prohibitive from both time and cost considerations. However, some aspects of the surface effects of realistic total exposure times can be considered economically.

Time-dependent effects of realistic mission cycles on fatigue resistance can be significant in superalloy disks. Earlier studies have shown that specimen fatigue tests, which have dwell times included within each cycle, can give lives significantly degraded from test cycles using conventional frequencies of 0.33 to 0.5 Hz (refs. 1 to 6). However, strain-controlled tests with strain dwells at maximum strain can allow relaxation of maximum cyclic stresses (ref. 7). This reduction in cyclic stress can counterbalance some of

the creep and environmental damage produced by service dwell times. Such stress relaxation can be exaggerated over that possible in real disks in service, which have large, elastically constrained volumes. A disk cannot be allowed to creep significantly due to very tight blade, clearance, and rotational constraints within a turbine engine rotor. The majority of a disk is therefore usually not subjected to stress-temperature conditions allowing creep over 0.1 to 0.2 percent during service life. However, the environmental exposures are present over the entire disk surface, and their effects on disk life need to be considered for accurate prediction of disk life. Extended exposures at elevated temperatures prior to conventional LCF testing has been shown to capture some of the effects of service environment in a cast blade alloy at 871 °C (ref. 8).

The purpose of this study was to examine the effects of extended exposures on the near-surface fatigue resistance of a disk superalloy. Powder metallurgy-processed, supersolvus heat-treated Udimet[®] 720 (U720) superalloy fatigue specimens were exposed in air at several potential maximum application temperatures of 650 to 704 °C for extended times. They were then tested using conventional fatigue tests at 650 °C to determine the effects of exposure on fatigue resistance.

Materials and Procedure

Material Processing

A U720 powder metallurgy disk was obtained courtesy of Solar Turbines from Wyman-Gordon Forgings. The powder was first atomized in argon and screened through a 150-mesh screen. It was then canned, hot isostatically pressed, extruded, and isothermally forged using typical conditions for this alloy (ref. 9). The forged pancake was then machined to a disk about 61 cm in diameter and 10-cm thick.

The disk was heat-treated at Wyman-Gordon Forgings on a steel tray in a gas-fired furnace. The solution heat treatment was performed at 1171 °C for 3 hr. The disk was then transferred in about 60 sec to a tank containing agitated oil held at a temperature of about 50 °C and oil quenched. The quenched disk was visually confirmed to be free of quench cracks. It was then aged at 760 °C/8 hr + 650 °C/24 hr, as typically performed on this alloy (ref. 9).

Exposures and Mechanical Testing

Specimens were extracted from the disk midsection away from all quenched surfaces in order to minimize any effects on mechanical properties of quenching rate variations at different specimen locations in the disk. The specimens had a gage diameter of 0.64 cm and length of 1.9 cm. Many of the fully machined specimens were first exposed in air as groups of five lying on a tray in a conventional resistance-heated furnace. Exposure temperatures at the fatigue testing temperature of 650 °C and at an elevated temperature of 704 °C were used for 100 and 1029 hr. A centerpoint exposure condition of 677 °C for 510 hr was also included. Fatigue tests were performed at 650 °C in closed-loop servo-hydraulic testing machines using induction heating and axial extensometers. Most baseline fatigue tests were performed in two stages to reduce total testing time. First, the test was conducted in strain control conditions using a triangular waveform to a total strain range of 0.7 percent and a strain ratio of $R_\epsilon = \epsilon_{\min}/\epsilon_{\max} = 0$, using a frequency of 0.33 Hz. After cycling for 24 hr, tests were continued to failure in load control conditions using a triangular waveform to achieve the same stabilized maximum and minimum loads as before, at a frequency of 10 Hz. Verification cyclic dwell fatigue tests were performed with strain controlled throughout the test using a triangular waveform with the same total strain range and strain ratio, but using a load cycle taking 20 sec followed by a dwell at 0 strain for 40 sec. The dwell was

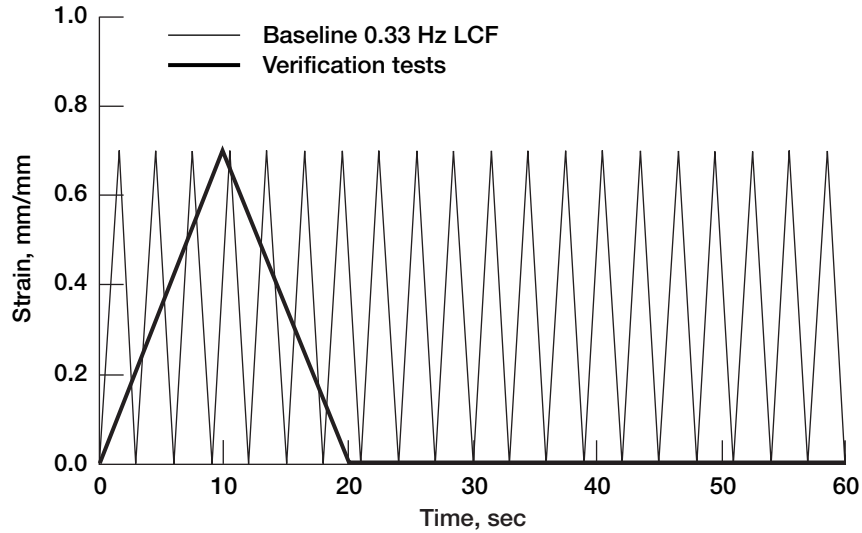


Figure 1.—Comparison of strain-time test waveforms.

performed at zero strain to prevent cumulative relaxation of the maximum cyclic stress due to the dwells. This gave a total cyclic dwell test time of 1 min per cycle. The strain versus time waveforms of baseline and verification fatigue tests are compared in figure 1. All tests were continued until failure.

Fractographic evaluations were performed on all specimens after failure to determine the crack initiation sites. Metallographic sections were prepared from one representative specimen for each exposure and testing condition. The sections were taken from the gage sections and oriented normal to the loading axis. Grain sizes were determined from selected specimens according to ASTM E112 linear intercept procedures using circular grid overlays.

Results and Discussion

Metallographic Characterizations

The typical microstructures of untested specimens are shown in figure 2. The material had a coarse grain size of ASTM 6.0 (45 μm) due to the supersolvus heat treatment. The grain boundaries displayed serrations due to the formation of relatively coarse γ' -precipitates during the relatively slow cooling of the deeply imbedded specimen blanks. The mean diameter of γ' -precipitates within the grains was about 0.4 μm .

Fatigue Test Results

Fatigue life is shown versus estimated cumulative probability to compare the effects of various exposures on subsequent LCF life in figure 3. Lives of exposed specimens were invariably lower than unexposed specimens, reducing mean life (arrow) by up to 70 percent. It can also be seen that exposed specimens had lower slopes on the probability plot, indicating more scatter and larger standard deviations than for unexposed specimens. Scatter plots of life versus exposure temperature and time are shown in figure 4.

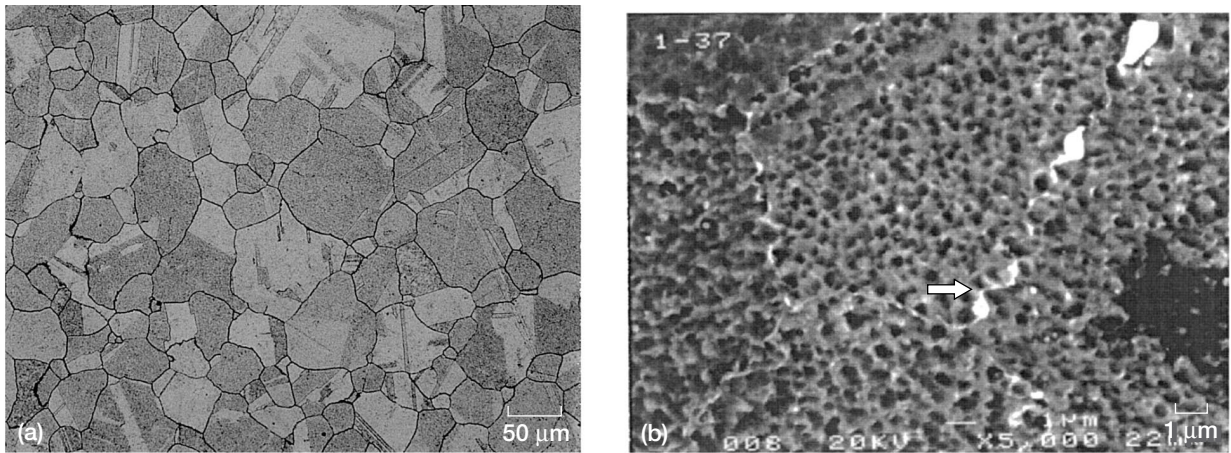


Figure 2.—Typical microstructures. (a) Grain size. (b) Serrated grain boundaries decorated with carbides (arrow).

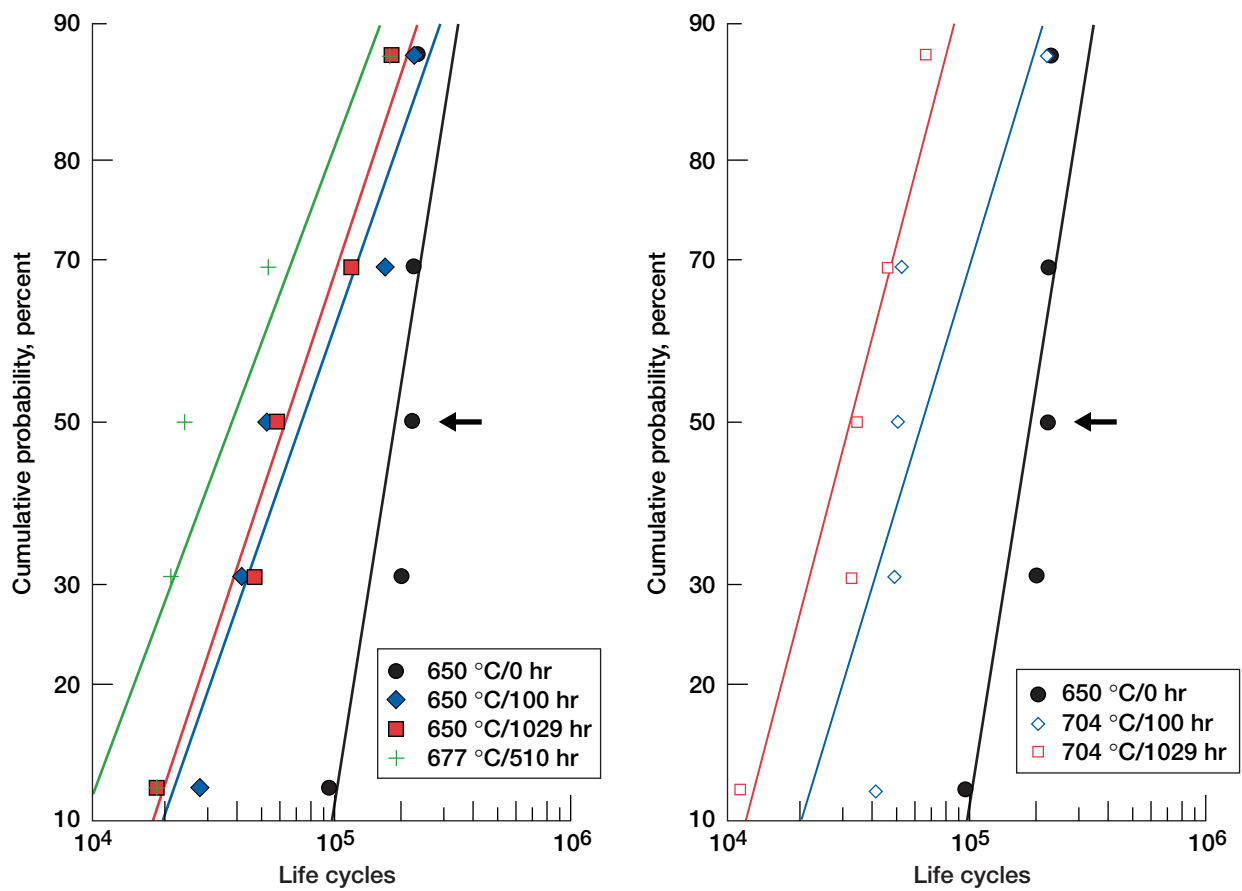


Figure 3.—Estimated cumulative probability versus fatigue life of exposed specimens (mean life indicated by arrows).

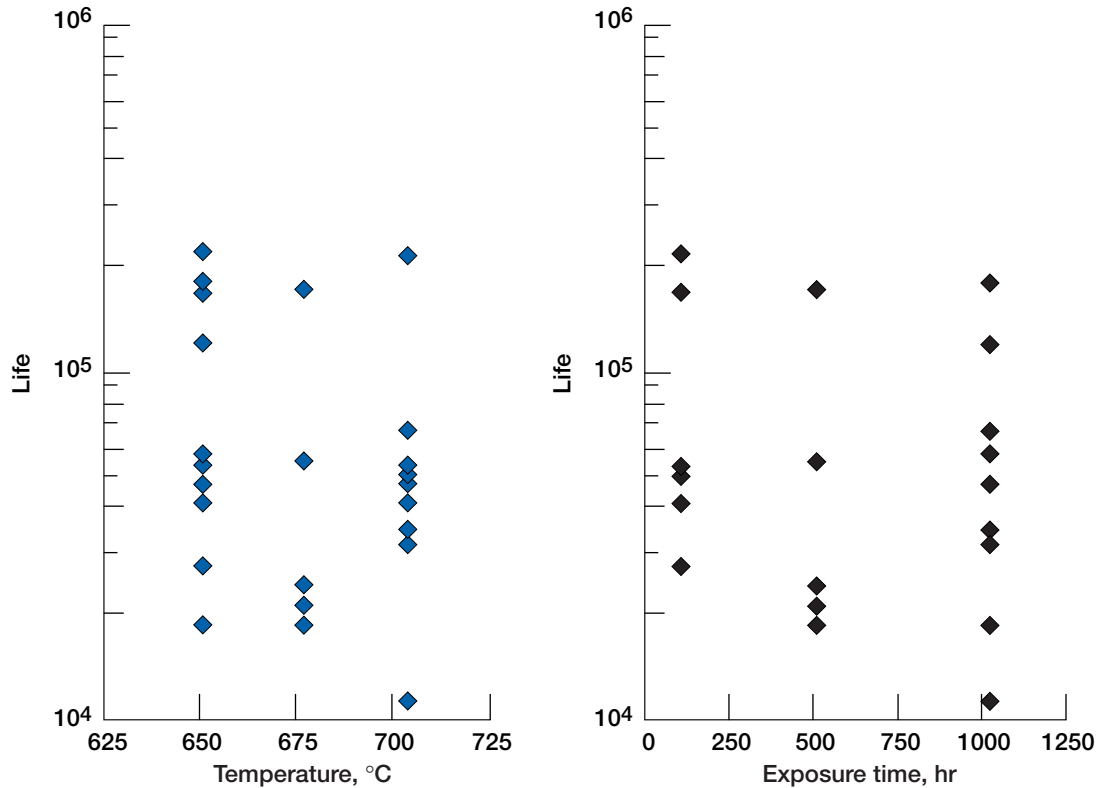


Figure 4.—Fatigue life versus exposure temperature and time.

A nonlinear regression model was generated using forward stepwise regression with the factors exposure temperature and $\log(\text{time})$ to model fatigue life. The resulting relationship obtained had poor correlation and only included time

$$\log(\text{life}) = 4.9409 - 0.3174 \times t'$$

where $t' = (\log(\text{time}) - 1.5062) / 1.506$. This gave a low adjusted correlation coefficient $R^2_{\text{adj}} = 0.307$ and root mean square (rms) error of 0.322.

Fatigue Failure Sites

Typical fatigue failure sites are compared in figures 5 to 6. Unexposed specimens failed from cracks initiating internally at large grains or at nonmetallic inclusions, as shown in figure 5. The large grains appeared to start cracks by failing on a single flat plane or “facet,” presumably due to concentrated slip along a single slip band (ref. 7). The nonmetallic inclusions were predominantly composed of Al_2O_3 , and were presumably introduced during the powder production and handling processes before consolidation (ref. 6). Exposed specimens sometimes failed from cracks initiating internally at these above sites, but more often failed from cracks initiating at an environment-affected surface layer, especially for long exposure times. These cracks initiated and grew in a transgranular mode normal to the loading axis, as shown in figure 6.

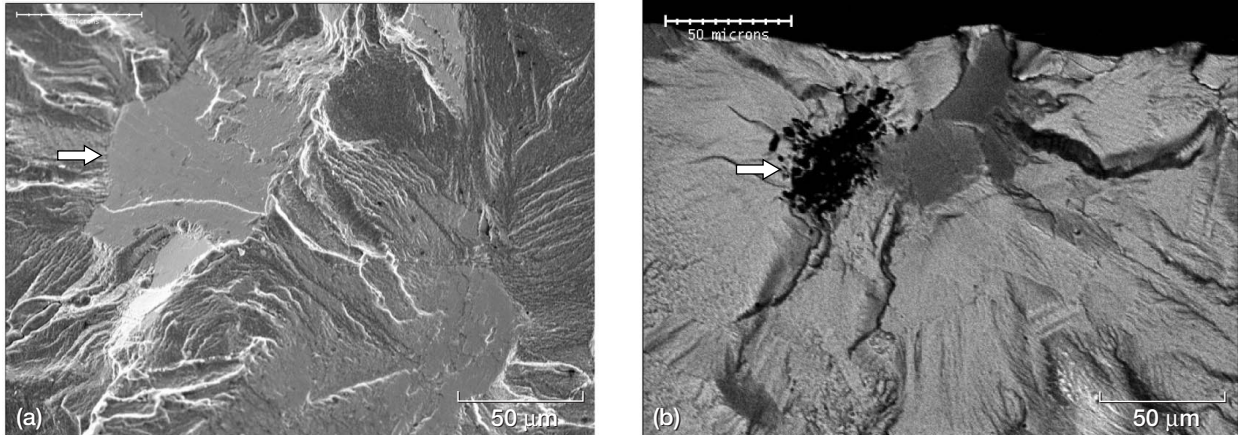


Figure 5.—Unexposed specimens tested at 650 °C. (a) Failing from internal large-grain facet giving longest life of 224 803 cycles. (b) Failing from near-surface alumina inclusion giving shortest life of 97 878 cycles.

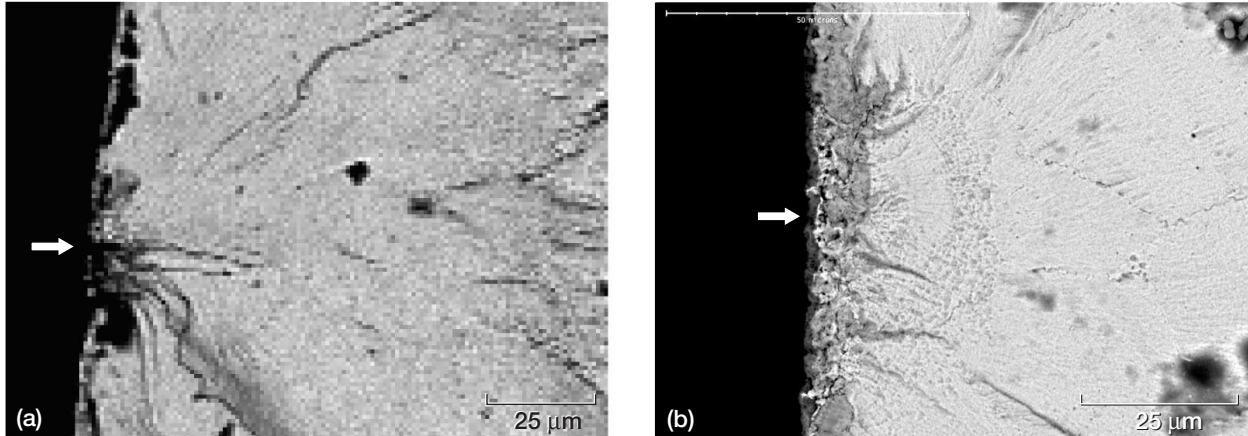


Figure 6.—Preexposed specimens failed from surface-initiated cracks. (a) After 650 °C/1029 hr giving life of 57 771 cycles. (b) After 704 °C/1029 hr giving life of 32 280 cycles.

These competing failure modes clearly accounted for the wide scatter in life of exposed specimens, as illustrated in the probability plot of figure 7. Specimens failing from internal cracks initiating at grain facets or inclusions had relatively long lives for each condition, comparable to unexposed lives. Specimens failing from cracks at the surface layer had relatively short lives and could be combined into one population. Life plotted versus depth of the failure initiation point indicated a strong correlation, as shown in figure 7. A nonlinear regression model was generated using forward stepwise regression of the factors exposure temperature, $\log(\text{time})$, depth of the failure initiation point categorized as 0 for surface and 1 for internal initiations, and their interactive terms to model fatigue life. Some cross-correlations of exposure time with depth of the failure initiation point, and exposure temperature with depth were present, which prevented inclusion of all terms in the model. This indicated that increased exposure time and temperature increased the likelihood of promoting surface-initiated failures. However, depth of the failure initiation was found to be a far better predictor of life. The resulting relationship obtained was therefore only a function of depth, but it gave a much improved R^2_{adj} of 0.628 and an rms error of 0.236 compared to the previous exposure time-based regression:

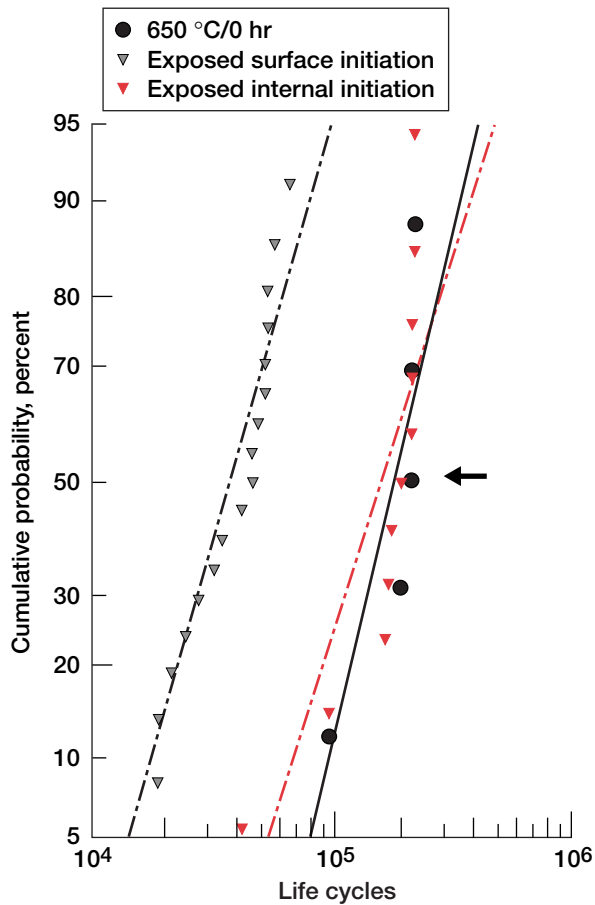


Figure 7.—Segregation of exposed specimens lives based on depth of failure initiation.

$$\log(\text{life}) = 4.5798 \text{ if depth} = \text{surface}$$

$$\log(\text{life}) = 5.2108 \text{ if depth} = \text{internal}$$

Transverse metallographic sections were prepared from representative specimens to compare the surface effects. As shown in figure 8, an oxidized surface layer predominantly made up of nickel oxide can be clearly seen in the exposed specimens. An additional zone with branched fingers of attack, rich in aluminum oxide, extended further in. The depth of the oxidized layer and the combined depth of the layer plus the attacked zone tended to increase with exposure temperature and exposure time. However, the surface oxide layer was too brittle to easily allow metallographic preparation for accurate measurements of oxide depth. Further metallographic work is underway to allow these measurements.

Verification Tests

In order to test the validity of using preexposures at the same or elevated temperatures to capture some effects of service exposures during cycles, two additional groups of tests were performed. Conventional cyclic tests were performed at 704 °C without prior exposures, in order to understand the effects of higher test temperature alone on inherent fatigue life. A cyclic dwell test was also performed at 650 °C to directly compare the effects of prior exposures to the effects of more realistic mixing of cyclic loading and exposures. The period of the cyclic dwell cycle was selected by simply dividing the longest exposure

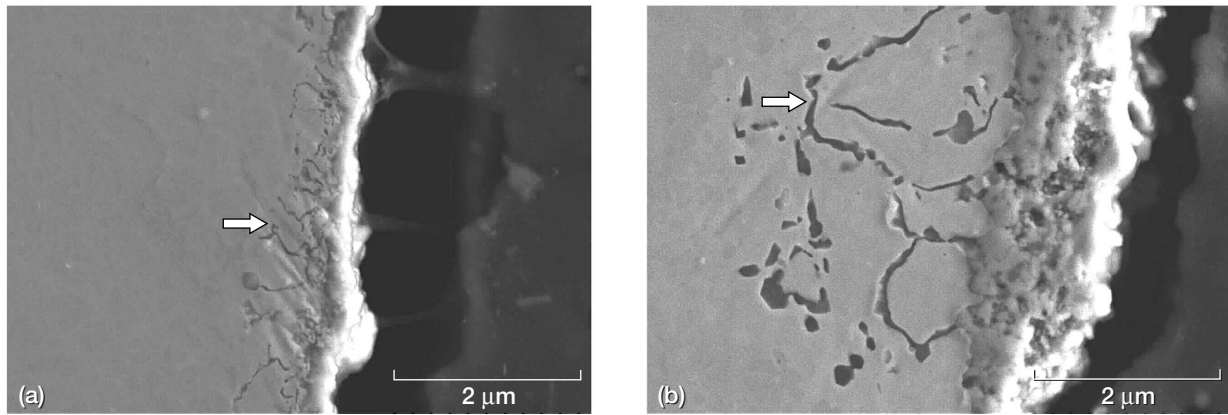


Figure 8.—Transverse metallographic sections of exposed specimens showing the environment-affected surface layer and alumina-rich fingers of attack (arrows) in exposed specimens. (a) After 650 °C/100 hr. (b) After 704 °C/1029 hr.

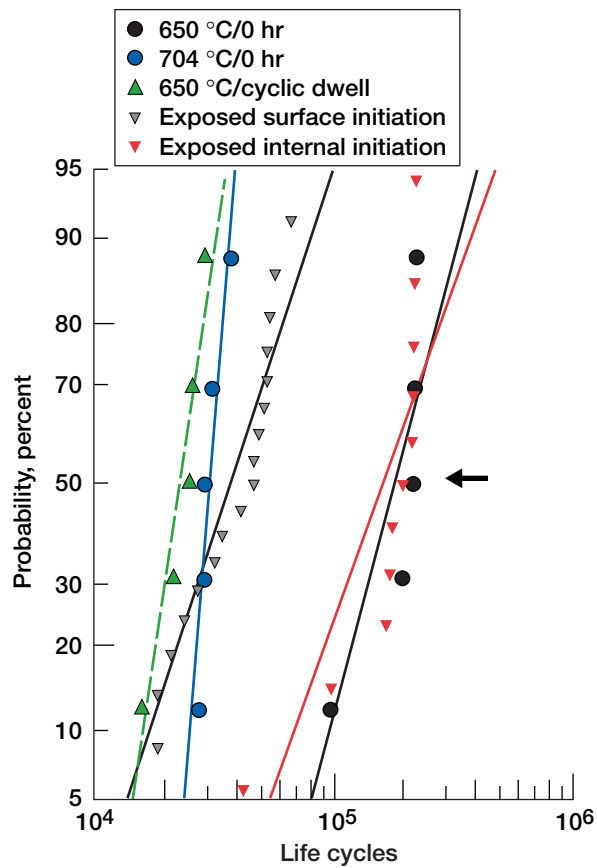


Figure 9.—Comparison of unexposed lives at 650 and 704 °C exposed lives and lives of tests at 650 °C having cyclic dwells.

time at 650 °C for 1029 hr by the observed subsequent log mean life of 64 021 cycles. This gave an overall cycle period of 1 min, as shown in figure 1. Within each cycle, a strain cycle of 0.7 percent with $R_{\epsilon} = 0$ was first applied to reproduce that of the conventional subsequent LCF tests. A dwell at zero strain was then applied to introduce exposure effects. The dwell was performed at zero strain rather than maximum strain, to prevent likely cumulative relaxation of the cyclic maximum stress from stress values of the conventional LCF tests.

The life results are compared to the previous results in the probability curves of figure 9. The unexposed 704 °C tests produced lives of 27 730 to 37 782 cycles, while the cyclic dwell tests produced lives of 16 054 to 29 204 cycles. These lives were comparable to those of exposed specimens having surface-initiated failures. Fractographic evaluations indicated the unexposed 704 °C tests and cyclic dwell tests specimens all had surface-initiated failures from the environment-affected surface layers (figs. 10 and 11).

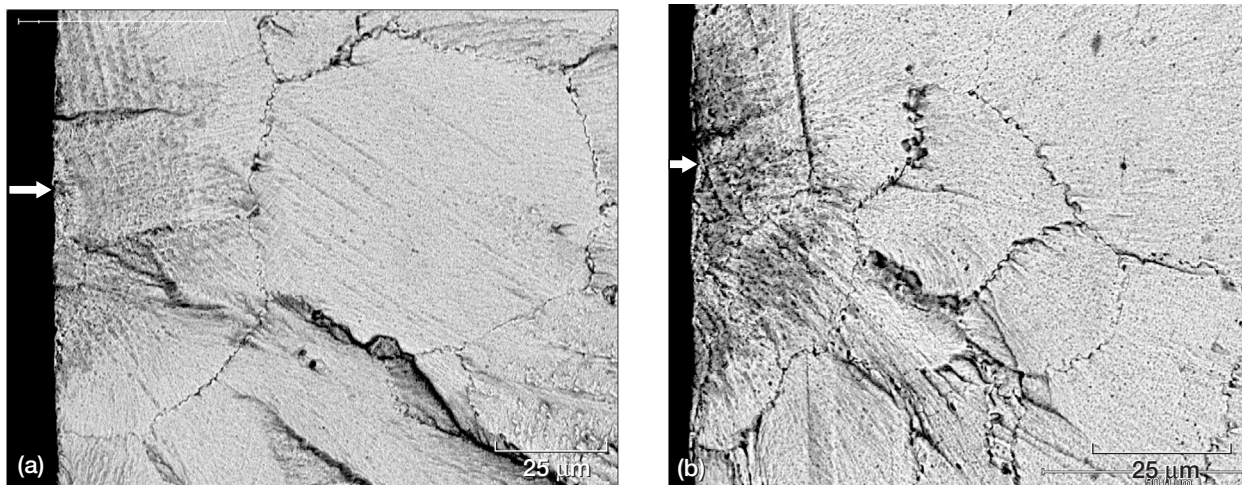


Figure 10.—Surface failure initiation sites for specimens tested at (a) 704 °C unexposed producing life of 29 333 cycles and (b) 650 °C with cyclic dwell producing life of 25 499 cycles.

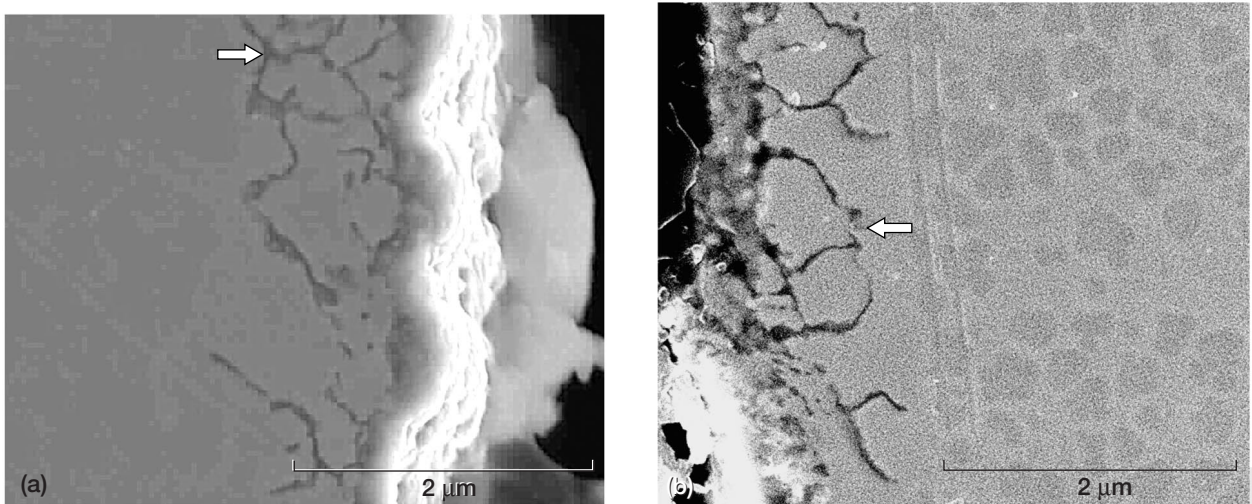


Figure 11.—Transverse metallographic sections of exposed specimens showing the environment-affected surface layer and alumina-rich fingers of attack (arrows). (a) After 704 °C unexposed LCF producing a life of 29 333 cycles. (b) After 650 °C with cyclic dwell producing life of 25 499 cycles.

Conclusions

In summary, prior exposures significantly affected fatigue life. The exposures reduced life and increased the scatter in life, compared to unexposed levels. Fractographic evaluations indicated the failure mode had shifted by the exposures from internal to surface crack initiations. The increased scatter in life was related to the competition between internal crack initiations at inclusions or large grains producing longer lives, and surface crack initiations at an environment-affected surface layer producing shorter lives. The surface crack initiations and associated shorter lives did successfully mimic that observed in more realistic cyclic dwell fatigue tests, as well as in tests at higher temperatures.

It can be concluded that prior exposures can be used to help approximate some aspects of service exposure effects. The exposures accomplish this by shifting to some degree the probable failure initiation site to the environment-affected surface layer, as in cyclic dwell tests. This produces a significantly lower life than for internally initiated failures observed in conventional low-cycle fatigue (LCF) tests. Therefore, it is necessary to screen and select sufficiently long exposure times that can induce this surface-failure initiation mode. It would then be necessary to segregate the resulting lives of exposed specimens according to the failure initiation site. The lives corresponding to surface-initiated failures can reasonably approximate cycle dwell life, at least for the cyclic dwell tests of this study. Lives corresponding to internally initiated failures should be considered separately. These internally initiated failures could in some cases approximate exposure effects associated with microstructural instabilities and defects, rather than environmental effects.

References

1. Manson, S.S.; Halford, G.R.; and Hirschberg, M.H.: Creep-Fatigue Analysis by Strain-Range Partitioning. Symposium on Design for Elevated Temperature Environment, S.Y. Zamrik, ed., American Society of Mechanical Engineers, New York, NY, 1971, pp. 12–24.
2. Ellis, J.R.; and Esztergar, E.P.: Considerations of Creep-Fatigue Interaction in Design Analysis. Symposium on Design for Elevated Temperature Environment, American Society of Mechanical Engineers, New York, NY, 1971, pp. 29–43.
3. Halford, G.R.: Low-Cycle Thermal Fatigue, NASA TM–87225, 1986.
4. Cailletaud, C., et al: A Review of Creep-Fatigue Life Prediction Methods. Seventh International Conference on Structural Mechanics in Reactor Technology—SMiRT 7, ONERA TP 1983–122, 1983, pp. 122–132.
5. Cowles, B.A., et al.: Cyclic Behavior of Turbine Disk Alloys at 650 °C. J. Eng. Mater. Technol. Trans. ASME, vol. 102, 1980, pp. 356–363.
6. Day, M.F.; and Thomas, G.B.: Analysis of the Low-Cycle Fatigue Behaviour of Two Ni-Cr-Base Alloys. Fatigue Fract. Engng. Mater. Struct., vol. 8, no. 1, 1985, pp. 33–48.
7. Hyzak, J.M.: The Effect of Defects on the Fatigue Initiation Process in Two P/M Superalloys. Air Force Wright Aeronautical Laboratories Technical Report AFWAL–TR–80–4063, 1980.
8. Antolovich, Stephen D.; Domas, Paul; and Strudel, J.L.: Low Cycle Fatigue of René 80 as Affected by Prior Exposure. Metall. Trans. A, vol. 10A, no. 12, 1979, pp. 1859–1868.
9. Furrer, D.U.: A Review of U720LI Alloy and Process Development. Mater. Des. Approach. Exper., J.-C. Zhao, M. Fahrman, and T.M. Pollock, eds., 2001, pp. 281–296.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (<i>Leave blank</i>)		2. REPORT DATE July 2002	3. REPORT TYPE AND DATES COVERED Technical Memorandum	
4. TITLE AND SUBTITLE Effects of High-Temperature Exposures on the Fatigue Life of Superalloy Udimet [®] 720			5. FUNDING NUMBERS WU-708-24-13-00	
6. AUTHOR(S) Timothy P. Gabb, Jack Telesman, Peter T. Kantzos, Joseph W. Sweeney, and Paul F. Browning				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration John H. Glenn Research Center at Lewis Field Cleveland, Ohio 44135-3191			8. PERFORMING ORGANIZATION REPORT NUMBER E-13354	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001			10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA TM-2002-211570	
11. SUPPLEMENTARY NOTES Prepared for the 131st Annual Meeting and Exhibition sponsored by the Minerals, Metals, and Materials Society, Seattle, Washington, February 17-21, 2002. Timothy P. Gabb and Jack Telesman, NASA Glenn Research Center; Peter T. Kantzos, Ohio Aerospace Institute, Brook Park, Ohio; Joseph W. Sweeney, Akima Corporation, Cleveland, Ohio; and Paul F. Browning, Solar Turbines, Inc., San Diego, California. Responsible person, Timothy P. Gabb, organization code 5120, 216-433-3272.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category: 07 Available electronically at http://gltrs.grc.nasa.gov/GLTRS This publication is available from the NASA Center for AeroSpace Information, 301-621-0390.			12b. DISTRIBUTION CODE	
13. ABSTRACT (<i>Maximum 200 words</i>) The purpose of this study was to examine the effects of extended exposures on the near-surface fatigue resistance of a disk superalloy. Powder metallurgy processed, supersolvus heat-treated Udimet [®] 720 (U720) fatigue specimens were exposed in air at temperatures from 650 to 705 °C, for 100 hr to over 1000 hr. They were then tested using conventional fatigue tests at 650 °C, to determine the effects of exposure on fatigue resistance. The exposures reduced life by up to a factor of 8 and increased the scatter in life, compared to unexposed levels. Fractographic evaluations indicated the failure mode was shifted by the exposures from internal to surface crack initiations. The increased scatter in life was related to the competition between internal crack initiations at inclusions or large grains producing longer lives, and surface crack initiations at an environmentally affected surface layer producing shorter lives.				
14. SUBJECT TERMS Gas turbine engines; Rotating disks; Heat resistant; Alloys; Fatigue; Materials			15. NUMBER OF PAGES 16	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT	