

High Purity Hydrogen from Coal-Derived Syngas

Jim Torkelson, Neng Ye, Zhijiang Li and Mark Fokema
Aspen Products Group, Inc.

May 15, 2007

Project ID: PDP 21

Overview

Timeline

- Start: June 2005
- End: May 2008
- 75% Complete

Budget

- Total project funding
 - DOE: \$498k
 - Contractor: \$125k
- Funding received in FY06
 - \$231k
- Funding for FY07
 - \$201k

Barriers

- Hydrogen from Coal – Research, Development & Demonstration Program
 - WGS Reaction Barriers
 - D. Impurity Intolerance/Catalyst Durability
 - Hydrogen Separation Barriers
 - I. Poisoning of Catalytic Surfaces
 - Q. Impurities in Hydrogen from Coal



Overall Goal

Develop water gas shift (WGS) membrane reactor that cost-effectively produce pure hydrogen from coal-derived synthesis gas containing significant amounts of hydrogen sulfide and hydrogen chloride

- Replaces multiple process units (contaminant removal, high temperature shift, low temperature shift, pressure swing adsorption) with single catalytic membrane reactor
- High process efficiency realized by improving hydrogen yield at low steam to carbon ratios
- Produces high-pressure CO₂-rich stream potentially suitable for sequestration



Objectives

- Develop sulfur- and chloride-tolerant, highly active WGS catalyst that is able to operate at low steam to carbon ratios
- Develop low-cost, contaminant-tolerant H₂-selective membrane
- Demonstrate an integrated WGS membrane reactor operating on simulated coal-derived syngas
- Analyze cost benefits of the demonstrated WGS membrane reactor technology



Approach

Develop water gas shift catalyst and H₂-selective membrane that both operate at 300-500°C, at 300-500 psig and are tolerant of high concentrations of H₂S and HCl

Catalyst

- MoS₂-based catalyst with modifiers to promote impurity tolerance


Membrane

- Dense Ta-based membrane with surface modifications to promote H₂ dissociation/association reactions in the presence of S and Cl



WGS Catalyst Development

60% CO, 25% H₂, 10% CO₂, 5% N₂, 3000 ppm H₂S, H₂O/CO=4, 400 psig, GHSV=3000 h⁻¹

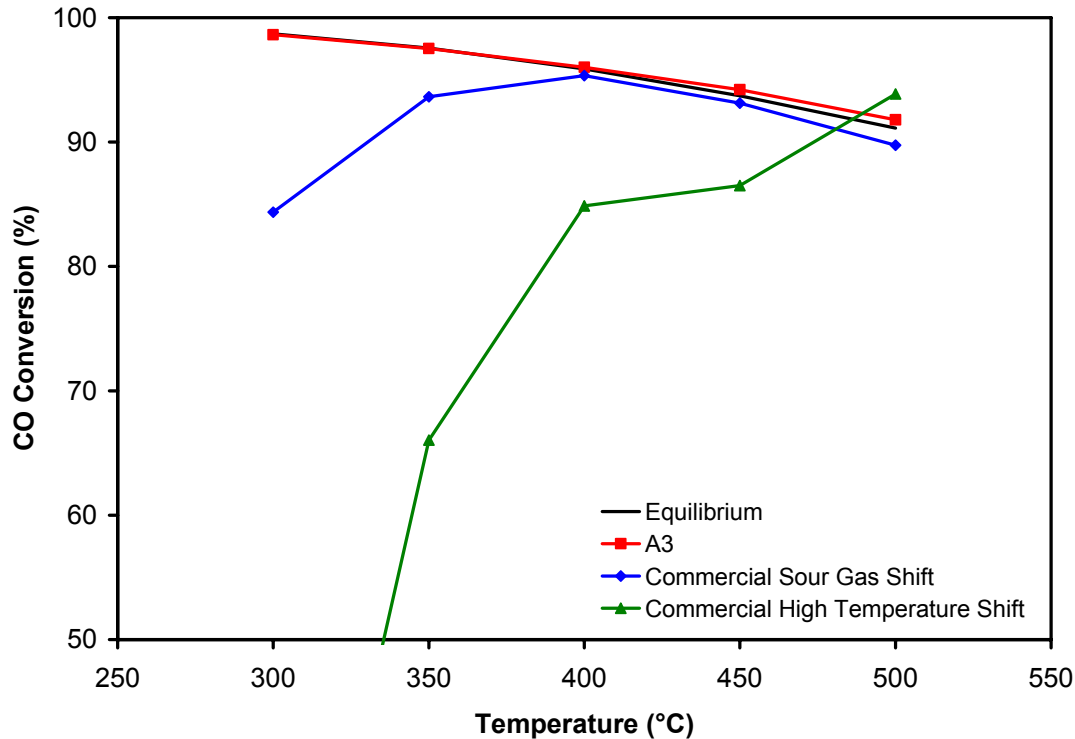


- Equilibrium yields realized with catalyst A3 at 300-500°C
- Tolerant to 3000 ppm_v (dry gas) H₂S



WGS Catalyst Stability


Catalyst A3, 60% CO, 25% H₂, 10% CO₂, 5% N₂, H₂O/CO=4, 400°C, 400 psig, GHSV=3000 h⁻¹

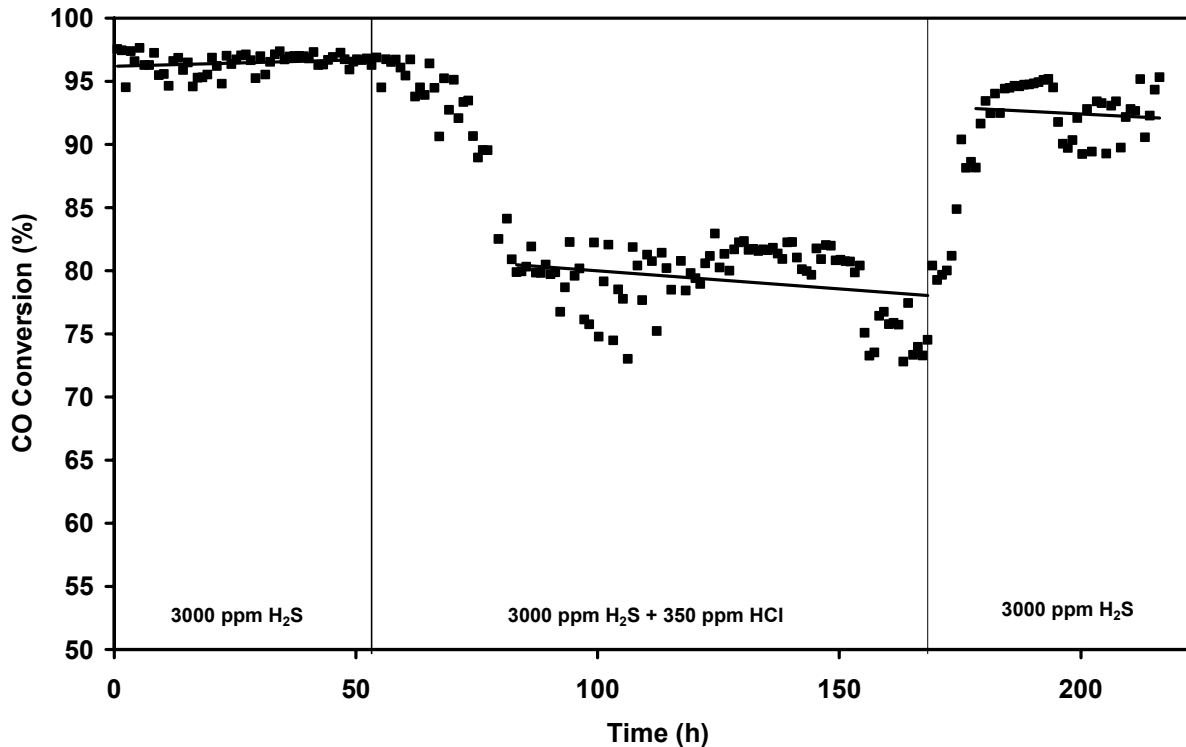

- Stable in the presence of 3000 ppm_v (dry gas) H₂S
- Mild reversible deactivation with 350 ppm_v (dry gas) HCl




Membrane Design

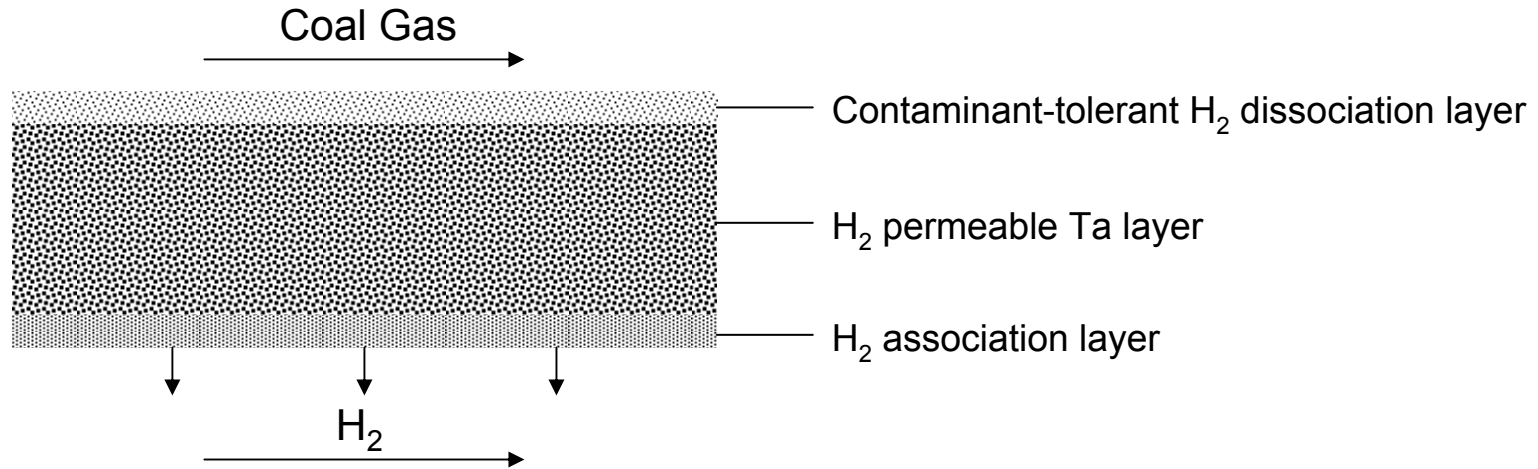

- Developed substrate cleaning and coating technique
- Examined effects of substrate thickness, coating composition, coating thickness and annealing conditions on pure H₂ permeability
- Examined effects of H₂O, H₂S, CO, and CO₂ on membrane performance



Membrane H₂ Permeability

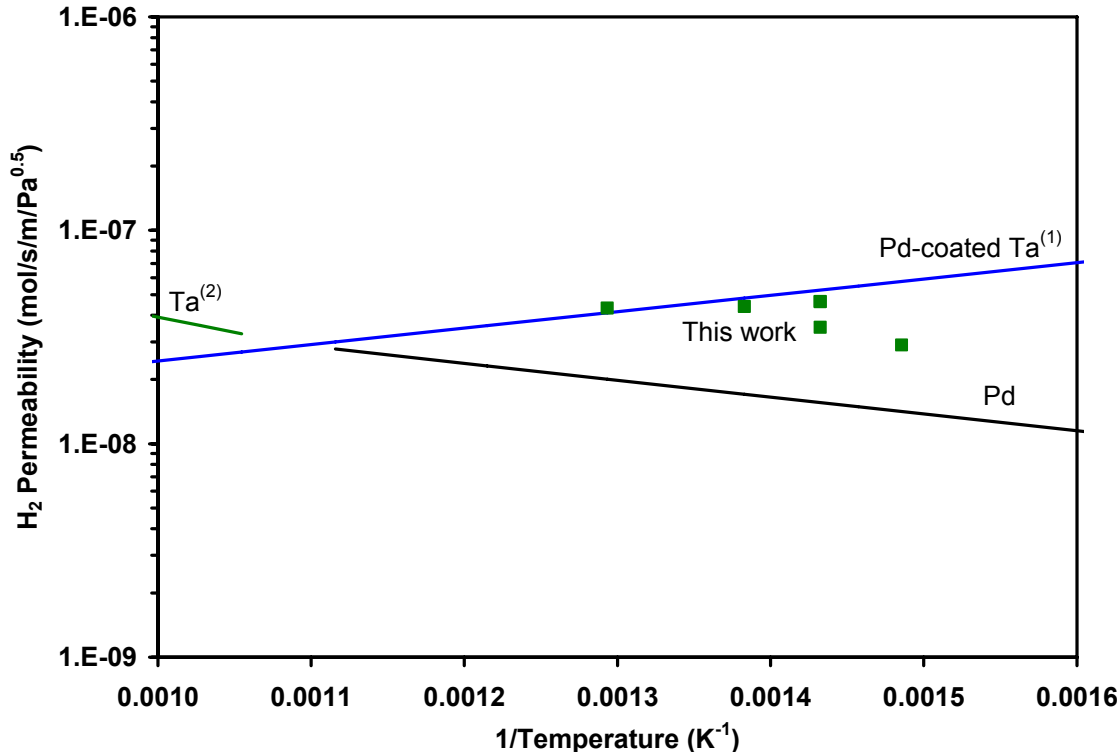


Test Conditions
95% H₂ – 5% He
350-550°C
200 psig H₂

- H₂ permeability greater than dense Pd-based membranes
- High selectivity → H₂ purity >99.9%
- Good mechanical strength - tested up to 550°C & 400 psi



Membrane Sulfur Tolerance

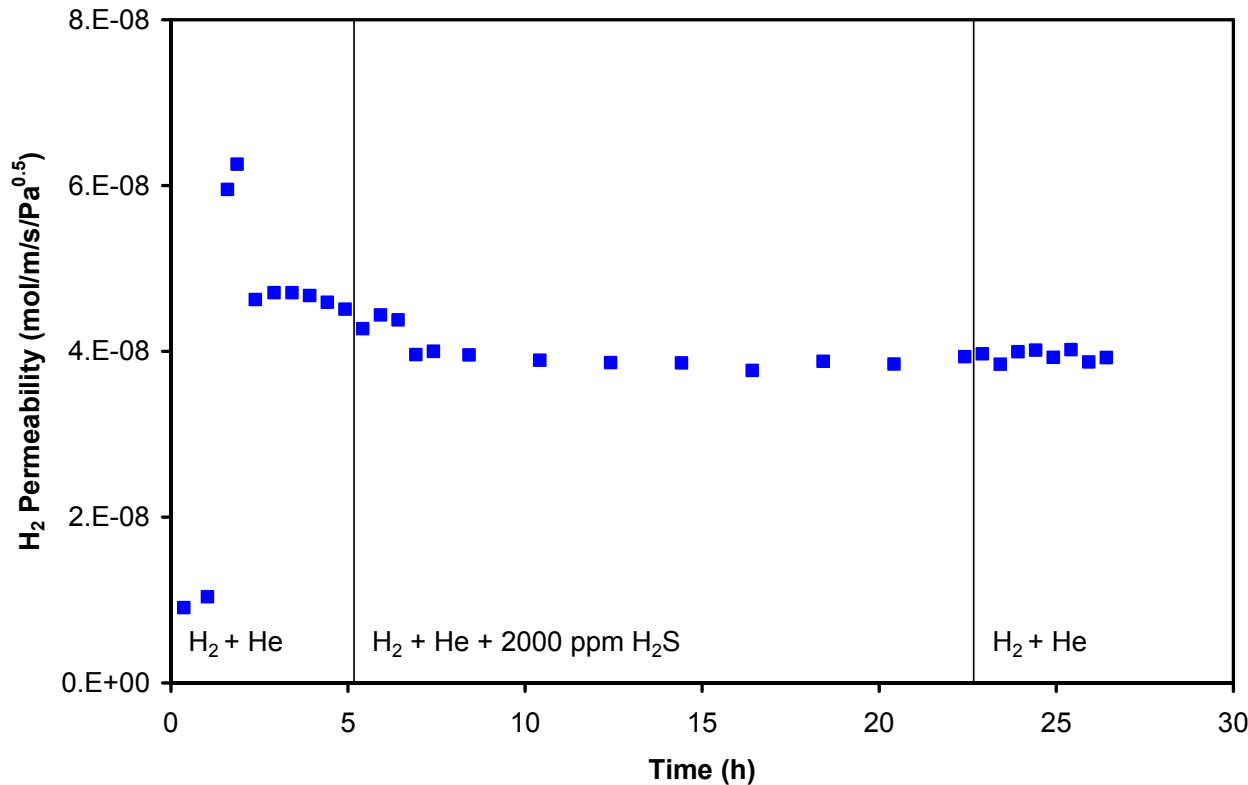

Test Conditions

425°C


150 psig H₂

- Membrane tolerant of high concentration of H₂S
- 14% reduction in permeability upon exposure to 2000 ppm H₂S



ASPEN PRODUCTS GROUP, INC.

Membrane Moisture Tolerance

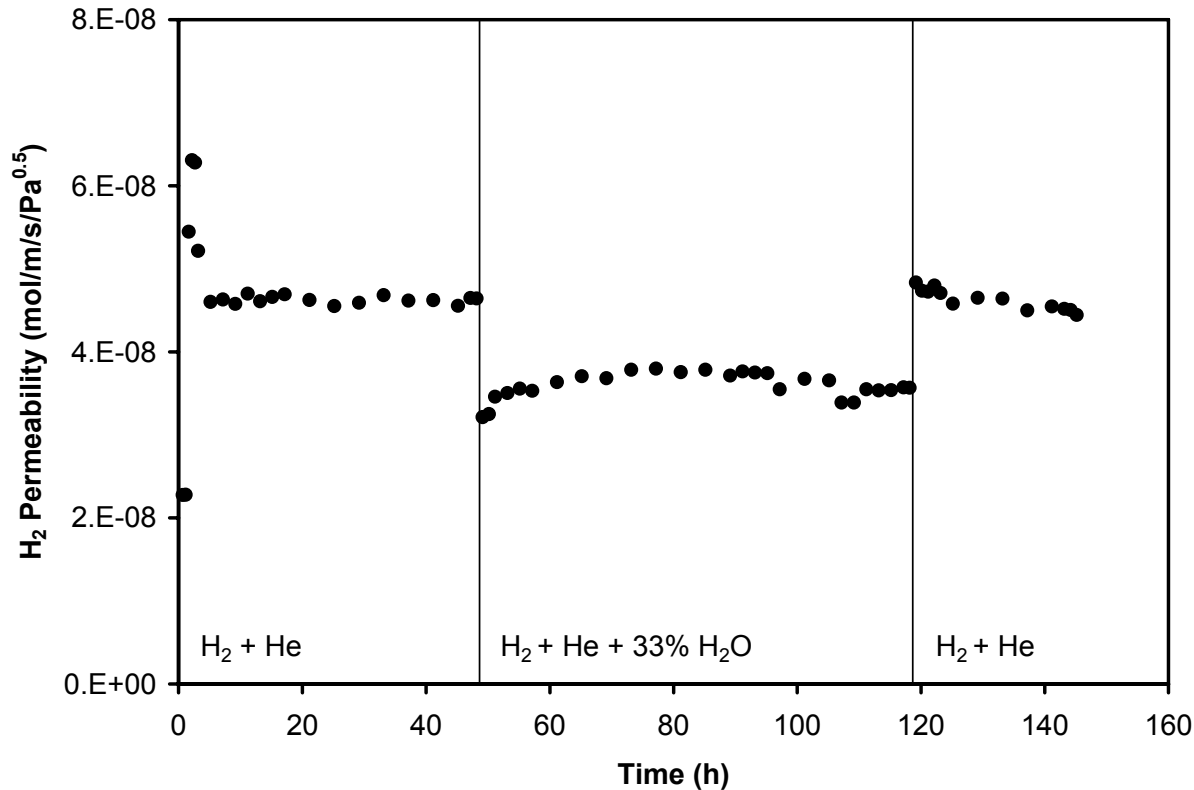

Test Conditions

425°C

150 psig H₂

- Membrane tolerant of high concentration of steam
- 22% reduction in permeability upon exposure to 33% H₂O



ASPEN PRODUCTS GROUP, INC.

Future Work

FY 2007

- Quantify performance and stability of membrane in contaminant-laden syngas
- Examine membrane microstructure in order to relate permeability to structure and synthetic parameters
- Fabricate and demonstrate integrated water gas shift membrane reactor

FY 2008

- Conduct cost analysis



Summary

Water Gas Shift

- Contaminant-tolerant water gas shift catalyst development and testing completed
- Equilibrium yields demonstrated at practical operating conditions
- Catalyst maintains high activity over wide temperature range (300-500°C)
- Excellent catalyst durability in the presence of 3000 ppm H₂S and 350 ppm HCl observed over 220 hours

H₂-Permeable Membrane

- Dense metal membranes with high H₂ permeability and H₂ selectivity demonstrated
- Membrane H₂ permeability greater than that of Pd-based membranes
- Membrane maintains high permeability in the presence of 2000 ppm H₂S and 33% H₂O



Hydrogen From Coal Program Goals

Water Gas Shift Catalyst

Performance Criteria	Current Status	Targets		This Work
		2010	2015	
Catalyst Form	Pellets	Advanced configurations – TBD		Pellets
Active Metal	Cu/Zn or Fe/Cr or Co/Mo	Advanced configurations – TBD		Mo
Feed Temperature (°C)	200-300	>250	>400	>250
Feed Pressure (psia)	450-1150	>450	>750	415
Approach to Equilibrium (°C)	8-10	<6	<4	<4
Min. H ₂ O/CO Ratio	2.6	<2.6	<2	<2
Sulfur Tolerance (ppm _v)	varies	>20	>100	3000
COS Conversion	varies	Partial	Total	-
Chloride Tolerance (ppm _v)	varies	>3	>100	350
Durability (y)	3-7	>7	>10	-
Catalyst Cost (\$/lb)	~5	<5	<5	-

From “2006 Hydrogen from Coal Program RD&D Plan”

Hydrogen From Coal Program Goals

Hydrogen Separation

Performance Criteria	Current Status			Targets			This Work
	Microporous	Cermet	Dense Ceramic	2007	2010	2015	
Flux (scfh/ft ²)	20-100	~300	2	100	200	300	20
Temperature (°C)	300-600	300-400	900	400-700	300-600	250-500	350-550
S Tolerance (ppm _v)	Yes	~20	-	-	20	>100	2000
Cost (\$/ft ²)	150-200	<200	-	150	100	<100	-
WGS Activity	No	-	-	Yes	Yes	Yes	Yes
ΔP Capability (psig)	100	1000	-	100	400	800	400
CO Tolerance	Yes	Yes	-	Yes	Yes	Yes	-
H ₂ Purity (%)	90-98	>99.999	-	95	99.5	99.99	>99.9
Durability (y)	-	0.9	-	1	3	5	-

From “2005 Hydrogen from Coal Program RD&D Plan” & “2006 Hydrogen from Coal Program RD&D Plan”

Acknowledgement

This material is based upon work supported by the Department of Energy under Award Number DE-FC26-05NT42452.

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

