


NASA/TM-2005-213165



Photometric Evaluation of Photo-luminescent Materials for Multi-Egress Guidance Placards

Lighting Environment Test Facility

*James C. Maida
Johnson Space Center*

Report Prepared by
*Charles K. Bowen
Johnson Engineering, Houston*

*Charles D. Wheelwright
Johnson Engineering, Houston*

Lyndon B. Johnson Space Center Houston, Texas

August 2005

The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the lead center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers, but having less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.


- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or co-sponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized databases, organizing and publishing research results ... even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA STI Help Desk at (301) 621-0134
- Telephone the NASA STI Help Desk at (301) 621-0390
- Write to:
NASA STI Help Desk
NASA Center for AeroSpace Information
7121 Standard Drive
Hanover, MD 21076-1320

NASA/TM-2005-213165



Photometric Evaluation of Photo-luminescent Materials for Multi-Egress Guidance Placards

Lighting Environment Test Facility

James C. Maida / SF5 / NASA James.maida@jsc.nasa.gov

Report Prepared by

Charles K. Bowen / SF5 / Johnson Engineering

charles.k.bowen1@jsc.nasa.gov

Charles D. Wheelwright / SF5 / Johnson Engineering

charles.d.wheelwright1@jsc.nasa.gov

National Aeronautics and
Space Administration

Johnson Space Center
Houston, Texas 77058-3696

August 2005

Available from:

NASA Center for AeroSpace Information
7121 Standard Drive
Hanover, MD 21076-1320

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161

This report is also available in electronic form at <http://ston.jsc.nasa.gov/collections/TRS>

Background	1
Experimental Conditions and Apparatus	1
Experimental Procedure	2
Results	4
Discussion	7
Acknowledgements	8
Reference.....	8

Background

The purpose of this investigation was to evaluate several photo luminescent (PL) materials being considered for construction of emergency egress placards in the International Space Station (ISS). The use of PL material is intended to allow the placards to be read by ISS crew members in the event of an extensive power failure resulting in the loss of interior illumination.

Several PL materials were included in the study. These fell into two general categories: paints or plastic/plastic laminate sheeting. In each case, the PL material was intended to be used as a luminous substrate over which the placard symbols would be printed in contrasting, opaque ink, allowing the placard information to be read in all illumination conditions. Two colors of paint and five plastic materials were considered. The plastic materials were taken from samples provided by the manufacturer, Luna Technologies, International, Inc. Two paint samples were obtained from the Johnson Engineering Decal Design Production Facility (DDPF). Each sample consisted of a thin sheet of plastic coated with a uniform layer of PL paint. One sample was of a blue color manufactured by Nichia Corporation, and the other was of a yellow-green color manufactured by Wilflex Incorporated.

The five plastic material samples were identified as follows:

Lunaplast card – stiff, laminated 0.063 inch thick structure, having a white reflective layer on the back;

Lunaplast flex – thin, pliant, laminated 0.017 inch thick structure, having a white reflective layer on the back;

Lunaplast acrylic low load – stiff, translucent, homogeneous 0.125 inch thick sheet;

Lunaplast acrylic medium load – stiff, translucent, homogeneous 0.125 inch thick sheet;

Lunaplast polycarbonate – stiff, opaque, extruded 0.10 inch thick with a curved cross-section and textured surface;

All of these PL plastic materials glow with a yellow-green color.

Illumination sources used to excite the materials in the study included fluorescent General Lighting Assembly (GLA) and prototype Solid State Lighting (SSL) luminaires. The sources used were selected to have characteristics most closely resembling those of the luminaires aboard present and future ISS modules.

Experimental Conditions and Apparatus

The experiments were performed in the Lighting Environments Test Facility (LETF). Instruments used included a Photo Research Model PR-1500 luminance meter for measuring the brightness of the samples following excitation and a Photo Research Model 504 illuminance meter for monitoring the illumination falling on each sample during excitation.

Sources of illumination for the experiment included overhead fluorescent luminaires in the LETF, “flight-like” GLA training luminaires, and a prototype SSL luminaire. During the initial screening experiment, the samples were illuminated to approximately 15 foot-candles (fc) by the overhead fluorescent lights in the LETF. Subsequent experiments on the reduced sample set were performed with 10.5fc illumination on the sample provided by the GLA or SSL as indicated.

Experimental Procedure

Sample preparation. The PL materials were cut into two sets of approximately 1.5 by 2.0 inch rectangular samples. Self-adhesive Velcro® tape patches were applied to the backs of all samples to hold them in position during tests, and identifying marks were placed on the samples that were similar in appearance. All samples were stored in the dark for at least 36 hours prior to testing.

Screening evaluation. To streamline the experimentation, a preliminary subjective evaluation was performed on all of the samples to eliminate obviously inferior materials from subsequent objective testing. This evaluation was performed following simultaneous illumination of all samples under overhead fluorescent lights for 30 minutes. The lights were switched off, and the apparent brightness of the samples was observed for a period of about 15 minutes.


Following the period of observation, one material was eliminated from further study. The Nichia blue PL paint sample initially seemed dim compared with all the others, but appeared to maintain its luminance over the time of observation. This impression may have been an accurate estimate of the relative brightness of the blue paint, but it was likely in part to have been influenced by the gradual dark adaptation of the observer. In any case, the blue paint sample was the dimmest of all initially, and so it was eliminated.

Objective testing procedure. Samples of the six remaining materials were wrapped in black velvet and stored in a dark cabinet for 36 hours prior to further testing. In turn, these samples were then individually exposed to 10.5fc illumination from the prototype SSL luminaire for a 10-second period. Luminance measurements were made and recorded for the sample at 10 seconds and 60 seconds after the end of the exposure period. After the second data recording was completed, the sample was exposed to an additional 600 seconds of the same illumination, followed by luminance measurements at the same sampling intervals. This pattern was repeated for the balance of the samples, and then the samples were returned to dark storage for about 48 hours prior to further testing.

Upon reviewing the brightness of the materials following SSL illumination, the experimenters eliminated the extruded Lunaplast polycarbonate sample from further consideration due to its low luminance in comparison to the other materials. In addition, since the Lunaplast acrylic low load material afforded no performance advantage in initial

brightness or brightness decay over the similar Lunaplast acrylic medium load material, it too was eliminated.

The remaining four materials were tested under GLA illumination using the same procedure as previously described. Illumination of the sample under test was initially set to 10.5fc after the GLA had warmed up for more than 10 minutes. The GLA was turned off long enough to check the luminance meter calibration and to place the sample in position for the test. At the beginning of testing, the experimenters noted a reddish color from the GLA during the onset of both the initial 10-second and the subsequent 60-second exposure period for each sample. Following the GLA test session, the samples were returned to dark storage, and measurements were made of the visible spectrum of light emitted by a “cold” GLA as it warmed up. The significant changes in the spectrum during the first five minutes of operation prompted questioning of the results obtained following the 600-second illumination of the samples (Figure 1). The experimenters reasoned that the 10-second illumination results could be considered valid, since they were indicative of a realistic short-term illumination circumstance that might result from a power failure immediately following turning on the lights in a module of the ISS. The 600-second illumination results, however, were deemed a less realistic representation of the results of a power failure following long-term steady state illumination of the GLAs. For this reason, the 600-second measurements were repeated with a change in procedure. Under the revised protocol, the GLA was allowed to operate for at least ten minutes prior to the exposure of each sample. Then the 600-second illumination period was followed by measurements as previously described.

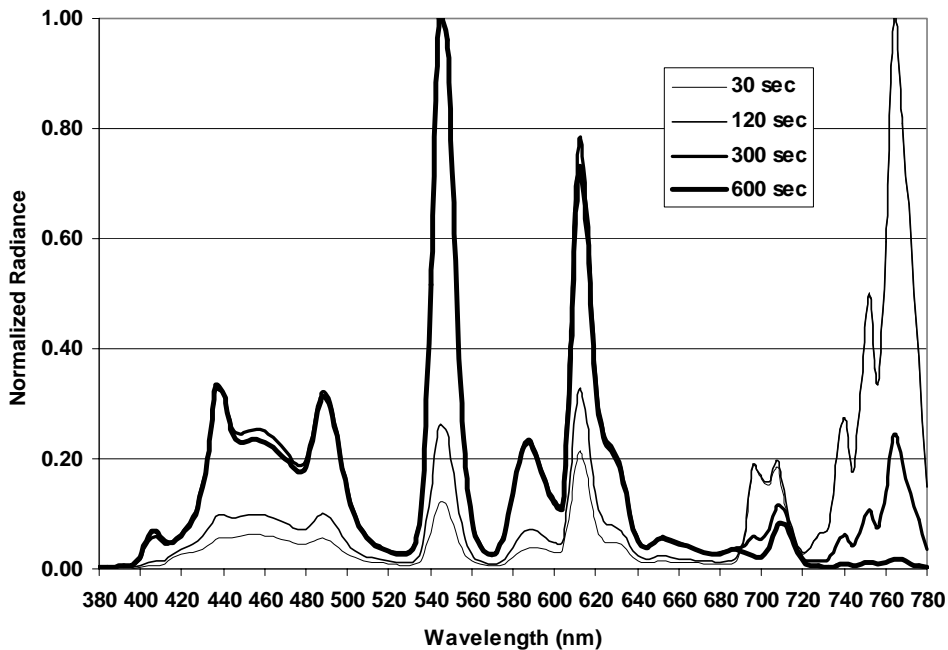

Results

10-second excitation. In the case of short-term excitation by fluorescent GLA, the luminance of all materials was quite low, 0.005 foot Lambert or less, with the Wilflex paint the brightest (Figure 2). With short-term excitation by the SSL, the Lunaplast flex material outperformed the others, providing about three times the brightness of the Wilflex paint illuminated by the GLA (Figure 3). Luminance decay rates were greatest for the Lunaplast flex material and the Wilflex paint samples.

600-second excitation. With long-term GLA excitation, the brightness of the Lunaplast flex material increased about thirty-fold over the short-term GLA excitation result, whereas the Wilflex paint brightness increased by a ratio of only 4:1 (Figure 4). The three plastic materials afforded luminances exceeding 0.075fL during the first minute following cessation of excitation — roughly seven times the luminance afforded by the Wilflex paint.

There was little difference in the luminance of the Wilflex paint sample during the minute following long-term exposure to light from the GLA or the SSL. The brightness of all three plastic materials exceeded that of the Wilflex paint by a factor from 4:1 to 7:1, depending on the type of excitation source. The GLA excitation produced higher luminance from the plastic materials than did the SSL excitation (Figure 5).

Luminance decay rates for the plastic materials were nearly identical, regardless of the type of excitation source. The Wilflex paint's luminance decay rate was somewhat greater than that of the plastic materials.

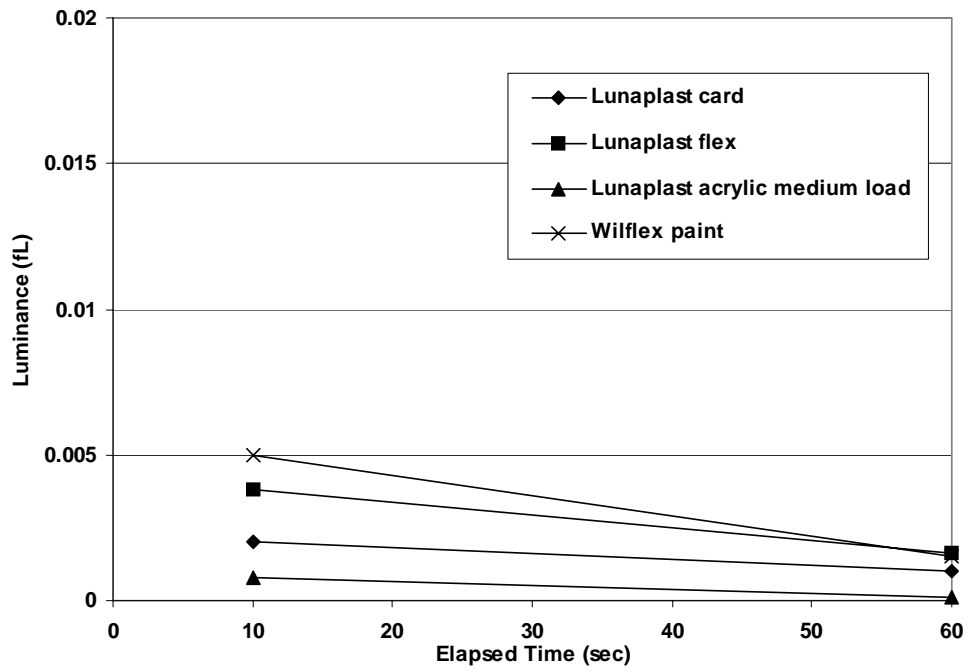


Figure 2. Photoluminescence for 10-second GLA excitation

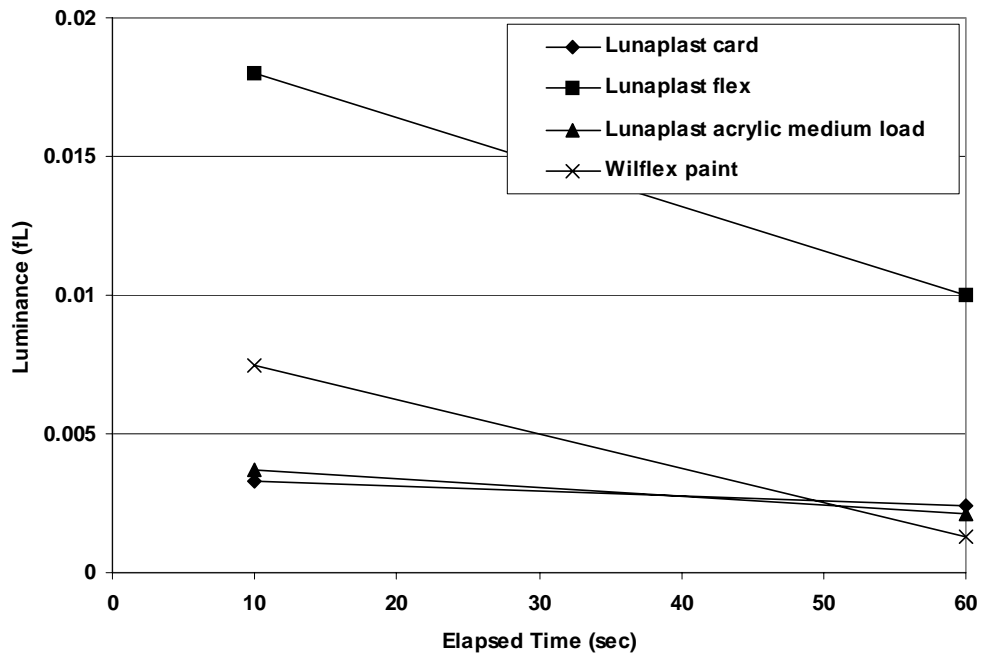


Figure 3. Photoluminescence for 10-second SSL excitation

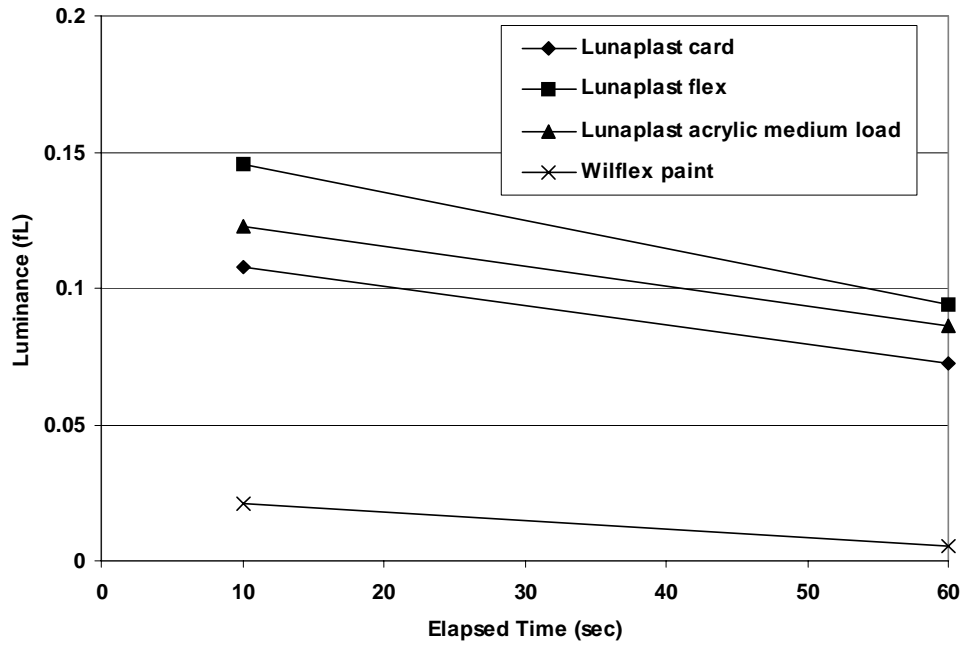


Figure 4. Photoluminescence for 600-second fluorescent GLA excitation

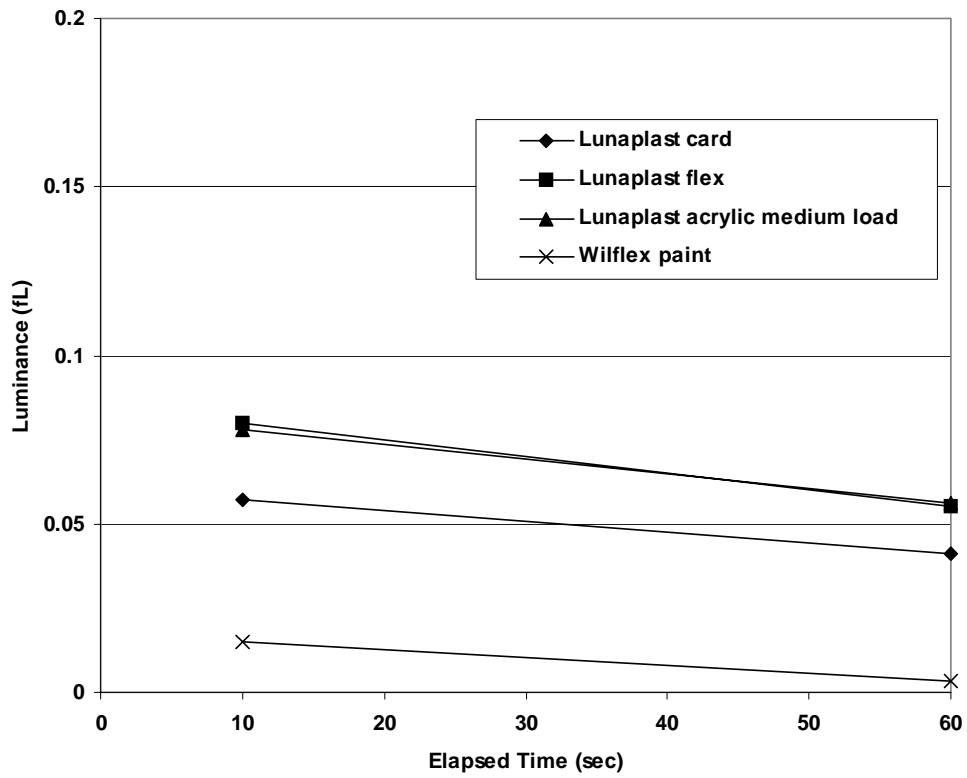


Figure 5. Photoluminescence for 600-second SSL excitation

Discussion

Material characteristics. Of the final four materials studied in the experiment, the brightness and endurance of the Wilflex paint proved inferior to that of the plastic materials. Among the plastics, the Lunaplast flex material offered the best performance overall, with the degree of superiority dependent on the type of excitation illuminant. After having been fully excited, all three plastic materials are bright enough for use in emergency egress placards.

All three plastic materials responded more strongly to long-term GLA excitation, compared to long-term SSL excitation. Differences between this pattern and some short-term results may probably be explained in terms of changes in the spectrum of light emitted by the GLA as it is warming up. Initially, the GLA emits very long wavelength (red) light, which decreases as short (blue) and middle (yellow, green) visible wavelengths increase with time (Figure 1). The spectrum of the SSL, in contrast, is stable from the time it is turned on, with most of its energy concentrated in the short (visible blue) wavelengths (Figure 6). It is likely that during the first half minute of operation the SSL produces considerably more total light energy than does the GLA, and that the PL material used in the plastics is much more sensitive to illumination at shorter visible wavelengths. The manufacturer's specifications for the Lunaplast materials indicate that the wavelength range for excitation includes the range of 200nm to 450nm, with the optimum at 360nm, in the band near the (violet) limit of the visible range.

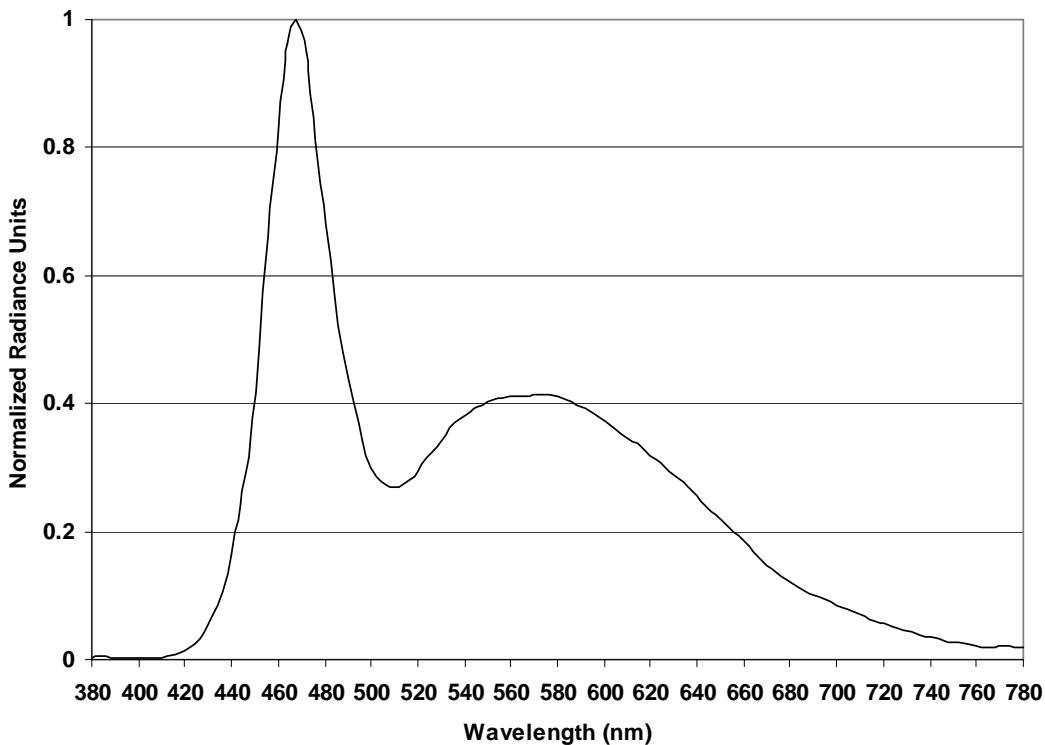


Figure 6. Normalized spectral characteristics of SSL

Thinner materials (Wilflex paint, Lunaplast flex) appeared to be more readily excited under the short-term illumination condition. This may be due to reduced attenuation and scattering of the light as it propagates within the material. The Lunaplast acrylic medium load material might benefit from having the active PL component suspended in a thinner layer of plastic. The addition of a reflective white backing to the Lunaplast acrylic medium load material to capture more of the excitation photons that pass through the plastic without encountering the active PL chemical might improve its “charging” efficiency.

The color of the light emitted by the PL material following illumination should ideally be chosen to correspond to the viewer’s most sensitive wavelength range, considering whether the viewer is light- or dark-adapted. As the human eye adjusts from photopic (cone) to scotopic (rod) receptor dominance, the peak sensitivity in response to color moves from the yellow-green wavelengths of the visible spectrum to the blue-green wavelengths, a phenomenon known as the Purkinje shift (Sekular & Blake, p. 90). In the case of the initial subjective evaluation by a light-adapted viewer, the Purkinje shift probably tended to offset the decrease in actual light production by the Nichia blue PL paint over time. To a light-adapted viewer immediately following the loss of ambient illumination, the yellow-green light emitted by the plastic PL materials in the study should initially appear brighter than equivalent intensity light from blue-emitting PL material.

Acknowledgements

The experimenters owe Danny Wells and Mike Miley of the Product Development Department supporting the Advanced Engineering Department of Lockheed-Martin a debt of thanks for their providing the prototype SSL and technical assistance during the evaluations.

Reference

Sekuler, Robert and Randolph Blake (1990) Perception (2nd ed.). New York: McGraw-Hill.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave Blank)	2. REPORT DATE August 2005	3. REPORT TYPE AND DATES COVERED NASA Technical Memorandum		
4. TITLE AND SUBTITLE Photometric Evaluation of Photo-luminescent Materials for Multi-Egress Guidance Placards.			5. FUNDING NUMBERS	
6. AUTHOR(S) James C. Maida				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Lyndon B. Johnson Space Center Houston, Texas 77058			8. PERFORMING ORGANIZATION REPORT NUMBERS S-963	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001			10. SPONSORING/MONITORING AGENCY REPORT NUMBER TM-2005-213165	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Available from the NASA Center for AeroSpace Information (CASI) 7121 Standard Hanover, MD 21076-1320 Category: 23-3			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The purpose of this investigation was to evaluate several photo luminescent (PL) materials being considered for construction of emergency egress placards in the International Space Station (ISS). The use of PL material is intended to allow the placards to be read by ISS crew members in the event of an extensive power failure resulting in the loss of interior illumination.				
14. SUBJECT TERMS Materials science, plastics, luminescence,			15. NUMBER OF PAGES 18	16. PRICE CODE
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT Unlimited	
