

**SANS AND SAXS STUDY ON AQUEOUS MIXTURES OF FULLERENE-
BASED STAR IONOMERS AND SODIUM DODECYL SULFATE**

by

U. Jeng, W. -J. Liua, and T. -L. Lin

**Department of Engineering and System Science
National Tsing Hua University
Hsinchu 30043 Taiwan**

and

C. -S. Tsao

**Division of Nuclear Fuel and Materials
Institute of Nuclear Energy Research
Lungtan 325 Taiwan**

and

T. Canteenwala and L. Y. Chiang

**Center for Condensed Matter Sciences
National Taiwan University
Taipei 106, Taiwan**

and

L.P. Sung and C. C. Han

**National Institute of Standards and Technology
Gaithersburg, MD 20899-8621 USA**

Reprinted from the *Physica A: Statistical Mechanics and its Applications*, Volume 304, 191, 2002.

NOTE: This paper is a contribution of the National Institute of Standards and Technology and is not subject to copyright.

NIST

National Institute of Standards and Technology
Technology Administration, U.S. Department of Commerce



ELSEVIER

Physica A 304 (2002) 191–201

PHYSICA A

www.elsevier.com/locate/physa

SANS and SAXS study on aqueous mixtures of fullerene-based star ionomers and sodium dodecyl sulfate

U. Jeng^a, T.-L. Lin^{a, *}, W.-J. Liu^a, C.-S. Tsao^b, T. Canteenwala^c,
L.Y. Chiang^c, L.P. Sung^d, C.C. Han^d

^aDepartment of Engineering and System Science, National Tsing Hua University,
Hsinchu 30043, Taiwan

^bDivision of Nuclear Fuel and Materials, Institute of Nuclear Energy Research, Lungtan 325, Taiwan

^cCenter for Condensed Matter Sciences, National Taiwan University, Taipei 10617, Taiwan

^dNational Institute of Standards and Technology, Gaithersburg, MD 02899, USA

Abstract

Fullerene-based star ionomer $C_{60}[\text{CO}(\text{CH}_2)_5\text{O}(\text{CH}_2)_4\text{SO}_3\text{Na}]_6$ (FC₁₀S), with six sodium-dodecyl-sulfate-like arms randomly bonded on the fullerene, has been synthesized. This novel molecule has a high water solubility and a structural shape resembling the skeleton of a micelle of sodium dodecyl sulfate (SDS). We study aqueous mixtures of the C₆₀-based ionomers and SDS using small angle neutron scattering (SANS) and small angle X-ray scattering (SAXS). With a selected deuteration of SDS, we have identified the formation of complex aggregates of FC₁₀S with SDS in the mixtures. The structural information of the complex aggregates is extracted from the SANS and SAXS data measured for the mixtures. On the average, the complex aggregates observed have a cylinder-like shape with a radius of 19 Å and a length of ≈100 Å for the sample mixtures containing 2.3 or 1.2 mM of FC₁₀S and 6 mM of SDS. The mean aggregation numbers of FC₁₀S and SDS in each complex aggregate are 15 and 11, respectively. © 2002 Elsevier Science B.V. All rights reserved.

Keywords: SANS; SAXS; Fullerene-derived ionomers; Aggregation structure

1. Introduction

Recently, we have synthesized fullerene-based ionomers $C_{60}[(\text{CH}_2)_4\text{SO}_3\text{Na}]_6$ (FC₄S) for potential biomedical applications such as free radical scavenging or antioxidant-action

* Corresponding author. Fax: +886-3-5728445.

E-mail address: tllin@mx.nthu.edu.tw (T.-L. Lin).




Fig. 1. Schematic view of a fullerene-based star ionomer FC₁₀S.

facilitating [1,2]. With the six sulfobutyl arms randomly bounded on the C₆₀ cage, the star-like FC₄S has high water solubility. In our previous studies, using SANS and SAXS, we found that FC₄S formed globular aggregates of a nano-scale size in aqueous solutions [3,4]. In a continued study for the effect of arm-length on aggregation behaviors, the six sulfobutyl arms of FC₄S were extended to a length similar to SDS. The long-arm fullerene-based ionomers, C₆₀[CO(CH₂)₅O(CH₂)₄SO₃Na]₆ (FC₁₀S) were found to form rod-like aggregates in water solutions, with a much larger aggregation number (more than four folds) and stronger interparticle interactions than that for FC₄S [5].

Due to the constraint of the star-like morphology, both these C₆₀-ionomers seem to have an aggregation structure of “loose” hydrophobic-rich regions and a high water content for the aggregates. Such a structure is very different from the typical closely packed hydrophobic core structure for the linear type of surfactants. It will be interesting to know how the aggregation structure of loose hydrophobic regions for the star-like C₆₀-ionomers influences their interactions with surfactants, lipids, or polymers. Also, due to the unique physical characteristics of fullerenes and the star-like morphology, we expect that FC₁₀S can lead to different microstructures from that formed by SDS in complex solutions. For instance, in mixtures of SDS and dodecyltrimethylammonium (DTAB) [6,7] the transformation of the rod-like micelles into vesicles or lamellar sheets may be suppressed when the linear SDS is replaced by the star-like FC₁₀S (Fig. 1). In such cases, FC₁₀S may be used to stabilize the micellar phase of the mixtures. It is also interesting to study the effect of FC₁₀S in SDS-protein [8] or SDS-polymer systems [9,10], where bindings of surfactants to proteins or polymers have been observed. The surfactant-binding effect may have implications for applications of FC₁₀S in biomedical systems, such as preventing formation of the toxic β-sheet structure of amyloid β-peptide that is responsible for Alzheimer’s disease [11].

Here, we report a study of aqueous mixtures containing FC₁₀S and SDS. In this system we ask whether star FC₁₀S with SDS-like arms can absorb SDS and form compact core-shell structure similar to SDS micelles. In extracting the structural information of the mixed complex aggregates of C₆₀-ionomers and SDS we adapt SAXS and SANS with the contrast variation method [12,13] as described below.

2. Scattering model and contrast variation for SANS and SAXS

Small angle scattering (SAS) for particles of a monodisperse size in a colloidal solution can be modeled as [14]

$$I(Q) = I_0 \tilde{P}(Q) S(Q). \quad (1)$$

In the above equation $\tilde{P}(Q)$ is the normalized form factor with $\tilde{P}(0)=1$, and $S(Q)$ the structure factor. The wave vector transfer $Q=4\pi \sin(\theta/2)/\lambda$ is defined by the scattering angle θ and the wavelength λ of the radiation quanta, whereas $I_0=n_p(\rho-\rho_w)^2V^2$ is the scattering amplitude with the number density n_p and the volume V for the particles. The scattering length density (SLD) for the particles and the solvent are denoted by ρ and ρ_w , respectively. For rod-like particles,

$$\tilde{P}(Q) = \int_0^1 \left| \frac{2J_1(v)}{v} \frac{\sin(w)}{w} \right|^2 d\mu. \tag{2}$$

The above form factor is averaged from the spatial orientations of right-circular cylinders of radius r and length L , with $v=Qr(1-\mu^2)^{1/2}$, $w=(1/2)QL\mu$, and the first order Bessel function J_1 [15,16].

For a cylindrical aggregate containing, respectively, N_i , N_w , and N_s numbers of C₆₀-based ionomers FC₁₀S, water, and SDS molecules, we can construct a scattering length density $\rho = (N_i b_i + N_w b_w + N_s b_s)/V$ for the complex aggregate, where $V = (N_i V_i + N_w V_w + N_s V_s)$. The symbols b_i, b_w, b_s and V_i, V_w, V_s denote, respectively, the scattering lengths and volumes for FC₁₀S, D₂O, and SDS [17]. We can now write I_0 in Eq. (1) as

$$I_0 = n_p [N_i (b_i - \rho_w V_i) + N_s (b_s - \rho_w V_s)]^2. \tag{3}$$

From Eq. (3), we see that I_0 can be changed significantly when SDS molecules ($b_s = 16.0$ fm) in the aggregate are replaced by d-SDS ($b_s = 276.2$ fm) of a much higher scattering length, presuming that there are non-trivial SDS molecules in the aggregate ($N_s \neq 0$). Furthermore, the deuteration will not change the scattering profile, provided that SDS molecules distribute uniformly in the aggregate [17]. Here, we neglect the possible isotope effect on the structure of the aggregates, which seems safe when the system studied is not close to critical conditions for phase transitions [18,19]. An estimation for the scattering length density of FC₁₀S, SDS, d-SDS, and D₂O shows (see Fig. 2) that the SANS contrast for the complex aggregates in D₂O solutions is

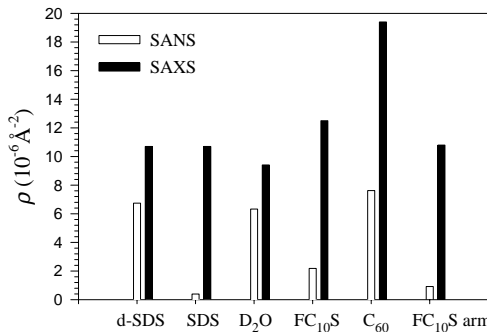


Fig. 2. SANS (empty bars) and SAXS (solid bars) scattering-length-density ρ for the related chemical groups. The volumes used in the calculations are 410 \AA^3 for SDS, 2780 \AA^3 for FC₁₀S, 377 \AA^3 for an FC₁₀S arm, and 524 \AA^3 for C₆₀.

mainly contributed by the arms of FC₁₀S and SDS of low ρ values, whereas the SAXS contrast for the same system is provided largely by the C₆₀ of FC₁₀S, which has a much higher scattering length density than that for water or the arms of FC₁₀S.

3. Experiment

3.1. Synthesis

The synthesis route for the fullerene-based ionomers hexa(sulfobutoxypentylcarboxy)[60]-fullerene has been reported in Ref. [5]. Here we only brief the procedures. The sodium naphthalide reagent was allowed to react with C₆₀ in toluene. Caprolactone was then added to the reaction mixture for the intermediate of hexa(hydroxypentylcarboxy)[60]fullerene sodium salt. The reaction of this sodium salt with 1,4-butane sultone was carried out to afford the product of hexa(sulfobutoxypentylcarboxy)[60]fullerene in 45% yield after purification.

3.2. Measurements

In preparing FC₁₀S/SDS mixtures, we kept the SDS concentration lower than the critical micelle concentration (CMC) for SDS, which is 8 mM [19], to avoid the complication due to the scattering contribution from pure SDS micelles. Under this condition, two contrast-variation systems with different FC₁₀S/SDS ratios were prepared. The first system included two D₂O mixtures of 2.33 mM of FC₁₀S ionomers, respectively, with 6-mM SDS and 6-mM d-SDS added. For the second system, a lower FC₁₀S concentration of 1.17 mM was used in another two D₂O solutions containing 6-mM SDS and 6-mM d-SDS, respectively.

Sample solutions were charged, individually, into quartz cells of a 5-mm path length for SANS measurements, which were conducted under a controlled temperature ($23 \pm 0.5^\circ\text{C}$) on the 8-m SANS instrument at the National Institute of Standards and Technology (NIST). Pinholes of 2.5 and 1 cm diameters separated by 4.1 m were used to collimate the incident beam of a wavelength of 5 Å. The wavelength dispersion $(\Delta\lambda/\lambda)_{\text{FWHM}}$ of the beam is 25%. With the center of the two-dimensional detector shifted 6° away from the direct beam and a sample-to-detector distance of 3.6 m, the data measured covered a Q -range from 0.01 to 0.2 \AA^{-1} . The transmissions measured for all sample solutions were all close to the 5-mm D₂O transmission 0.66. Data were corrected for sample transmission, background, and detector sensitivity, and normalized to an absolute scattering scale, scattering cross section per unit sample volume $I(Q)$, by comparison to the scattering from H₂O [20]. The uncertainty for the $I(Q)$ thus calibrated is estimated to be 5–10%.

SAXS measurements for the sample solutions contained in 1-mm-thick cells of Kapton windows were performed on the 8-m SAXS instrument at Tsing-Hua University, Hsinchu [21]. The incident beam, from an 18-kW rotating-anode X-ray source, was collimated by three pinholes of diameters 1.0, 1.0, and 2.0 mm, arranged in 3.1-m path length. With a beam wavelength of 1.54 Å and a sample-to-detector distance of

2.3 m, the SAXS instrument scanned the scattering intensity in a Q range from 0.02 to 0.22 \AA^{-1} . Data were collected by a two-dimensional area detector, and corrected for sample transmission, background, and detector sensitivity, and normalized to an absolute scattering scale by comparison to the scattering from a secondary standard sample of lead stearate. The accuracy for SAXS $I(Q)$ thus calibrated is within $\pm 10\%$.

4. Results and analysis

4.1. SANS and SAXS data

Fig. 3 shows the SANS data for the mixtures of 2.33-mM FC_{10}S with 6-mM SDS (squares) and 6-mM d-SDS (circles), respectively. The apparent difference in the intensities and the similarity in the scattering profiles highly suggest that the system contains complex aggregates of FC_{10}S with SDS, as explained in the previous section for the scattering characteristics of the complex aggregates. In addition, the profiles for the mixtures measured in most of the Q -region resemble that for the pure FC_{10}S solution of 2.33 mM (diamonds), indicating that the complex aggregates have a cylinder-like structure similar to that for pure FC_{10}S aggregates observed in a previous study [5].

Since d-SDS has a scattering length density close to that for D_2O (see Fig. 2), its monomers or micelles in D_2O solutions are virtually invisible to neutrons. Therefore, most of the data measured in an absolute intensity scale for the $\text{FC}_{10}\text{S}/\text{d-SDS}$ mixture

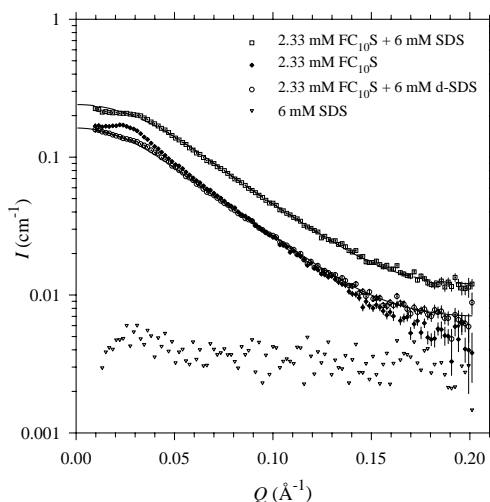


Fig. 3. SANS data for the two sample mixtures of 2.33-mM FC_{10}S containing 6-mM SDS (squares) and 6-mM d-SDS (circles), respectively. The two sets of contrast data are fitted (dashed and solid curves) jointly with the SAXS data (see Fig. 4) by a rod-like particle model with a hard sphere interaction. Also shown are the SANS data for a pure FC_{10}S solution of 2.33 mM (diamonds) and the SANS data for a pure SDS solution of 6 mM (triangles).

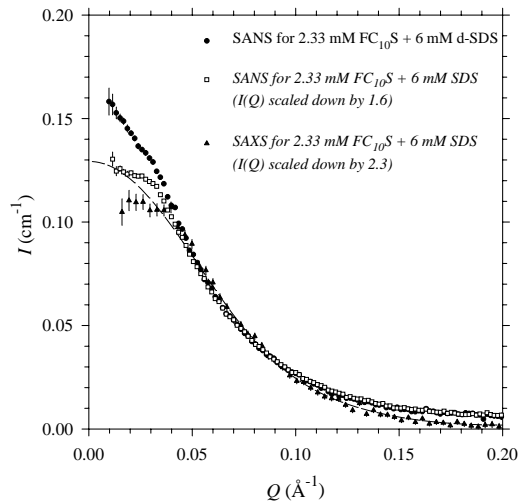


Fig. 4. The SANS data (squares) and SAXS data (triangles) for the sample mixtures of 2.33-mM $\text{FC}_{10}\text{S}/6\text{-mM SDS}$ are scaled down by 1.6 and 2.3, respectively, to superimpose the SANS data (circles) for the $\text{FC}_{10}\text{S}/\text{d-SDS}$ mixture. The SAXS data are fitted (dashed curve) together with the two sets of SANS data by a rod-like model.

are nearly the same as that for the pure FC_{10}S solution. For a closer look at the low- Q region ($Q \lesssim 0.03 \text{ \AA}^{-1}$), the profile for the $\text{FC}_{10}\text{S}/\text{d-SDS}$ mixture departs from that for the pure FC_{10}S solution. This deviation should result from (1) a smaller rod length for the $\text{FC}_{10}\text{S}/\text{SDS}$ aggregates, and (2) smaller interactions between the complex aggregates (corresponding to a less obvious scattering shoulder) for the mixing system, as compared with the pure FC_{10}S system [17]. The smaller interaction observed for the complex aggregates may be due to a charge-screening effect induced by the free ionic d-SDS monomers in the solution [19]. As in common ionic micellar solutions of high concentrations, the charge screening effect is often achieved by adding salt into the solutions [22,23].

In Fig. 3, we also show the SANS result (triangles) for a pure SDS solution of 6 mM in D_2O . The relatively flat SANS spectrum confirms that the scattering contribution from SDS micelles or monomers is negligible at this surfactant concentration, since 6 mM is lower than the CMC of SDS.

After a proper scaling for superimposing, we observe that the SANS profile for the $\text{FC}_{10}\text{S}/\text{SDS}$ mixture deviates downward slightly from that for the $\text{FC}_{10}\text{S}/\text{d-SDS}$ mixture in the small- Q region as shown in Fig. 4. Since the structure factor of a system does not change with the selected deuteration of SDS in the system [17], this discrepancy should result solely from a difference in the form factor. In fact, the radius of gyration R_g may change with the contrast variation used, when the deuterated component is not uniformly distributed in an aggregate [17]. The small discrepancy observed, therefore, indicates that the SDS molecules distribute in a slightly inward region of the complex aggregate. This leads to a smaller R_g for $\text{FC}_{10}\text{S}/\text{SDS}$ aggregates in D_2O , as compared

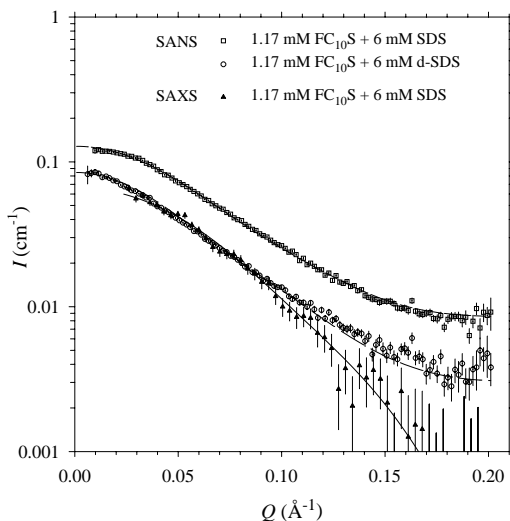


Fig. 5. The two sets of SANS data and one set of SAXS data for the sample mixtures of 1.17-mM FC_{10}S are fitted jointly (dashed and solid curves) with the same model used for the first system.

to the R_g for $\text{FC}_{10}\text{S}/\text{d-SDS}$ aggregates in D_2O . (Numerical values for R_g will be given below.)

For the SAXS result, since the X-ray scattering length densities for SDS and FC_{10}S arms are both close to that for water, the SAXS profiles measured for $\text{FC}_{10}\text{S}/\text{SDS}$ mixtures are dominated by the C_{60} cages of FC_{10}S (see Fig. 2). After scaling down by a factor of 2.3, the SAXS profile measured for the mixture of 2.33-mM FC_{10}S and 6-mM SDS (triangles in Fig. 4) can overlap approximately the SANS profiles for the same solution. In the low- Q region, the SAXS profile deviates downwards from the SANS profiles. These SAXS features indicate that the C_{60} cages in the aggregate distribute in a cylinder-like region of similar radius but smaller length, in comparison with the distribution of FC_{10}S arms observed from the SANS data. In other words, the FC_{10}S arms extend outwards slightly more than the C_{60} cages do, especially in the longitudinal direction of the aggregate.

For the second system of a lower FC_{10}S concentration of 1.17 mM, Fig. 5 shows the SAS data for the two sample solutions, respectively, treated with 6-mM SDS (squares and triangles) and 6-mM d-SDS (circles). These three scattering profiles are similar to those for the first system. Indeed, after normalizing to the FC_{10}S concentration, the three SAS profiles can overlap well the corresponding profiles of the first system. Such a result implies that (1) the structure of the complex aggregates does not change with the FC_{10}S concentrations studied, and (2) the scattering intensity is essentially linearly proportional to the FC_{10}S concentration. The latter suggests that nearly all C_{60} -based star ionomers in the mixtures form complex aggregates [3], namely, $n_p \approx C/N_i$, where C is the concentration of FC_{10}S and N_i the average number of FC_{10}S per aggregate.

4.2. Model fitting

In extracting the structural information for the FC₁₀S/SDS aggregates, we fit jointly the three sets of SAS data for the solutions of 2.33-mM FC₁₀S using a rod-like particle model [4,18]. Adapting $V_s=410 \text{ \AA}^3$ from Cabane et al. [24] and using $n_p=C/N_i$, we have independent fitting parameters N_i , V_i , and N_s (see Eqs. (2) and (3)). In principle, the three parameters N_i , V_i , and N_s can be determined uniquely by the absolute scattering intensities of the three sets of contrast data. Since the interparticle interaction is small, we may approximate $S(Q)$ for the system by a structure factor generated from the Percus–Yevick hard sphere model [25], with a volume fraction $\eta=n_pV$ and an effective sphere diameter σ from $V=\pi r^2L=4/3\pi(\sigma/2)^3$. This approximation is reasonable when the L/σ ratio is smaller than about 2 [17]. For larger values, we use a more elaborated form for σ as described in Ref. [5]. Note, the common $S(Q)$ used for the three sets of SAS data adds no additional parameters to the fitting process. We also take into account the smearing effect of $I(Q)$ due to the divergence and the wavelength dispersion of the beam for the SANS and SAXS data, respectively, in a non-linear fitting process for a least χ^2 contributed by the three sets of data.

The fitting result (dashed and solid curves in Fig. 3 for the SANS data, dashed curve in Fig. 4 for the SAXS data) demonstrates that all three sets of data can be described simultaneously well by cylindrical-like particles having compositions of $N_i=15 \pm 1$ and $N_s=11 \pm 1$, with $V_i=2420 \pm 50 \text{ \AA}^3$. The dry volume V_i obtained for FC₁₀S is close to 2780 \AA^3 estimated from a C₆₀-cage and six arms of FC₁₀S. The R_g values for the complex aggregates can be obtained from the best-fitted r and L values summarized in Table 1 using $R_g=(r^2/2+L^2/12)^{1/2}$ [15]. In fact, the R_g values are more meaningful than the L values that are determined using the approximation of a homogeneous aggregate in the model. They are 32.9 and 28.6 Å, respectively, for the FC₁₀S/d-SDS and FC₁₀S/SDS aggregates observed by SANS, and 24.3 Å for the

Table 1
Summary of the fitting results for the SAS data^a

	FC ₁₀ S (mM)	SDS (mM)	R_g (Å)	r (Å)	L (Å) ^b
SANS	2.33	6.0 (d-SDS)	32.9	19.5 ± 0.6	103 ± 6
	2.33	6.0 (SDS)	28.9	19.5 ± 0.6	88 ± 4
SAXS	2.33	6.0 (SDS)	24.8	19.2 ± 1.5	72 ± 10
SANS	1.17	6.0 (d-SDS)	32.9	19.5	103
	1.17	6.0 (SDS)	28.9	19.5	88
SAXS	1.17	6.0 (SDS)	24.8	19.2	72

^aThe SAS data are fitted using a rod-like particle model with a hard sphere interaction. The radius of gyration R_g is derived from the radius r and length L fitted for the cylinder-like aggregates. For the mixtures of 2.23-mM FC₁₀S, the volume fraction $\eta=0.012$ and $S(0)=0.91$, whereas $\eta=0.006$ and $S(0)=0.95$ for the mixtures of 1.17-mM FC₁₀S. The aggregation numbers obtained for the complex aggregates in both mixtures are $N_i=15 \pm 1$ for FC₁₀S and $N_s=11 \pm 1$ for SDS (or d-SDS), with the dry volume $V_i=2420 \pm 50 \text{ \AA}^3$ for FC₁₀S. Note, an ellipsoidal model, with a semi-major axis of $\approx 70 \text{ \AA}$ and a semi-minor axis of $\approx 20 \text{ \AA}$, can fit the data as well with the same N_i , N_s , and V_i values as that obtained from the rod-like model.

^bThe length of a stretched FC₁₀S arm is about 15 Å.

FC₁₀S/SDS aggregates observed by SAXS. These R_g values relate subsequently to the distribution of FC₁₀S arms, SDS molecules, and the C₆₀-cages of FC₁₀S in the complex aggregate, as discussed previously. Again, the result indicates that the fullerenes of the star FC₁₀S distribute more inwards in the complex structure. While the SDS adsorbed fills mainly in the center region of the rod-like aggregates, but not the ends of the aggregate. Compared to pure FC₁₀S aggregates, the radius for the complex aggregates obtained (see Table 1) is nearly the same, whereas the length is significantly smaller (~50%). Using $V = \pi r^2 L = N_i V_i + N_w V_w + N_s V_s$ with $r = 19.5 \text{ \AA}$, $L = 103 \text{ \AA}$, and $V_w = 30.3 \text{ \AA}^3$ [22] we can deduce a water content $N_w = 2700 \pm 200$ for the complex aggregate. Such a water content occupies roughly 60% of the aggregate volume.

In Fig. 5, we show that the three sets of SAS for the second system of 1.17-mM FC₁₀S can also be fitted (dashed and solid curves) satisfactorily using exactly the same structural parameters (see Table 1) as that for the first system. The result implies that the critical concentration for forming the complex aggregates of FC₁₀S/SDS is much lower than the FC₁₀S concentrations studied.

5. Discussion and conclusions

Using SAXS and SANS with the contrast variation method, we have found that C₆₀-based star ionomers FC₁₀S form complex aggregates with SDS in water solutions. In comparison with pure FC₁₀S aggregates [5], the aggregation number of FC₁₀S in FC₁₀S/SDS mixtures is significantly lowered (~50%) due to the intervening of SDS molecules. The ratio N_s/N_i between the deduced aggregation numbers of SDS and FC₁₀S is ≈ 0.7 , which can be regarded as a mean SDS-absorption efficiency for FC₁₀S. Furthermore, the higher SDS-excess concentration in the second system of a lower FC₁₀S concentration does not lead to a higher SDS-absorption efficiency. It seems that the SDS-absorption efficiency for FC₁₀S is insensitive to the SDS concentrations in the mixtures, when the SDS concentrations are lower than their CMC. From the composition obtained for the complex aggregates, we deduce the free SDS in the 2.33 and 1.17 mM FC₁₀S/SDS systems to be about 4.4 and 5.2 mM, respectively.

The SDS-absorption efficiency observed for FC₁₀S is low, considering that each star ionomer FC₁₀S has plenty of space in between the six SDS-like arms ready for SDS to settle in. For a comparison, the aggregation number for pure SDS micelles is > 60 [25]. Structurally speaking, the feature of loose hydrophobic regions for the FC₁₀S/SDS complex aggregates, in comparison with the compact hydrophobic core for pure SDS micelles, suggests that the affinity of SDS to FC₁₀S may not compete with the affinity between FC₁₀S themselves. As a consequence, SDS molecules prefer not to park their aliphatic tails in the roomy core-near region of FC₁₀S of a hydrophobic attribute, for a compact core-shell structure that we have anticipated.

The mechanism for forming the FC₁₀S/SDS aggregates of small amount of SDS molecules may be explained by the existence of arm-rich regions in the complex aggregates. These arm-rich regions, presumably, are formed through the interactions between the aliphatic parts of the FC₁₀S arms. For absorbing SDS monomers in a mixture of an SDS concentration lower than the CMC for SDS, the arm-rich sites must

provide a lower interfacial energy for the free SDS monomers to compensate the entropy loss of the system due to absorption. Following the argument, the SDS-absorption efficiency for FC₁₀S is limited by the arm-rich sites available in the complex aggregates. Estimated from the composition for the complex aggregates obtained, each absorbed SDS associates averagely with 8 SDS-like arms from several FC₁₀S in a complex aggregate. This number of arms should be sufficient for packing (trapping) an SDS monomer. From the above discussion, a higher SDS-absorption efficiency may be achieved by C₆₀-based star ionomers of more than six SDS-like arms, since more arms anchored on a C₆₀ cage will increase the density of the arm-rich sites. The same goal may also be reached by lowering the system's entropy influence by lowering temperature.

Acknowledgements

We acknowledge the support of the National Institute of Standards and Technology for the use of the 8-m SANS instrument. This work was supported by the grant for the user-training program of the Institute of Nuclear Energy Research and the National Science Council, grant NSC89-2113-M-007-018.

References

- [1] Y.L. Lai, W.-Y. Chiou, F.J. Lu, L.Y. Chiang, *J. Pharmacol.* 126 (1999) 778.
- [2] S.S. Huang, Y.H. Chen, L.Y. Chiang, M.C. Tsai, *Fullerenes Sci. Technol.* 7 (4) (1999) 551.
- [3] U. Jeng, T.-L. Lin, C.-S. Tsao, C.-H. Lee, L.Y. Wang, L.Y. Chiang, C.C. Han, *J. Phys. Chem. B* 103 (1999) 1059.
- [4] C.-S. Tsao, T.-L. Lin, U. Jeng, *J. Phys. Chem. Solids* 60 (1999) 1351.
- [5] W.-J. Liu, U. Jeng, T.-L. Lin, T. Canteenwala, L.Y. Chiang, *Fullerenes Sci. Technol.* 9 (2) (2001) 131.
- [6] K.L. Herrington, E.W. Kaler, D.D. Miller, J.A. Zasadzinski, S. Chiruvolu, *J. Phys. Chem.* 97 (1993) 13 792.
- [7] M. Bergström, J.S. Pedersen, *Langmuir* 14 (1998) 3754.
- [8] S.-H. Chen, J. Teixeira, *Phys. Rev. Lett.* 57 (1986) 2583.
- [9] J.-H. Kim, M.M. Domach, R.D. Tilton, *J. Phys. Chem.* 103 (1999) 10 582.
- [10] B. Cabane, R. Duplessix, *J. Phys.* 48 (1987) 651.
- [11] K.J. Marcinowski, H. Shao, E.L. Clancy, M.G. Zagorski, *J. Am. Chem. Soc.* 120 (1998) 11 082.
- [12] J. Penfold, E. Staples, I. Tucker, *Adv. Colloid Interface Sci.* 68 (1996) 31.
- [13] I.P. Purcell, J.R. Lu, R.K. Thomas, A.M. Howe, J. Penfold, *Langmuir* 14 (1998) 1637.
- [14] T.-L. Lin, *Physica B* 180&181 (1992) 505.
- [15] L.A. Feigin, D.I. Svergun, *Structure Analysis by Small-Angle X-ray and Neutron Scattering*, Plenum, New York, 1987, p. 69.
- [16] S.H. Chen, *Ann. Rev. Phys. Chem.* 37 (1986) 351.
- [17] S.-H. Chen, T.-L. Lin, in: K. Sköld, D.L. Price (Eds.), *Methods of Experimental Physics—Neutron Scattering in Condensed Matter Research*, Vol. 23B, Academic Press, New York, 1987 (Chapter 16).
- [18] T. Zemb, P.J. Charpin, *Physique* 46 (1985) 249.
- [19] B. Cabane, R.J. Duplessix, *Physique* 43 (1982) 1529.
- [20] C.J. Glinka, J.G. Barker, B. Hammouda, S. Krueger, J.J. Moyer, W.J. Orts, *J. Appl. Crystallogr.* 31 (1998) 430.
- [21] K. Linliu, S.-A. Chen, T.L. Yu, T.-L. Lin, C.-H. Lee, J.-J. Kai, S.-L. Chang, J.S. Lin, *J. Polym. Res.* 2 (1995) 63.

- [22] Y.C. Liu, C.Y. Ku, P. LoNostro, S.-H. Chen, *Phys. Rev. E* 51 (1995) 4598.
- [23] J.B. Hayter, J. Penfold, *J. Chem. Soc. Faraday Trans. I* 77 (1981) 1851.
- [24] B. Cabane, R. Duplessix, T. Zemb, *J. Phys.* 46 (1985) 2161.
- [25] I. Krakovsky, Z. Bubenikova, H. Urakawa, K. Kajiwara, *Polymer* 38 (1997) 3637.